

2020-14

by Zulfa Nailul Ilmi

Submission date: 24-May-2021 10:27PM (UTC+0800)

Submission ID: 1593182620

File name: 2020-14.pdf (7.51M)

Word count: 11037

Character count: 68445

Article

Characterization of Alginate from *Sargassum duplicatum* and the Antioxidant Effect of Alginate–Okra Fruit Extracts Combination for Wound Healing on Diabetic Mice

Zulfa Nailul Ilmi ¹, Pugar Arga Cristina Wulandari ¹, Saikhu Akhmad Husen ², Dwi Winarni ², Mochammad Amin Alamsjah ³, Khalijah Awang ⁴, Marco Vastano ⁵, Alessandro Pellis ^{5,6}, Duncan Macquarrie ⁵ and Pratiwi Pudjiastuti ^{1,*}

¹ Department of Chemistry, Faculty of Science and Technology, Airlangga University,

Surabaya 60115, Indonesia; zulfanailulilmi@gmail.com (Z.N.I.); cristinapugar@gmail.com (P.A.C.W.)

² Department of Biology, Faculty of Science and Technology, Airlangga University, Surabaya 60115, Indonesia; saikhu-a-h@fst.unair.ac.id (S.A.H.); dwi-w@fst.unair.ac.id (D.W.)

³ Department of Marine, Faculty of Fisheries and Marine, Airlangga University, Surabaya 60115, Indonesia; alamsjah@fpm.unair.ac.id

⁴ Department of Chemistry, Faculty of Science, University of Malaya, Kuala Lumpur 50603, Malaysia;

khalijah@um.edu.my

⁵ Department of Chemistry, University of York, Heslington, York YO10 5DD, UK;

marco.vastano@york.ac.uk (M.V.); alessandro.pellis@york.ac.uk (A.P.);

duncan.macquarrie@york.ac.uk (D.M.)

⁶ Department for Agrobiotechnology, IFA-Tulln, Institute for Environmental Biotechnology, University of Natural Resources and Life Sciences, Vienna, Konrad Lorenz Strasse 20, A-3430 Tulln an der Donau, Austria

* Correspondence: pratiwi-p@fst.unair.ac.id; Tel: +62-856-3390-952

47

Received: 12 July 2020; Accepted: 27 August 2020; Published: 2 September 2020



Featured Application: In this study, we evaluated antioxidant effect of alginate–okra extracts combination as topical application (ointment) for wound healing on diabetic mice. Characterization of alginate was used to determine structural characteristics and Okra fruit extract was determined total flavonoids content that have effect of the antioxidant properties. The antioxidant properties of extracts combination reduce blood-glucose levels to non-diabetic conditions (normal) significantly by topical application of diabetic open wound. These conditions can accelerate the activities of wound-healing processes on diabetic mice. The activities of wound-healing processes were performing periodically by histopathology test on skin tissue to evaluated wound healing parameters (wound area, neutrophils, macrophages, fibrocytes, fibroblasts and collagen densities).

Abstract: Diabetes mellitus is a group of metabolic disorders characterized by high blood-glucose levels over a prolonged period that causes complications when an open wound is present. Alginate is an antioxidant and a good absorbent of exudates. Okra fruit contains flavonoids that can act as antioxidants. The antioxidant properties of extracts combination reduce blood-glucose levels significantly to accelerate the activities of wound-healing processes on diabetic mice. Alginate was characterized by Size Exclusion Chromatography–Multiple Angle Laser Light Scattering (SEC–MALLS), thermal stability and Proton Nuclear Magnetic Resonance (¹H–NMR). The evaluation of wound healing on 36 male mice were divided into 12 groups including normal control (NC), diabetics control (DC), alginate (DA) and alginate–okra (DAO) groups in three different times by histopathology test on skin tissue. The results of SEC–MALLS analysis showed that alginate as single and homogeneous polysaccharide. The ¹H–NMR spectrum showed that the mannuronate/guluronate ratio of the used alginate was 0.91. Alginate, okra fruit extract and their combination were classified as moderate and strong antioxidants. The numbers of fibrocytes, fibroblasts, collagen densities had

9

significantly increased from three to seven days. In contrast, wound width, neutrophil, macrophages had significantly decreased at 14 days. The administration of extracts combination increased the re-epithelization of the wound area and wound-healing process on diabetic mice.

Keywords: alginate; *Sargassum duplicatum*; okra; antioxidant; diabetic; wound healing

1. Introduction

Diabetes mellitus (DM) is a disease that causes complex metabolic disorder associated with insulin resistance, impaired insulin signaling, β -cell dysfunction, abnormal glucose levels and changes in lipid metabolism [1]. The condition of high blood-glucose level (hyperglycemia) is caused by impaired of insulin production or secretion, insulin resistance. Hyperglycemia causes an increase of reactive oxygen species (ROS) levels which is not counterbalanced by an adequate supply of antioxidants. This imbalance can cause oxidative stress which is the source of the development of diabetes mellitus complications because it triggers the development of insulin resistance [2]. Complication of diabetes mellitus causes chronic wound healing disorders such as inflammation, tissue formation granulation, re-epithelization and tissue renovation [3].

All these complications often result in open wounds with long-term healing problems that frequently cause the need of amputation. Epidemiological data report that 2.8% of the world's population suffered from diabetes in 2000, and the trend is expected to increase up to 4.4% by 2030 and also the percentage of amputation in diabetic wounds is expected to increase to about 50–70%. The excessive generation of ROS in diabetic conditions is caused by acute serum glucose and the accumulation of advanced glycation end-products (AGEs). Endogenous or externally supplied antioxidants (due to inadequate supply of antioxidants) can lower ROS levels through the reduction of cellular molecular oxidation. Antioxidants obtained can neutralize the oxidative stress to improve wound healing in diabetes [5].

Wound-healing processes in diabetic mice have been usually treated performed in general through the administration of topical medications, topical or systemic antibiotics and vascular reconstruction. However, open wound healing has a weakness due to the use of chemical substances that cause long-term side effects in diabetics [6,7].

Alginate is a natural polysaccharide produced from *Sargassum* sp. (among others) containing α -L-guluronic acid (G) and β -D-mannuronic acid (M) residues [8]. Alginate—in form of hydrogels, foams, films, nanofibers, topical formulations or wafers—has been widely used as bioactive dressing for wound healing [9]. As other biocompatible materials, alginate can be loaded natural compound or drugs for improved wound-healing process like simvastatin [10], honey [11], *Aloe vera* [12], curcumin [13]. Alginate can maintain a moist condition in the wound area and acts as antibacterial and antioxidant agent, absorb wound exudate as a hemostatic agent [14–16]. Moreover, alginate with composition of guluronic acid residue (G) higher than Mannuronic acid residue (M) produce a more rigid structure, thereby increasing the availability of alginate ions to make it easier to absorb exudate and proton donor in the free radical scavenging process (antioxidant), so it is easy to wound healing. Molecular weight of polysaccharides affects the ability of radical scavenging. Reduction in molecular weight below 12 kDa can affect the conformational chain or guluronic acid content which has an impact on the availability of alginate ions in radical scavenging [17].

Abelmoschus esculentus L. is known as okra plant that contains many flavonoids that play a major role as antioxidant agents against ROS to inhibit free radicals [18]. Hence, the okra fruit may be used as an alternative medicine for the reduction of blood glucose and cholesterol levels as antidiabetic and antihyperlipidemic properties [19,20]. In addition, okra fruit extract can accelerate wound healing through the induction of the production of cytokine and growth factor productions [21].

In this study, we report the characterization of alginate from *Sargassum duplicatum* (J. Agardh) to evaluate its characteristic on the wound-healing process. The novelty of this study lies in investigating antioxidant effect of alginate from *S. duplicatum* and okra fruit extracts combination for wound-healing process in diabetic mice. The activities of wound-healing process were performed by using an alginate-okra extracts ointment on wound performing periodically by histopathology tests on diabetic mice skin tissues.

2. Materials and Methods

2.1. Plants Collection

Brown seaweeds of *S. duplicatum* were taken from Madura Island, Indonesia in May 2018. The species was identified at Oceanographic Research Center, LIPI, Jakarta, Indonesia (Approval Reference Number: 1/3/18-id/2018). Okra (*A. esculentus*) fruits were obtained from Rungkut district, Surabaya, Indonesia. Identification of species was conducted at the Laboratory Biosystem of Biology Department, Airlangga University, Surabaya, Indonesia.

2.2. Extraction of Sodium Alginate

The method of extraction of alginate from *S. duplicatum* referred to research from Great Hall of Products and Biotechnology of Marine and Fisheries, Jakarta with modification from LIPI. Sample of *S. duplicatum* was cleaned, dried and grinded. Two hundred grams of dried sample was soaked using 0.1% (1:75 *w/v*) KOH for two hours, then added of 1% (1:30 *w/v*) HCl was added and let it react for an hour. The residue was then washed with water to a neutral pH and added 2% (1:30 *w/v*) Na₂CO₃ at 60–70 °C for two hours with constant stirring. The extract was added 10% of HCl until a pH in the 2.8–3.2 range was reached. Two percent Na₂CO₃ at pH 7 was added until the formation of a gel filtrate was obtained. Gel filtrate was bleached with 4% (1:2 *v/v*) NaOCl for 15 h. Filtrate was refined by using isopropyl alcohol for 30 min to form fibers [22]. The extraction of sodium alginate powder from *S. duplicatum* was pale yellow color and 12.140 ± 0.684% yield based on the dry weight of brown seaweed.

2.3. Characterization of Sodium Alginate

The characterization of sodium alginate was conducted using the SEC-MALLS for determination of molecular weight of alginate. The G/M ratio of sodium alginate from *S. duplicatum* was identified by ¹H-NMR spectroscopy. The thermogravimetric analysis (TGA) was performed to evaluate the strength and thermal stability of the polymer matrix by recording phase transitions and the degradation pattern of alginate based on percent of weight loss and its decomposition under nitrogen gas. All measurements were conducted at the Department of Chemistry, University of York, Heslington, UK.

2.3.1. SEC-MALLS

The molecular weight of alginate and its distribution were determined using the gel permeation chromatography technique using a Shimadzu HPLC system (Shimadzu UK Limited, Milton Keynes, UK) comprising a CBM-20A Controller, LC-20AD Pump with degasser, SIL-20A Autosampler and SPD-20A detector; and HELEOS-II light scattering and Optilab rEx refractive index detectors supplied by Wyatt. A PL Aquagel-OH mixed column (7.5 mm × 300 mm, 8-μm particle size; Agilent Technologies, Santa Clara, CA, USA) and a PL Aquagel-OH mixed guard column (7.5 × 50 mm, 8-μm particle size; Agilent Technologies, USA) were used as the stationary phase with 50-mM sodium nitrate dissolved in deionized water as mobile phase constituting. The flow rate of the mobile phase was 0.5 mL min⁻¹ [23]. The alginate solution (1.5 mg mL⁻¹), dissolved in deionized water, were filtered through a nylon membrane (Whatman, UK) before analysis. For the dn dc⁻¹ value, 0.168 was used [24].

2.3.2. Nuclear Magnetic Resonance (NMR) Spectroscopy

¹H-NMR spectroscopy analysis was performed on a JEOL JNM-ECS400A spectrometer (JEOL, Peabody, MA, USA) at a frequency of 400 MHz for ¹H. D₂O was used as NMR solvent if not otherwise specified. All samples were freeze dried before analysis [25]. Acquisition parameter were: T = 90 °C and 128 scans. samples were not pre-hydrolyzed like in reference [25] since the alginate was fully soluble in D₂O.

2.3.3. Thermogravimetric Analysis (TGA)

TGA was performed on a PL Thermal Sciences STA 625 thermal analyzer (PL Thermal Sciences Limited, Surrey, UK). 10 mg of accurately weighed sample in an aluminum sample cup was placed into the furnace with a N₂ flow of 100 mL min⁻¹ and heated from room temperature to 625 °C at a heating rate of 10 °C min⁻¹. From the TGA profiles the temperatures at 10% and 50% mass loss (TD₁₀ and TD₅₀, respectively) were subsequently determined [26].

2.4. Extraction of Okra Fruits

Green okra fruits were cut, dried and milled until a fine powder was obtained. The sample was soaked by using 96% ethanol (1:3 (w/v)) and the procedure was thoroughly repeated [27]. The filtrate was evaporated under vacuum at 50 °C and then freeze dried. The sample was kept at 4 °C until further use.

2.5. Determination of Total Flavonoids Content

The total flavonoids of the okra fruits extract were determined by colorimetric aluminum chloride using UV-vis spectrophotometer [27]. Five milligrams of extract was added 5 mL 96% of ethanol until 10 mL volume. Sample solution (1 mL) was put in a 10-mL volumetric flask and added 1 mL of 10% AlCl₃ and 8 mL of 5% potassium acetate solution. The mixtures were incubated for 30 min at room temperature and the absorbance was determined at 431 nm. The calibration curve was made from the standard in concentrations variation of 0.01-, 0.02-, 0.03-, 0.04- and 0.05-mg/mL quercetin, respectively. The concentration variations of samples were made as same as standard of quercetin. The standard curve was plotted between concentration and absorbance, so that the equation obtained linear regression and expressed as mg quercetin equivalent (QE)/g okra fruit extract.

2.6. Antioxidant Assay

Antioxidant assay were performed on alginate and okra fruit extracts and their combination using DPPH method. The DPPH solution was prepared as 50.0-µg/mL concentration in methanol and extracts stock solutions were prepared as 1000.0-µg/mL concentration in methanol. The extract stock solutions were diluted in various of concentrations in methanol as 200.0-, 150.0-, 125.0-, 100.0-, 75.0-, 50.0-, 25.0-, 15.0-, 10.0- and 6.0-µg/mL concentrations. Dilution series of the samples as 100 µL and 100 µL of DPPH solution were added into 96-well plates. The mixtures were incubated in dark chamber for 30 min and was determined the absorbance at 517 nm by using an ELISA reader [28]. The radical DPPH scavenging activity was expressed as radical DPPH scavenging percentage using the formula:

$$\text{Radical DPPH scavenging (\%)} = \frac{A_{\text{DPPH}} - A_{\text{sample}}}{A_{\text{DPPH}}} \times 100\%$$

where, A_{DPPH} was absorbance of DPPH solution and A_{sample} was absorbance of DPPH solution in the presence of samples. IC₅₀ values of the extracts were calculated from graphs plotting of radical DPPH scavenging (%) and concentration of the sample solutions [29].

2.7. Preparation and Induction of the Diabetic Mice

Mice (*Mus musculus*) adult male, BALB/c strains having 3–4 months of age and a body weight in the 20–35-g range were purchased from Faculty of Pharmacy, Airlangga University, Surabaya. The ethical clearance for treating animals and all the experimental protocol were approved by Faculty of Veterinary Medicine, Airlangga University, Surabaya, Indonesia with Approval Reference Number: 2. KE. 049.04.2019 (4 April 2019). Mice were acclimated at 12-h light and 12-h dark rotating system for two weeks. Food and beverage were guarded during research. Mice were then fed with lard for five weeks at a dose of 0.3 mL (oral) to obtain high fat diet. Mice were induced streptozotocin (STZ) using multiple low dose method 30 mg/kg body weight as much as 0.15 mL for 8 days at intraperitoneal (i.p.) to induce Type II diabetes mellitus [30]. The body weight of mice was measured before and after the administration of lard and STZ induction. Meanwhile, the blood-glucose levels were determined after STZ induction and after 3, 7 and 14 days of treatments.

2.8. Animal Grouping and Treatments

The thirty-six mice were divided into 12 groups: three and nine groups for non-diabetic as normal (N) and diabetic (D) groups, respectively. Each group contains three mice for 3, 7- and 14-day observation [24]. Non-diabetic mice were divided into 3 groups as normal control (NC₃, NC₇ and NC₁₄), while diabetic mice are divided into nine groups: three of diabetic control groups (DC₃, DC₇ and DC₁₄), three of alginate treatment groups (DA₃, DA₇ and DA₁₄) and three of alginate–okra treatment groups (DAO₃, DAO₇ and DAO₁₄) were given the Vaseline, Vaseline–alginate and Vaseline–alginate–okra ointments, respectively. The ointment was homogenized as single dose of 50 mg/kg body weight. The replication of the animal was based on the formula of Federer (1967) [31]. Mice were wounded to give 1-cm length wounds on the *glutea* (buttocks).

2.9. Wound Healing Observation

The histopathology preparation of skin tissue was conducted based on the method which was performed by the laboratory of Veterinary Pathology of Airlangga University. The histopathology test was observed in some parameters of wounds such as number of neutrophils, macrophages, fibrocytes, fibroblasts, collagen densities and cell regeneration areas (wound width) using a light microscope and the ImageJ software. Neutrophils were recognized as polymorphonuclear cells, lobulated nucleus which have small granules in their cytoplasm. Macrophages in connective tissue of healing area derived from monocytes which were identified as large, round cells with round nucleus and often have vacuolated cytoplasm because of their phagocytic activity. Fibroblasts are large flat and irregular shape cells, containing an oval prominent shaped nucleus and basophilic cytoplasm. In contrast, fibrocytes are inactive form of fibroblast which have darkly stained elongated nuclei, spindle shape and acidophilic cytoplasm.

2.10. Statistically Analysis

All the observations of wound healing were presented as a mean \pm standard error mean (SEM). The statistical analysis of wound healing observations was performed using normality and homogeneity test, one-way ANOVA and Duncan test. Nonparametric of Kruskal–Wallis and Mann–Whitney test were used if the results of normality and homogeneity were not qualified ($\alpha = 0.05$). The difference between the various mean were calculated by using IBM company (Corporate headquarters 1 New Orchard Road Armonk, New York 10504-1722, United States US: 914-499-1900) with the SPSS 20.0 software.

3. Results

3.1. Characterization of Sodium Alginate

3.1.1. Analysis of SEC-MALLS

Sodium alginate from *S. duplicatum* was characterized by SEC-MALLS to determine molecular weight and polydispersity index. The average molecular weight of alginate *S. duplicatum* was determined via SEC-MALLS analysis (Figure 1a). Sodium alginate extracted from *S. duplicatum* contains polysaccharides with weight-average molecular weight (M_w) and number-average molecular weight (M_n) of 3.535×10^4 g/mol and 2.015×10^4 g/mol, respectively. Molecular weight of commercial alginate products from brown seaweed about $0.32\text{--}4.0 \times 10^5$ g/mol [32]. Alginate's dispersity (M_w/M_n) as 1.76, showing a good homogeneity of the polysaccharide alginate from *S. duplicatum*.

3.1.2. Thermogravimetric Analysis (TGA)

TGA was required to check the thermal stability and strength of the polymer matrix. TGA was used to determine the degradation temperature and the overall thermal stability of alginate. Thermal stability and strength of the polymer matrix of the alginate from *S. duplicatum* was determined via thermogravimetric analysis (Figure 1b). The 5% of the mass was lost (TD₅) at 75 °C, it indicated that water loss. The 10% of the lost mass (TD₁₀) occurred at a temperature of 140 °C. The temperature when 20% of the mass was lost (TD₂₀) occurs at 223 °C. That is indicated as the destruction of the glycosidic bond [33]. The 50% of the lost mass (TD₅₀) occurred at 380 °C. That is indicated as the material of carbon intermediates charcoal [34].

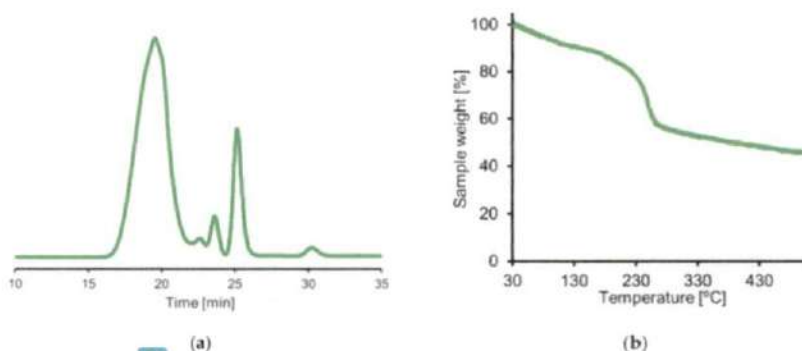


Figure 1. (a) Size Exclusion Chromatography-Multiple Angle Laser Light Scattering (SEC-MALLS) profile and (b) TGA of the sodium alginate from *Sargassum duplicatum*.

3.1.3. Proton Nuclear Magnetic Resonance (¹H-NMR) Analysis

The analysis was done according to Llanes et al. [25]. ¹H NMR spectra analysis was used to determine the Mannuronate/Guluronate (M/G) ratio of the used sodium alginate. Quantitatively, the guluronic and mannuronic mole fractions were associated with the area signal or integration of the respective peaks. The integration obtained is shown in I_A (guluronate peak area of G₁) 5.5–5.7 ppm, I_B (mannuronate peak area of M₁) 5.1–5.4 ppm, I_C (guluronic peak area of G₅) 4.9–5.1 ppm. The mole fraction of each composition of F_M and F_G is used to determine the M/G ratio of alginate with the equation referring to the research of Grasdalen et al. [35]. The signals of proton for alginate at ¹H-NMR spectrum has in range of 1–6 ppm. The anomer protons of each monosaccharide could be recognized from the α-glycosides and β-glycosides of the residues. Based on the ¹H-NMR spectra (Figure 2b), the anomer protons of α-guluronate and β-mannuronate were shown on the G₁ and M₁ proton at δ 5.6 and 5.1 ppm, respectively. Both signals are the most deshielded proton because both protons are

attached to anomeric carbon. The signals of 5–6 ppm belong to anomeric proton of the α -glycosidic or α -guluronate and the signals between in the range of 4.3–5 ppm belong to proton of β -glycosidic or β -mannuronate [36]. The proton of α -glycosidic is more deshielded than β -glycosidic because it is located at equatorial position as compared to axial position. Llanes et al. [25] showed proton signals of sodium alginate from *Sargassum* sp. that G₁, M₁, G₅ proton at δ 5.07, 4.68 and 4.45 ppm. The M/G ratio of the mannuronic and guluronic acid residues can be determined from the integration of the respective peaks of the ¹H-NMR spectra [37]. The M/G ratio and η value of alginate *S. duplicatum* were 0.91 and 0.68, respectively. The chemical structure of mannuronic acid and guluronic acid could be shown in Figure 2c,d.

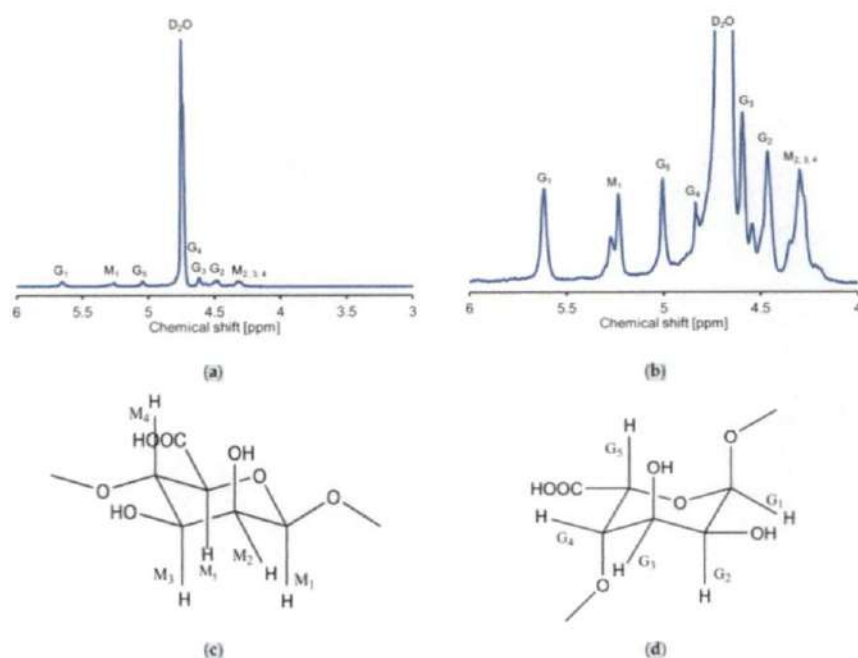


Figure 2. (a) ¹H-NMR spectra of sodium alginate from *S. duplicatum*; (b) details of ¹H-NMR spectra; (c) structure of mannuronic acid; (d) structure of guluronic acid.

3.2. Total Flavonoids Content and Antioxidant Assay

The total content of flavonoids of okra fruit extract was 43.96 mg (QE)/g or 4.40% ($y = 0.0105x - 0.0161$; $R^2 = 0.9989$). The parameter used to study the antioxidant activity is the value of inhibition concentration (IC₅₀) and it is classified in to 5 groups (very strong/highly active, strong/active, moderate, weak, inactive) [38]. In this study, ascorbic acid was selected as reference antioxidant (strong antioxidant). IC₅₀ was determined using DPPH method based on the percentage of DPPH radical scavenging activity. The IC₅₀ value of alginate *S. duplicatum* was 125.31- μ g/mL ($y = 0.2657x + 1.7814$; $R^2 = 0.959$). Okra fruit extract and alginate–okra fruit extracts combinations (AOEs) showed strong antioxidant comparable to ascorbic acid. As reported in Table 1 the IC₅₀ value of the okra fruits and of alginate–okra fruits extracts combination were 65.87- μ g/mL ($y = 0.097x + 43.611$; $R^2 = 0.9567$) and 79.34- μ g/mL ($y = 0.3384x + 13.957$; $R^2 = 0.9681$), respectively.

Table 1. Antioxidant activity of alginate, okra fruit and alginate-okra fruit extracts combinations (AOEs).

Sample of Extracts	IC ₅₀ (µg/mL)	Classification
Sodium alginate <i>S. duplicatum</i>	125.31	Moderate antioxidant
Okra fruit	65.87	Strong antioxidant
Alginate-okra extracts combination	79.34	Strong antioxidant
Ascorbic acid	55.89	Strong antioxidant

3.3. Determination of Weight on Mice

The results showed that the administration of lard for 3 weeks with a dose of 0.3 mL per oral could increase the weight of the body significantly ($\alpha < 0.05$) from 27.26 ± 4.23 g to 33.25 ± 2.97 g. Obesity of mice was characterized by increased weight after the administration of lard. (Data Not Shown)

3.4. Determination of Blood-glucose Levels

Alteration in blood-glucose levels on Day 1 to 14 after STZ induction and topical treatment is shown in Table 1. STZ was able to increase blood-glucose levels > 250 mg/dL on Day 1 which showed all diabetic groups in suffering of diabetes. Alginate administration did not lead to significantly lower blood-glucose levels ($\alpha > 0.05$) from Day 1 (251.50 ± 7.78 mg/dL) until Day 7 (229.50 ± 7.78 mg/dL) but decreased significantly at Day 14 (208.00 ± 8.49 mg/dL) if compared to the first day. In contrast, the topical treatment of alginate-okra could decrease the glucose levels significantly ($\alpha < 0.05$) from Day 1 (256.50 ± 19.09 mg/dL) until Day 14 (115.00 ± 19.06 mg/dL).

3.5. Histological Analysis of Wound Tissue

Histological analysis of the width of the wound was indicated by yellow line an area of re-epithelization on the wound (Figure 3). The re-epithelization area increased on Day 7 for both DA and DAO and wounds closed occurs on Day 14 for each group. The DAO groups showed that complete re-epithelization and faster than other groups and proved by histology on Day 7 and 14.

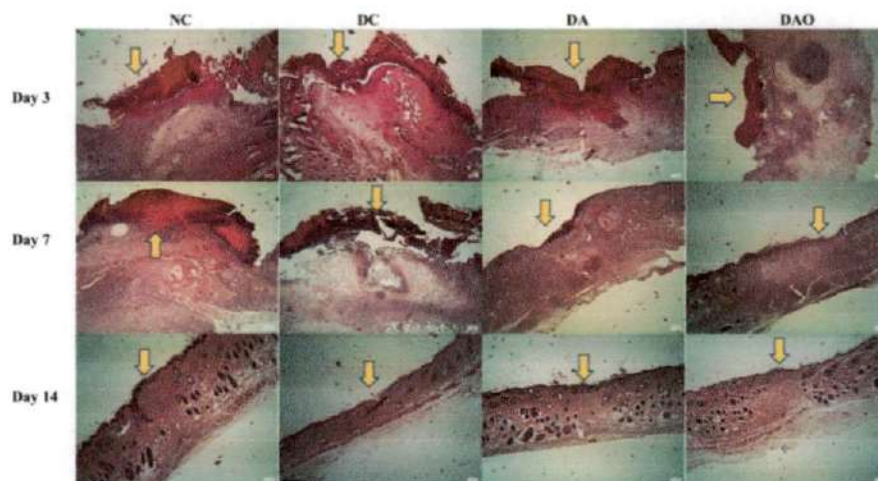


Figure 3. Histology of the wound width indicated by the yellow arrow. NC—normal control group; DC—diabetic control group; DA—alginate treatment group; DAO—treatment of alginate-okra fruit extracts. All groups have three variation times.

Wound parameter such as neutrophils (pale green), macrophages (yellow), fibrocytes (green), fibroblasts (blue) and collagen densities (orange) showed by histology magnification of wound width

(Figure 4). The number of neutrophils reaches the maximum at Day 3 while it decreases from Day 3 to Day 7 and 14 for all studied groups. The number of macrophages reaches the maximum at Day 7 while it decreased at Day 14 for all groups. The DC group was evidenced by the highest concentration of macrophages when compared to other groups. Fibrocyte and fibroblast were found in the Day 7 for re-epithelization and decreased in the Day 14, as they have formed collagen fibers for all groups. The DC group was found a number of fibrocytes, fibroblasts and the least formation of collagen fibers in the group.

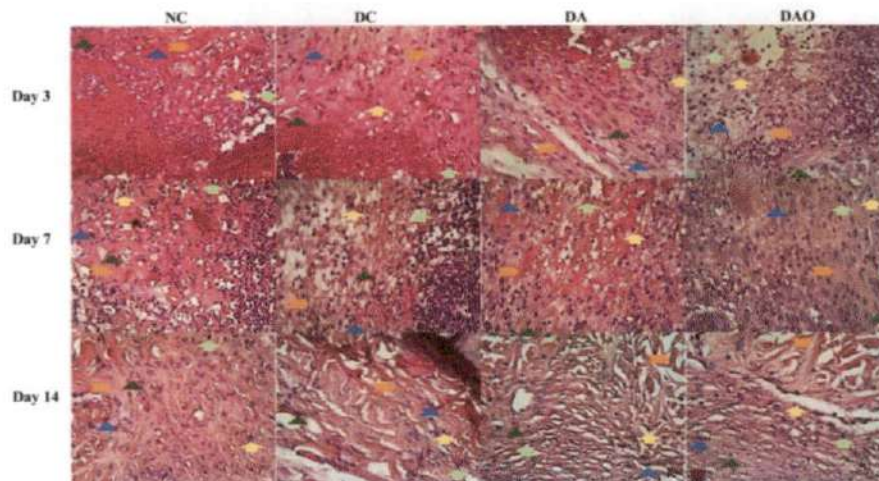


Figure 4. Histology of wound parameter including neutrophils—◆; Macrophages—●; Fibrocytes—▲; Fibroblasts—▲; Collagen density—➤; NC—normal control group; DC—diabetic control group; DA—alginate treatment group; DAO—treatment of alginate-okra fruit extracts. All groups have three variation times.

3.6. Analysis of Wound Parameter

3.6.1. Wound-Width Measurement

The difference in the wound width parameter of each group for time variation is shown in Figure 5. The wound width of diabetic DC group was significantly decreased from Days 3 to 14. DC group showed significant difference to normal NC group and diabetic groups as DA, DAO treated with alginate and okra fruit extracts ointment ($\alpha < 0.05$). Treatment group of DA and DAO were significantly decrease on Days 3 to 14 and they showed significant difference on Days 3 to 7. It showed that okra fruit extracts combination plays an important role in wound closure. No significant differences between DAO group and normal group (NC) on Days 3, 7 and 14 ($\alpha > 0.05$) was observed. This indicates that the topical administration of alginate and okra fruit extracts combination can increase re-epithelization of the wound area in comparison to the control group. Diabetic group (DC) showed that till has wound width on Day 14. Otherwise, NC, DA and DAO groups showed no wound width on Day 14 and it indicated a complete wound closure.

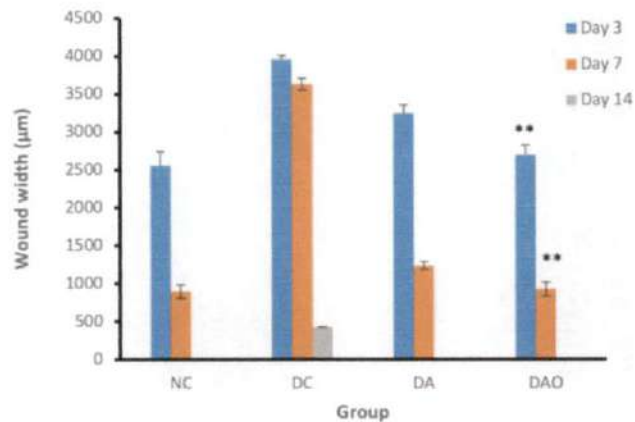


Figure 5. Graph of the wound width parameters. Notation on the graph shows the result of the statistical test ($\alpha < 0.05$). (**) notation shows insignificant differences with NC, but significant differences with DC. ** = $\alpha \leq 0.01$. NC—normal control group; DC—diabetic control group; DA—alginate treatment group; DAO—treatment of alginate–okra fruit extracts. All groups have three variation times.

3.6.2. Neutrophil Measurement

The differences in the number of neutrophils of each group in variations of time were represented in Figure 6. There were significant differences in the number of neutrophils parameters between treatment groups and DC group ($\alpha < 0.05$), but no significant differences between the treatment group and the NC group ($\alpha > 0.05$) were observed. The number of neutrophils increased on Day 3 and decreased on Day 7 and 14 for all groups.

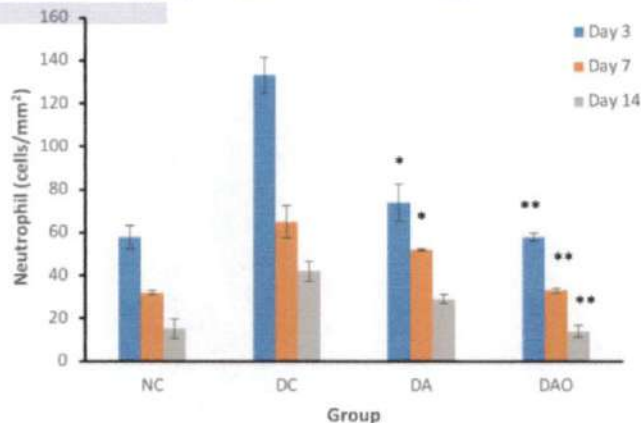


Figure 6. Graph of the number of neutrophils. Notation on the graph shows the result of the statistical test ($\alpha < 0.05$). (*) and (**) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha < 0.05$; ** = $\alpha \leq 0.01$. NC—normal control group; DC—diabetic control group; DA—alginate treatment group; DAO—treatment of alginate–okra fruit extracts. All groups have three variation times.

3.6.3. Macrophage Measurement

The difference in the number of macrophages each group in time variations were represented in Figure 7. Similar to the neutrophil parameter, the number of macrophages of DAO group was significant difference to the DC ($\alpha < 0.05$), but no significant difference with NC group ($\alpha > 0.05$). The increase of macrophages occurred up to Day 7 and decreased on Day 14 for all groups.

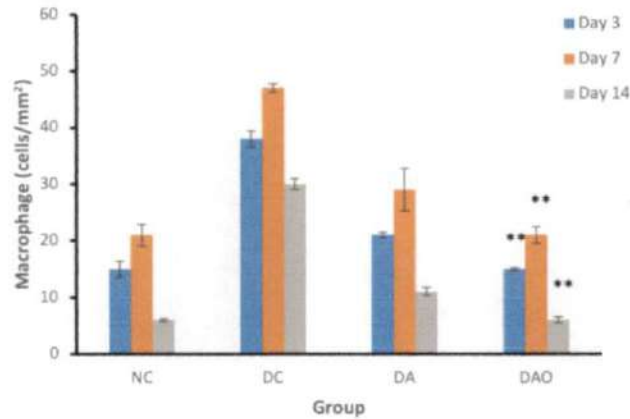


Figure 7. Graph of the number of macrophages. Notation on the graph shows the result of the statistical test ($\alpha < 0.05$). (**) notation shows insignificant differences with NC, but significant differences with DC. ** = $\alpha \leq 0.01$. NC—normal control group; DC—diabetic control group; DA—alginate treatment group; DAO—treatment of alginate–okra fruit extracts. All groups have three variation times.

3.6.4. Fibrocyte and Fibroblast Measurements

The difference in the number of fibrocytes and fibroblasts of each group in time variations are shown in Figure 8a,b. There were significant differences between DAO treatment with DC groups ($\alpha < 0.05$), but no significant difference with NC group ($\alpha > 0.05$). The number of fibrocytes and fibroblasts increased on Day 7 and decreased on Day 14 for all groups.

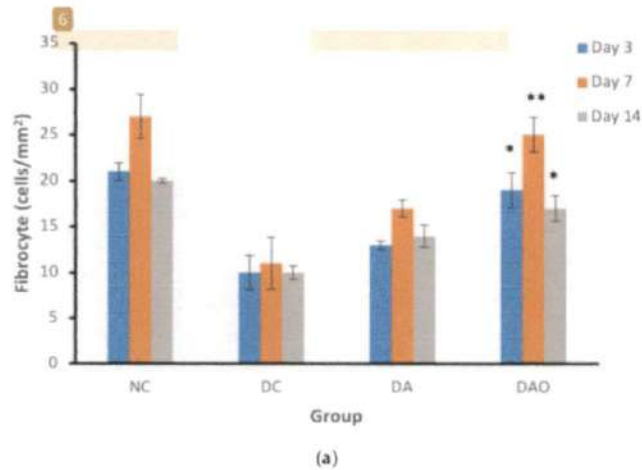


Figure 8. Cont.

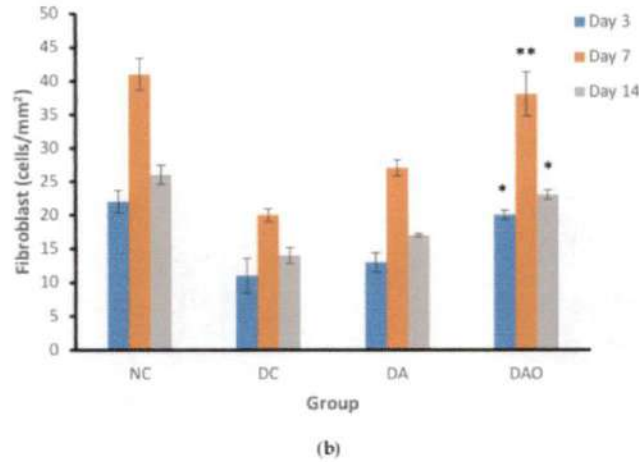


Figure 8. (a) Graph of the number of fibrocytes; (b) graph of the number of fibroblasts. Notation on the graph showed the result of the statistical test ($\alpha < 0.05$). (*) and (**) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha < 0.05$; ** = $\alpha \leq 0.01$. NC—normal control group; DC—diabetic control group; DA—alginate treatment group; DAO—treatment of alginate-okra fruit extracts. All groups have three variation times.

3.6.5. Collagen Densities Measurement

The different collagen densities of each group in time variations are shown in Figure 9. There were significant differences between treatment groups with DC ($\alpha < 0.05$), but no significant difference with NC group ($\alpha > 0.05$) was observed.

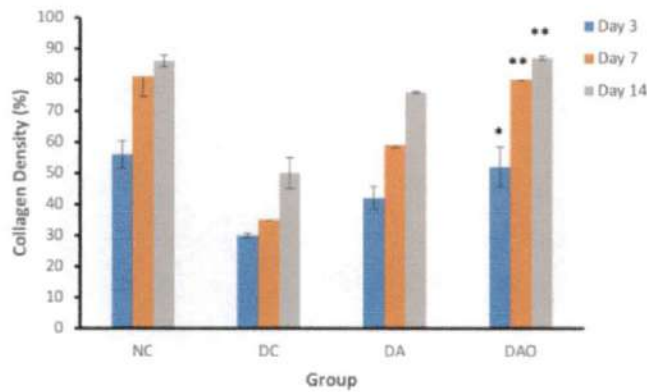


Figure 9. Graph of the collagen densities. Notation on the graph shows the result of the statistical test ($\alpha < 0.05$). (*) and (**) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha < 0.05$; ** = $\alpha \leq 0.01$. NC—normal control group; DC—diabetic control group; DA—alginate treatment group; DAO—treatment of alginate-okra fruit extracts. All groups have three variation times.

4. Discussion

The extraction yield of alginate from *S. duplicatum* was higher in comparison with the other seaweed such as *Cystoseira barbata*, *Dictyota caribaea* and *Padina perindusiata* of 9.9, 7.4 and 5.4%, respectively [39,40].

However, the extraction yield was lower than alginate from *C. implexa* and *L. variegata* of 29.15 and 27.57% [41], *S. angustifolium* and *Sargassum* sp. of 40.78 and 44.32%, respectively [42,43]. In general, the content of alginate in various types of brown seaweed varies widely depending on species and the method for extraction used [44]. The extraction yield and the color of alginate from *S. duplicatum* in this study like to the previous published literature which have pale yellow color and 12% yield [40].

Based on result of characterization of alginate *S. duplicatum*, polymer of alginate *S. duplicatum* is homogeneous because it has polydispersity index is less than two [45]. M_w and M_n of alginate of *S. duplicatum* were lower in comparison to M_w and M_n of *S. turbinarioides* (5.528×10^5 and 3.852×10^5 g/mol) and *S. vulgare* (1.10×10^5 and 1.94×10^5 g/mol) [46,47]. Alginate of *S. duplicatum* has residue of guluronate higher than mannuronate (M/G ratio = 0.91) and also it has η value as 0.68 (less than 1). Hence, it indicated that alginate extracted from *S. duplicatum* is a homopolymer block containing polyguluronate type structure [47]. The M/G ratio of alginate *S. duplicatum* is higher than *S. fluitans* (0.15–0.69), but lower than *S. siliculosum* (0.70–0.94) [48]. Some other *Sargassum* species have M/G ratio about 0.8–1.4 [25].

Quantitatively, okra fruit extracts has a total flavonoid and quercetin content higher from green okra extract of 27.0 mg/100 g and 20.03 mg (QE)/100 g [49,50]. The green okra fruits contain of flavonoid such as a quercetin derivative. The primary flavonoids of okra fruits are up to 81.0% of the total antioxidant compounds [51]. Total phenolic or total flavonoids in okra extracts play an important role in the ability of antioxidant activity in varying percentages [14]. Antioxidant activity could be classified based on the IC_{50} values, if the values less than 50 $\mu\text{g/mL}$ is very strong/highly active, 51–100 $\mu\text{g/mL}$ is strong/active, 101–250 $\mu\text{g/mL}$ is moderate, 251–500 $\mu\text{g/mL}$ is weak and more than 500 $\mu\text{g/mL}$ is inactive antioxidants [38]. Okra and AOE have strong inhibition 65.87 and 79.34, respectively in comparison with alginate of 125.31 at the same concentration. Sodium alginate from *Cystoseira barbata* inhibited of 174 radical scavenging activity of DPPH [12]. It showed that the antioxidant activity of alginates from different species has quite different activities, because antioxidant activity of plant extracts is associated with flavonoid or phenolic compounds in the extract and it depends on the arrangement of structural functional groups of the extracts. In addition, the existence of hydroxyl group, monosaccharide composition, molecular hydrogen bonds, and molecular weight affects the activity of antioxidants [52]. Some structural features of polysaccharides such as molecular weight, monosaccharide composition (block G and M), availability of hydroxyl groups, and molecular hydrogen bonds have an effect on scavenging activity. Alginate that contain block G higher than block M have an increase in antioxidant activity due to diaxial linkage in block G. It causes the obstructed rotation around the glycosidic linkage, so that it can reduce the flexibility of block G. it affects the availability of the hydroxyl group and increased proton donor capability for the free radical scavenger process in alginate molecule [47]. The addition of okra fruit extract combination on antioxidant activity showed the flavonoid content in okra fruit extract plays an important role in free radical scavenging. The reduction activity of phenolic hydroxyl groups causes flavonoids to contribute hydrogen atoms so that delocalization of phenoxy radical products occurs to protect tissue damage from ROS [53]. In this research, the addition of alginate to the extract combination reduced the IC_{50} value compared to okra fruit extracts. However, alginate can stabilize flavonoids in okra fruit extracts because G and M block residues tend to form diaxial links with intramolecular or extramolecular hydrogen bonds in more stable flavonoid compounds [54].

The administration of lard increase hyperlipidemia and insulin resistance that leads to Type 2 diabetes mellitus which was marked by obesity [30]. Onset of obesity due to the accumulation of excess fat can lead to chronic diseases and complications such as diabetes mellitus and cardiovascular disease [55]. STZ administration is expected to increase the condition of hyperglycemia (increase blood-glucose levels) and created diabetic-like syndrom [29]. The destruction of the pancreatic cells were carried out by free radical of STZ which was toxic to the insulin sensitive tissues, so that the secretion of insulin hormone was decrease [56]. Topical treatment using ointment was expected to lowering blood-glucose levels that lead to the wound healing on diabetic mice. Removal of the stratum

corneum layer in the skin layer during wound formation increase skin permeability thereby allowing the release of active compounds from topical formulations in the skin layer to enter the systemic circulation. In addition, active compounds pass penetration through the transappendageal route (sweat glands, hair follicles and sebaceous glands which include open channels on the outside surface of the skin) [57,58]. Tan et al. [59] revealed that the topical application of Vice-2 film which is a type of flavonoid-derived glycosides from various natural plants can reduce blood-glucose levels in diabetic mice. Hence, that, lowering blood-glucose levels on diabetic mice can be influenced by topical treatment of open wounds. The combination of extracts could reduce the condition of diabetes which is demonstrated in Table 2. The value observed of DAO group at day 14 was almost the same of the control group (115.0 ± 19.1). it is indicating the potentiality of okra fruit extract in reducing blood-glucose level on diabetic mice. Antioxidant properties can neutralize free radical damage so that blood-glucose levels decreases. Okra fruit extract can control blood-glucose levels, as an effective treatment for diabetic ulcers [60].

Table 2. Total blood glucose of mice on Days 1, 3, 7 and 14 after treatment.

Group Treatment	Blood-glucose Level (mg/dL)			
	Day 1	Day 3	Day 7	Day 14
Normal (NC)	111 ± 9.9	110.5 ± 7.8	107.5 ± 5.0	120.0 ± 14.1
Diabetic (DC)	269.5 ± 16.3	252.5 ± 19.1	287.5 ± 14.9	220.0 ± 24.0
Alginate ointment (DA)	251.5 ± 7.8	239.5 ± 27.6	229.5 ± 7.8	208.0 ± 8.5
Alginate-okra ointment (DAO)	256.5 ± 19.1	169.5 ± 24.8	182.5 ± 13.4	115.0 ± 19.1 *

Letter notation on the table shows the result of the statistical test ($\alpha < 0.05$). (*) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha \leq 0.05$. n = 3 animals per time point.

No significant differences between DAO group (2693.0 ± 12.2; 917.0 ± 91.3; 0 ± 0 µm) and normal group (NC) (2548.0 ± 187.2; 894.0 ± 87.6; 0 ± 0 µm) on Days 3, 7 and 14 (Table 3). This indicates that the topical administration of alginate and okra fruit extracts combination can increase re-epithelization of the wound area in comparison to the control group. Diabetic group (DC) showed that still has wound width on Day 14 (424.0 ± 5.2 µm). Otherwise, NC, DA and DAO groups showed no wound width on Day 14 (0 ± 0 µm) and it indicated a complete wound closure.

Table 3. Counts considering the mean and standard deviation of wound width.

Group Treatment	Wound Width (µm)		
	Day 3	Day 7	Day 14
Normal (NC)	2548.0 ± 187.2	894.0 ± 87.6	0 ± 0
Diabetic (DC)	3956.0 ± 52.2	3631.0 ± 74.8	424.0 ± 5.2
Alginate ointment (DA)	3240.0 ± 117.5	1229.0 ± 49.9	0 ± 0
Alginate-okra ointment (DAO)	2693.0 ± 12.2 **	917.0 ± 91.3 **	0 ± 0

Letter notation on the table shows the result of the statistical test ($\alpha < 0.05$). (**) notation shows insignificant differences with NC, but significant differences with DC. ** = $\alpha \leq 0.01$.

The number of neutrophils increased on Day 3 and decreased up to Day 14 for all groups, due to migration of neutrophil achieved a maximum between Day 1 and 2. The plateaued level on Day 3 and decreases on Day 5 [61]. Neutrophil secretions in diabetic conditions tend to be high compared to the normal conditions due to high ROS/RNS levels, resulting in increased inflammation and tissue damage [62]. This is evidence by the higher number of neutrophils on Day 3 up to Day 14 in the diabetic control group (133.0 ± 8.2; 65.0 ± 7.5; 42.0 ± 4.7 cells/mm²) compared to normal control group (58.0 ± 5.4; 32.0 ± 0.9; 15.0 ± 4.5 cells/mm²) (Table 4).

Table 4. Counts considering the mean and standard deviation of neutrophils.

Group Treatment	Neutrophils (cells/mm ²)		
	Day 3	Day 7	Day 14
Normal (NC)	58.0 ± 5.4	32.0 ± 0.9	15.0 ± 4.5
Diabetic (DC)	133.0 ± 8.2	65.0 ± 7.5	42.0 ± 4.7
Alginate ointment (DA)	74.0 ± 8.5 *	52.0 ± 0.5 *	29.0 ± 2.1
Alginate–okra ointment (DAO)	58.0 ± 1.9 **	33.0 ± 1.2 **	14.0 ± 2.6 **

Letter notation on the table shows the result of the statistical test ($\alpha < 0.05$). (*) and (**) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha < 0.05$; ** = $\alpha \leq 0.01$.

Number of macrophages increase up to Day 7 and decreased on Day 14 for all groups, because on the Day 7 the wound condition undergoes inflammatory and proliferation processes. For example in the DAO group on Day 3 up to Day 7 number of macrophages increased (15.0 ± 0.2 ; 21.0 ± 1.4 cells/mm²) and decreased on Day 14 (6.0 ± 0.5 cells/mm²) (Table 5). Neutrophils were secreting cytokines and granule proteins, which modulating monocyte or macrophage extravasation, phagocytosis and ROS production. In diabetics, the condition of hyperglycemia increases the activity of macrophages, thereby increasing the levels of ROS/RNS which causes a prolonged inflammatory phase [63]. In addition, hyperglycemia and oxidative stress conditions can lead to polarization and modulating macrophage dysregulation, because change epigenetic code which is inhibit the wound-healing process [64]. This is evidence by the higher number of macrophages on Day 3 up to Day 14 in the diabetic control group (38.0 ± 1.4 ; 47.0 ± 0.7 ; 30.0 ± 0.9 cells/mm²) compared to normal control group (15.0 ± 1.4 ; 21.0 ± 1.9 ; 6.0 ± 0.2 cells/mm²).

Table 5. Counts considering the mean and standard deviation of macrophages.

Group Treatment	Macrophages (cells/mm ²)		
	Day 3	Day 7	Day 14
Normal (NC)	15.0 ± 1.4	21.0 ± 1.9	6.0 ± 0.2
Diabetic (DC)	38.0 ± 1.4	47.0 ± 0.7	30.0 ± 0.9
Alginate ointment (DA)	21.0 ± 0.5	29.0 ± 3.8	11.0 ± 0.7
Alginate–okra ointment (DAO)	15.0 ± 0.2 **	21.0 ± 1.4 **	6.0 ± 0.5 **

Letter notation on the table shows the result of the statistical test ($\alpha < 0.05$). (**) notation shows insignificant differences with NC, but significant differences with DC. ** = $\alpha \leq 0.01$.

The number of fibrocytes and fibroblasts increased on Day 7 and decreased on Day 14 for all groups, because the wound conditions have peak proliferation phases for re-epithelization and angiogenesis processes [65]. For example in the DAO group on Day 3 up to Day 7 number of fibrocyte increased (19.0 ± 1.9 ; 25.0 ± 1.9 cells/mm²) and decreased on Day 14 (17.0 ± 1.4 cells/mm²) (Table 6). The same thing happened to the number of fibroblasts in the DAO group on Day 3 up to Day 7 increased (20.0 ± 0.7 ; 38.0 ± 3.3 cells/mm²) and decreased on Day 14 (23.0 ± 0.7 cells/mm²) (Table 7). Macrophages perform cytokine and growth factor secretions in the wound area to induce fibroblast migration and proliferation, production of granulation tissues, transient extracellular matrix and angiogenesis in the healing process. Conditions of high blood-glucose levels lead to migration and fibrocyte proliferation disorders, fibroblasts and keratinocytes, resulting in decreased secretion of cytokine, growth factor and extracellular matrix [63]. This is evidence by the lower number of fibrocytes on Day 3 up to Day 14 in the diabetic control group (10.0 ± 1.9 ; 11.0 ± 2.8 ; 10.0 ± 0.7 cells/mm²) compared to normal control group (21.0 ± 0.9 ; 27.0 ± 2.3 ; 20.0 ± 0.2 cells/mm²). The same thing happened to the number of fibroblasts on Day 3 up to Day 14 in the diabetic control group (11.0 ± 2.6 ; 20.0 ± 0.9 ; 14.0 ± 1.2 cells/mm²) compared to normal control group (22.0 ± 1.6 ; 41.0 ± 2.4 ; 26.0 ± 1.4 cells/mm²).

Table 6. Counts considering the mean and standard deviation of fibrocytes.

Group Treatment	Fibrocytes (cells/mm ²)		
	Day 3	Day 7	Day 14
Normal (NC)	21.0 ± 0.9	27.0 ± 2.3	20.0 ± 0.2
Diabetic (DC)	10.0 ± 1.9	11.0 ± 2.8	10.0 ± 0.7
Alginate ointment (DA)	13.0 ± 0.5	17.0 ± 0.9	14.0 ± 1.2
Alginate-okra ointment (DAO)	19.0 ± 1.9 *	25.0 ± 1.9 **	17.0 ± 1.4 *

Letter notation on the table shows the result of the statistical test ($\alpha < 0.05$). (*) and (**) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha < 0.05$; ** = $\alpha \leq 0.01$.

Table 7. Counts considering the mean and standard deviation of fibroblasts.

Group Treatment	Fibroblasts (cells/mm ²)		
	Day 3	Day 7	Day 14
Normal (NC)	22.0 ± 1.6	41.0 ± 2.4	26.0 ± 1.4
Diabetic (DC)	11.0 ± 2.6	20.0 ± 0.9	14.0 ± 1.2
Alginate ointment (DA)	13.0 ± 1.4	27.0 ± 1.2	17.0 ± 0.2
Alginate-okra ointment (DAO)	20.0 ± 0.7 *	38.0 ± 3.3 **	23.0 ± 0.7 *

Letter notation on the table shows the result of the statistical test ($\alpha < 0.05$). (*) and (**) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha < 0.05$; ** = $\alpha \leq 0.01$.

Fibroblast proliferation induces collagen synthesis and macromolecular matrix for structural formation of connective tissues. Diabetes conditions increase the activity of macrophages thereby increasing the production of ROS/RNS and lowering collagen synthesis [66]. This is evidence by the lower collagen densities on Day 3 up to Day 14 in the diabetic control group (30.0 ± 0.6 ; 35.0 ± 0.1 ; $50.0 \pm 4.9\%$) compared to normal control group (56.0 ± 4.3 ; 81.0 ± 6.4 ; $86.0 \pm 1.9\%$) (Table 8).

Table 8. Counts considering the mean and standard deviation of collagen densities.

Group Treatment	Collagen Densities (%)		
	Day 3	Day 7	Day 14
Normal (NC)	56.0 ± 4.3	81.0 ± 6.4	86.0 ± 1.9
Diabetic (DC)	30.0 ± 0.6	35.0 ± 0.1	50.0 ± 4.9
Alginate ointment (DA)	42.0 ± 3.8	59.0 ± 0.8	76.0 ± 0.3
Alginate-okra ointment (DAO)	52.0 ± 6.4 *	80.0 ± 0.3 **	87.0 ± 0.6 **

Letter notation on the table shows the result of the statistical test ($\alpha < 0.05$). (*) and (**) notation shows insignificant differences with NC, but significant differences with DC. * = $0.01 \leq \alpha < 0.05$; ** = $\alpha \leq 0.01$.

The topical administration of alginate can reduce the wounds with and increase cytokines and growth factor. This is because alginate has a hydroxyl group that plays a role in the properties of hydrophilicity, so that alginate can absorb moderate or heavy exudate liquid to reach 15 to 20 times in dry or gel form, so it is called a hemostatic agent [67]. Absorption of exudate on the wound area was occur due to the exchange of ions between exudate and alginate that keeps the moist condition of the wound physiologically and minimizing bacterial infections. In addition, it allows enough oxygen exchange to accelerate the formation of tissue granulation and re-epithelization [68]. The proportion of M/G residue affects alginate's ability as absorber. Higher M content is not firmly tied to molecules so it will increase the process of ion exchange between alginate and exudate wounds [69]. Based on literature, the wound healing activity of alginate topically on diabetic open wounds form complete epithelization on Day 14 [70].

The topical administration of okra fruit extract can reduce blood-glucose levels and improve wound-healing process, because it has strong antioxidant properties due to the role of the 3-hydroxyl group on the C ring of the flavonoids compounds to capture free radicals due to glucose oxidation

(hyperglycemia). Decreasing ROS/RNS can reduce hyperglycemia and increase glucose metabolism, thereby lowering oxidative stress and insulin resistance which increase wound healing [71]. The ointment formula contains flavonoids could be released into wounds and then to the bloodstream so as to induce secretion of cytokine, growth factor and increase insulin production or insulin sensitivity of somatic cells. Flavonoids also cause re-formation of antioxidants and serum lipid profiles in diabetic rats [59]. The wound healing activity of the okra fruit extract topically on open wounds effectively forms the complete epithelization on 15 day [72] and achieves a complete epithelization on 16 day [73].

5. Conclusions

Extraction and characterization of alginate from *S. duplicatum* and okra fruit extracts were carried out to determine the potentiality of them as an absorber of the wound and their antioxidant activity. The novelty of this research lies in the healing activity of open wounds from a combination of alginate and okra fruit extracts. Topical formulations are more effective when alginates are combined with okra fruit extracts because of the alginate can stabilize flavonoids, so it increased wound absorber and their antioxidant properties. The results show an improvement of the re-epithelization of the wound area, the recruitment of neutrophil, macrophages, fibrocytes, fibroblasts and increased collagen densities as parameters that plays an important role in the wound-healing process.

Further research and a more detailed analysis of the characterization of alginate structures to determine the role of alginate as an antioxidant agent in the combination of topical formulations for open wounds healing are needed. Moreover, variations of doses need to be done for further research to determine the optimum dose of the extract combination in open wound healing of diabetic mice. Hence, it would help to provide more insight of the mechanism of action this combination extracts on the process of diabetic wound healing.

Author Contributions: This paper is a part of master's degree thesis. Conceptualization, P.P. and D.W.; methodology, Z.N.I. and S.A.H.; software, Z.N.I.; validation, D.W., A.P., S.A.H.; formal analysis, Z.N.I., A.P. and M.V.; investigation, Z.N.I.; resources, Z.N.I., P.A.C.W. and M.A.A.; data curation, Z.N.I.; writing—original draft preparation, Z.N.I.; writing—review and editing, P.P., K.A. and D.M.; visualization, Z.N.I.; supervision, P.P. and D.W.; project administration, Z.N.I., P.A.C.W., S.A.H.; funding acquisition, P.P. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by Innovation and Research Center, Airlangga University, Grant Number 19/S/UN3/2019 and The APC was funded by Innovation and Research Center, Airlangga University. A.P. thanks the Austrian Science Fund (FWF) for the funding through the Erwin Schrödinger Fellowship, grant agreement: J4014-N34.

Acknowledgments: The author would like to thank Innovation and Research Center, Airlangga University for supporting this research through Mandat Research Grant, Airlangga University FY 2019 and Leonardo Gomez from the CNAP of the University of York for access to the SEC-MALLS system.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Das, S.; Majid, M.; Baker, A.B. Syndecan-4 Enhances Pdgf-Bb activity in diabetic wound healing. *Acta Biomater.* **2016**, *15*, 56–65. [CrossRef]
2. Houstis, N.; Rosen, E.D.; Lander, E.S. Reactive oxygen species have a causal role in multiple forms of insulin resistance. *Nature* **2006**, *440*, 944–948. [CrossRef] [PubMed]
3. Gary, S.R.; Woo, K.Y. The biology of chronic foot ulcers in persons with diabetes. *Diabetes/Metab. Res. Rev.* **2008**, *24*, 25–30. [CrossRef]
4. American Diabetes Association. Classification and diagnosis of diabetes mellitus. *Diabetes Care* **2015**, *38*, 8–16. [CrossRef]
5. Gilgun-Sherki, Y.; Melamed, E.; Offen, D. Oxidative stress induced-neurodegenerative diseases: The need for antioxidants that penetrate the blood brain barrier. *Neuropharmacology* **2001**, *40*, 959–975. [CrossRef]
6. Prompers, L.; Schaper, N.; Apelqvist, J.; Edmonds, M.; Jude, E.; Mauricio, D. Prediction of outcome in individuals with diabetic foot ulcers: Focus on the differences between individuals with and without peripheral arterial disease. *Eurodiab Study Diabetol.* **2008**, *51*, 747–755. [CrossRef]

7. Babitha, S.; Rachita, L.; Karthikeyan, K.; Shoba, E.; Janani, I.; Poornima, B. Electrospun protein nanofibers in healthcare: A review. *Int. J. Pharm.* **2017**, *523*, 52–90. [[CrossRef](#)]
8. Ode, I. The content of Alginate seaweed of *Sargassum crassifolium* from the coastal waters of Hutumuri village Ambon City. *J. Sci. Agribus. Fish.* **2014**, *6*, 3.
9. Sezer, A.D.; Cevher, E. Biopolymers as wound healing materials: Challenges and new strategies. In *Biomaterials Applications for Nanomedicine*; Pignatello, R., Ed.; InTech: Rijeka, Croatia, 2011; pp. 383–414.
10. Yu, W.; Jiang, Y.Y.; Sun, T.W.; Qi, C.; Zhao, H.; Chen, F.; Shi, Z.; Zhu, Y.J.; Chen, D.; He, Y. Design of a novel wound dressing consisting of alginate hydrogel and simvastatin-incorporated mesoporous hydroxyapatite microspheres for cutaneous wound healing. *R. Soc. Chem.* **2016**, *6*, 104375–104387. [[CrossRef](#)]
11. Nazeri, S.; Ardakani, E.M.; Babavalian, H.; Latifi, A.M. Evaluation of Effectiveness of Honey-Based Alginate Hydrogel on Wound Healing in a Mouse Model of Rat. *J. Appl. Biotechnol. Rep.* **2015**, *2*, 293–297.
12. Ahmed, M.M.; Jahangir, M.A.; Saleem, M.A.; Kazmi, I.; Bhavani, P.D.; Muheem, A. Formulation and Evaluation of Fucidin Topical Gel Containing Wound Healing Modifiers. *Am. J. Pharmtech Res.* **2015**, *5*, 232–242.
13. Hegge, A.B.; Andersen, T.; Melvik, J.E.; Bruzell, E.; Kristensen, S.; Tonnesen, H.H. Formulation and bacterial phototoxicity of curcumin loaded alginate foams for wound treatment applications: Studies on curcumin and curcuminoids XLII. *J. Pharm. Sci.* **2011**, *100*, 174–185. [[CrossRef](#)]
14. Suzuki, Y.; Nishimura, Y.; Tanihara, M.; Suzuki, K.; Kitahara, A.K.; Yamawaki, Y.; Nakamura, T.; Shimizu, Y.; Kakimaru, Y. Development of alginate gel dressing. *J. Artif. Organs.* **1998**, *1*, 28–32. [[CrossRef](#)]
15. Dyson, M.; Young, S.R.; Pendte, L.; Webster, D.F.; Lang, S. Comparison of the effects of moist and dry conditions on dermal repair. *J. Investig. Dermatol.* **1988**, *91*, 434–439. [[CrossRef](#)]
16. Sellimi, S.; Younes, I.; Ayed, H.B.; Maalej, H.; Montero, V.; Rinaudo, M.; Dahia, M.; Mechichi, T.; Hajji, M.; Nasri, M. Structural, physicochemical and antioxidant properties of sodium alginate isolated from a Tunisian brown seaweed. *Int. J. Biol. Macromol.* **2015**, *72*, 1358–1367. [[CrossRef](#)]
17. Szekealska, M.; Pucilowska, A.; Szymańska, E.; Ciosek, P.; Wirmicka, K. Alginate: Current Use and Future Perspectives in Pharmaceutical and biomedical applications. *Int. J. Polym. Sci.* **2016**, *8*, 1–17. [[CrossRef](#)]
18. Liao, H.; Liu, H.; Yuan, K. A New Flavonol glycoside from the *Abelmoschus esculentus* Linn. *Pharmacogn. Mag.* **2012**, *8*, 12–15. [[CrossRef](#)]
19. Sengkhamparn, N.; Verhoef, R.; Schols, H.; Sajjanantakul, T.; Voragen, A.G. Characterisation of cell wall polysaccharides from okra (*Abelmoschus esculentus* (L.) Moench). *Carbohydr. Res.* **2009**, *344*, 1824–1832. [[CrossRef](#)]
20. Sabitha, V.; Ramachandran, S.; Naveen, K.R.; Panneerselvam, K. Antidiabetic and antihyperlipidemic activity of *Abelmoschus esculentus* (L.) Moench. in streptozotocin-induced diabetic rats. *J. Pharm. Bioall. Sci.* **2011**, *3*, 397–402. [[CrossRef](#)]
21. Gouma, E.; Simos, Y.; Verginadis, I.; Batistatou, S.; Karkabounas, S.; Evangelou, A.; Ragos, V.; Peschos, D. Healing effects of Quercetin on full thickness epidermal thermal injury in Wistar rats. *Int. J. Phytomedicine* **2016**, *8*, 277–281.
22. Rasyid, A. Algae coklat (*Phaeophyta*) as source of alginate: Oceanography LIPI. *Oseana* **2003**, *28*, 33–38.
23. Vastano, M.; Pellis, A.; Botelho-Machado, C.; Simister, S.; McQueen-Mason, S.J.; Farmer, T.J.; Gomez, L.D. Sustainable Galactarate-Based Polymers: Multi-Enzymatic Production of Pectin-Derived Polyesters. *Macromol. Rapid Commun.* **2019**, *40*, 1900361. [[CrossRef](#)] [[PubMed](#)]
24. Rinaudo, M. Main properties and current applications of some polysaccharides as biomaterials. *Polym. Int.* **2008**, *3*, 397–430. [[CrossRef](#)]
25. Llanes, F.; Sauriol, F.; Morin, F.G.; Perlin, A.S. An examination of sodium alginate from *Sargassum* by NMR spectroscopy. *Can. J. Chem.* **1997**, *75*, 585–590. [[CrossRef](#)]
26. Devi, N.; Kakati, D.K. Smart porous microparticles based on gelatin/sodium alginate polyelectrolyte complex. *J. Food Eng.* **2006**, *117*, 193–204. [[CrossRef](#)]
27. Ahiakpa, J.K.; Amoatey, H.M.; Amenorpe, G.; Apatey, J.; Ayeh, E.A.; Quartey, E.K.; Agbemavor, W.S. Mucilage content of 21 accessions of okra (*Abelmoschus* spp L.). *Sci. Agric.* **2014**, *2*, 96–101.
28. Prieto, J.M. Procedure: Preparation of DPPH Radical and Antioxidant Scavenging Assay. Dr. Prieto's DPPH Microplate Protocol; School of Pharmacy and Biomolecular Science, Liverpool John Moores University: Liverpool, UK, 2012; pp. 1–3.

29. Raisi-Nafchi, M.; Kavooosi, G.; Nasiri, S.M. Physico-mechanical and antioxidant properties of carboxymethylcellulose and alginate dispersions and essential oil based films for use as food packaging materials. *Acad. J. Food Res.* **2016**, *4*, 001–010. [CrossRef]
30. Novelli, M.; Bonamasa, B.; Masini, M.; Funel, N.; Canistro, D.; Martano, M.; Soleti, A. Persistent correction of hyperglycemia in streptozotocin-nicotinamide-induced diabetic mice by a non-conventional radical scavenger. *Naunyn-Schmied. Arch. Pharmacol.* **2010**, *382*, 127–137. [CrossRef] [PubMed]
31. Federer, W.T. *Experimental Design Theory and Application*; Oxford & IBH: Calcutta, India, 1967.
32. Rinaudo, M. Seaweed polysaccharaides. In *Comprehensive Glycoscience: From Chemistry to System Biology*; Kalmering, J.P., Ed.; Elsevier Science: Amsterdam, The Netherlands, 2007; Volume 2, pp. 691–735.
33. Soares, S.; Cammino, G.; Levchick, S. Comparative study of the thermal decomposition of pure cellulose and pulp paper. *Polym. Degrad. Stab.* **1995**, *49*, 275–283. [CrossRef]
34. Patel, N.; Lalwari, D.; Gollmer, S.; Injeti, E.; Sari, Y.; Nesamony, J. Development and evaluation of a calcium alginate based oral ceftriaxone sodium formulation. *Prog. Biomater.* **2016**, *5*, 117–133. [CrossRef]
35. Grasdalen, H.; Larsen, B.; Smidsrod, O. A P.M.R. study of the composition and sequence of urinate residues in alginates. *Carbohydr. Res.* **1979**, *68*, 23–31. [CrossRef]
36. Cui, S.W. *Food Carbohydrates: Chemistry, Physical Properties, and Application*, 1st ed.; CRC Press: Boca Raton, FL, USA, 2005.
37. Jensen, H.M.; Larsen, F.H.; Engelsen, S.B. Characterization of alginates by Nuclear Magnetic Resonance (NMR) and vibrational spectroscopy (IR, NIR, Raman) in combination with chemometrics. *Nat. Prod. Mar. Algae* **2015**, *1308*, 347–363.
38. Jun, M.; Fu, H.Y.; Hong, J.; Wan, X.; Yang, C.S. Comparison of antioxidant activities of isoflavones from kadzu root (*Puerari lobata ohwi*). *J. Food Sci.* **2003**, *68*, 2117–2122. [CrossRef]
39. Sellimi, S.; Maaleja, H.; Rekik, D.M.; Benslimia, A.; Ksouda, G.; Hamdi, M.; Sahnoun, Z.; Li, S.; Nasri, M.; Hajji, M. Antioxidant, antibacterial and in vivo wound healing properties of laminaran purified from *Cystoseira barbata* seaweed. *Int. J. Biol. Macromol.* **2018**, *119*, 633–644. [CrossRef]
40. Nishinari, K.; Doi, E. *Food Hydrocolloids: Structure, Properties, and Functions*; Plenum Press: New York, NY, USA, 1993.
41. Viswanathan, S.; Nallamuthu, T. Extraction of sodium alginate from selected seaweeds and their physicochemical and biochemical properties. *Int. J. Innov. Res. Sci. Eng. Technol.* **2014**, *3*, 2319–8753.
42. Gholamipoor, S.; Nikpour-Ghanavati, Y.; Oromiehie, A.R.; Mohammadi, M. Extraction and characterization of alginate from *Sargassum angustifolium* collected from Northern Coasts of Persian Gulf, Bushehr. *Int. Symp. Adv. Sci. Technol.* **2013**, *1*, 1–5.
43. Helmiyati, A.M. Characterization and properties of sodium alginate from brown algae used as an ecofriendly superabsorbent. *IOP Conf. Ser. Mater. Sci. Eng.* **2017**, *188*, 12019. [CrossRef]
44. Larsen, B.; Salem, D.M.S.A.; Sallan, M.A.E.; Mishrikey, M.M.; Beltagy, A.I. Characterization of the alginates from algae harvested at the Egyptian Red Seacoast. *Carbohydr. Res.* **2003**, *338*, 2325–2336. [CrossRef]
45. Atkins, P.; Paula, J.D. *Physical Chemistry*, 9th ed.; University Press: Oxford, UK, 2010.
46. Fenoradosa, T.A.; Ali, G.; Delattre, C.; Laroche, C.; Petit, E.; Wadouachi, A.; Michaud, P. Extraction and characterization of an alginate from the brown seaweed *Sargassum turbinarioides* Grunow. *Environ. Boil. Fishes* **2009**, *22*, 131–137. [CrossRef]
47. Sari-Chmayssem, N.; Taha, S.; Mawlawi, H.; Guégan, J.; Jeftić, J.; Benvegnu, T. Extracted and depolymerized alginates from brown algae *Sargassum vulgare* of Lebanese origin: Chemical, rheological, and antioxidant properties. *J. Appl. Phycol.* **2016**, *28*, 1915–1929. [CrossRef]
48. Davis, T.A.; Llanes, F.; Volesky, B.; Diaz-Pulido, G.; McCook, L.; Mucci, A. ¹H-NMR study of Na alginates extracted from *Sargassum* spp. in relation to metal biosorption. *Appl. Biochem. Biotechnol.* **2003**, *110*, 75–90. [CrossRef]
49. Anjani, P.P.; Damayanthi, E.; Handharyani, E. Antidiabetic potential of purple okra (*Abelmoschus esculentus* L.) extract in streptozotocin-induced diabetic rats. *IOP Conf. Ser. Earth Environ. Sci.* **2018**, *196*, 012038. [CrossRef]
50. Savova-Tsanova, S.; Ribarova, F.; Petkov, V. Quercetin content and ratios to total flavonols and total flavonoids in Bulgarian fruits and vegetables. *Bulg. Chem. Commun.* **2018**, *50*, 69–73.
51. Shui, G.; Peng, L.L. An improved method for the analysis of major antioxidants of *Hibiscus esculentus* Linn. *J. Chromatogr.* **2004**, *1048*, 17–24. [CrossRef]

52. Lo, T.C.; Chang, C.A.; Chiu, K.; Tsay, P.; Jen, J. Correlation evaluation of antioxidant properties on the monosaccharide components and glycosyl linkages of polysaccharide with different measuring methods. *Carbohydr. Polym.* **2011**, *86*, 320–327. [CrossRef]
53. Verma, A.K.; Singh, H.; Satyanarayana, M. Flavone-based novel antidiabetic and antidyslipidemic agents. *J. Med. Chem.* **2012**, *55*, 4551–4567. [CrossRef]
54. Wei, C.; Yang, X.; Wang, D.; Fang, F.; Lai, J.; Wang, F.; Wu, T. Fatty acid composition and evaluation on antioxidation activities of okra seed oil under ultrasonic wave extraction. *Cereals Oils Assoc.* **2016**, *31*, 89–93.
55. Husen, S.A.; Wahyuningsih, S.P.A.; Ansori, A.N.M.; Hayaza, S.; Susilo, R.J.K.; Darmanto, W.; Winarni, D. The effect of okra (*Abelmoschus esculentus* Moench) pods extract on malondialdehyde and cholesterol level in STZ-induced diabetic mice. *Ecol. Environ. Conserv.* **2019**, *25*, 50–56.
56. Husen, S.A.; Khaleyla, F.; Ansori, A.N.M.; Susilo, R.J.K.; Winarni, D. Antioxidant activity assay of alpha-mangostin for amelioration of kidney structure and function in diabetic mice. *Adv. Soc. Sci. Educ. Humanit. Res.* **2018**, *98*, 84–88.
57. Andrews, S.N.; Jeong, E.; Prausnitz, M.R. Transdermal delivery of molecules is limited by full epidermis, not just stratum corneum. *Pharm. Res.* **2013**, *30*, 1099–1109. [CrossRef]
58. Mathes, S.H.; Ruffner, H.; Graf-Hausner, U. The use of skin models in drug development. *Adv. Drug Deliv. Rev.* **2014**, *69*, 81–102. [CrossRef] [PubMed]
59. Tan, W.S.; Arulselvan, P.; Ng, S.; Taib, C.N.M.; Sarian, M.N.; Fakurazi, S. Improvement of diabetic wound healing by topical application of Vicenin-2 hydrocolloid film on Sprague Dawley rats. *Complementary Altern. Med.* **2019**, *19*, 20. [CrossRef]
60. Jain, N. A review on *Abelmoschus esculentus*. *Pharmacacia* **2012**, *1*, 1–8.
61. Kim, M.H.; Liu, W.; Borjesson, D.L.; Curry, F.R.; Miller, L.S.; Cheung, A.L.; Liu, F.T.; Isseroff, R.R.; Simon, S.I. Dynamics of neutrophil infiltration during cutaneous wound healing and infection using fluorescence imaging. *J. Investig. Dermatol.* **2008**, *128*, 1812–1820. [CrossRef] [PubMed]
62. Wong, S.L.; Demers, M.; Martinod, K.; Gallant, M.; Wang, Y.; Goldfine, A.B. Diabetes primes neutrophils to undergo NETosis, which impairs wound healing. *Nat. Med.* **2015**, *21*, 815–819. [CrossRef]
63. Patel, S.; Srivastava, S.; Singh, M.R.; Singh, D. Mechanistic insight into diabetic wounds: Pathogenesis, molecular targets and treatment strategies to pace wound healing. *Biomed. Pharmacother.* **2019**, *112*, 1086–1115. [CrossRef]
64. Malik, S.B.; Jayashree, B.S.; Shenoy, R.R. Epigenetic modulation of macrophage polarization-perspectives in diabetic wounds. *J. Diabetes Complicat.* **2018**, *32*, 524–530. [CrossRef]
65. Smith, J.L.; Sheffield, L.G. Production and regulation of leptin in bovine mammary epithelial cells. *Domest. Anim. Endocrinol.* **2002**, *22*, 145–154. [CrossRef]
66. Heublein, H.; Bader, A.; Giri, S. Preclinical and clinical evidence for stem cell therapies as treatment for diabetic wounds. *Drug Discov. Today* **2015**, *20*, 703–717. [CrossRef]
67. Bello, Y.M.; Philips, T.J. Recent advance in wound healing. *JAMA* **2000**, *283*, 716–718. [CrossRef]
68. Aderibigbe, B.A.; Buyana, B. Alginate in wound dressing. *Pharmaceutics* **2018**, *10*, 42. [CrossRef] [PubMed]
69. Uzun, M. A Review of wound management materials. *J. Text. Eng. Fash. Technol.* **2018**, *4*, 53–59. [CrossRef]
70. Wang, T.; Gu, Q.; Zhao, J.; Mei, J.; Shao, M.; Pan, Y.; Zhang, J.; Wu, H.; Zhang, Z.; Liu, F. Calcium alginate enhances wound healing by up-regulating the ratio of collagen types I/III in diabetic rats. *Int. J. Clin. Exp. Pathol.* **2015**, *8*, 6636–6645.
71. Wahyuningsih, S.P.A.; Pramudya, M.; Putri, I.P.; Winarni, D.; Savira, N.I.I.; Darmanto, W. Crude polysaccharides from okra pods (*Abelmoschus esculentus*) grown in Indonesia enhance the immune response due to bacterial infection. *Adv. Pharmacol. Sci.* **2018**, *1*, 450–538. [CrossRef] [PubMed]
72. Capapas, C.A.; Reas, D.D. Wound Healing Activity of the Extract from the Fresh Fruits of Okra, *Abelmoschus esculentus* (Linn., 1753) on Rabbits. Ph.D. Thesis, University of San Carlos-Josef Baumgartner Learning Resource Center, Science and Technology Section, Cebu, Philippines, March 2012.
73. Farooqui, M.B.; Khasim, S.M.; Rafiq, M.; Khan, A.A. Evaluation of wound healing activity of *Abelmoschus esculentus* (Linn.) in albino wistar rats. *Eur. J. Pharm. Med. Res.* **2018**, *5*, 508–511.



2020-14

ORIGINALITY REPORT

15%

SIMILARITY INDEX

10%

INTERNET SOURCES

14%

PUBLICATIONS

0%

STUDENT PAPERS

PRIMARY SOURCES

- 1 www.mdpi.com 1%

Internet Source
- 2 Sacha Pérocheau Arnaud, Linglin Wu, Maria-Angelica Wong Chang, James W. Comerford et al. "New bio-based monomers: tuneable polyester properties using branched diols from biomass", Faraday Discussions, 2017 1%

Publication
- 3 Ivo Campione, Francesca Lucchi, Nicola Santopuoli, Leonardo Seccia. "3D Thermal Imaging System with Decoupled Acquisition for Industrial and Cultural Heritage Applications", Applied Sciences, 2020 <1%

Publication
- 4 Fankai Kong, Hengxu Liu, Binghan Wang, Huaqiu Ding, Zhen Jiang, Hailong Chen, Hongli Pan, Weiming Su. "Wind-Load Response and Evacuation Efficiency Analysis of Marine Evacuation Inflatable Slide", Applied Sciences, 2019 <1%

Publication

5	www.ncbi.nlm.nih.gov Internet Source	<1 %
6	bmccomplementmedtherapies.biomedcentral.com Internet Source	<1 %
7	Bojan Starman, Andraž Maček, Primož Rus, Štefan Obid, Aleš Kralj, Miroslav Halilovič. "Primary Seal Deformation in Multipane Glazing Units", Applied Sciences, 2020 Publication	<1 %
8	M. Fleur Sernee, Julie E. Ralton, Tracy L. Nero, Lukasz F. Sobala et al. "A Family of Dual-Activity Glycosyltransferase-Phosphorylases Mediates Mannogen Turnover and Virulence in Leishmania Parasites", Cell Host & Microbe, 2019 Publication	<1 %
9	ro.ecu.edu.au Internet Source	<1 %
10	www.tandfonline.com Internet Source	<1 %
11	Leila Golpasandhagh, Parvin Salehi, Babak Karimi, Eskandar Moghimipour. "Therapeutic effect of Ziziphus lotus honey on hard palate ulcers in rats", Medical Studies, 2021 Publication	<1 %

- 12 Nachiket Patel, Darshan Lalwani, Steven Gollmer, Elisha Injeti, Youssef Sari, Jerry Nesamony. "Development and evaluation of a calcium alginate based oral ceftriaxone sodium formulation", Progress in Biomaterials, 2016
Publication <1 %
-
- 13 Hengameh Homayouni, Gholamreza Kavooosi, Seyed Mehdi Nassiri. "Physicochemical, antioxidant and antibacterial properties of dispersion made from tapioca and gelatinized tapioca starch incorporated with carvacrol", LWT, 2017
Publication <1 %
-
- 14 S. Suhariningsih, Suryani Dyah Astuti, Saikhu Akhmad Husen, Dwi Winarni et al. "The combined effect of magnetic and electric fields using on/off infrared light on the blood sugar level and the diameter of Langerhans islets of diabetic mice", Veterinary World, 2020
Publication <1 %
-
- 15 ousar.lib.okayama-u.ac.jp
Internet Source <1 %
-
- 16 www.freepatentsonline.com
Internet Source <1 %
-
- 17 Roberto Testa, Anna Bonfigli, Stefano Genovese, Valeria De Nigris, Antonio Ceriello. <1 %

"The Possible Role of Flavonoids in the Prevention of Diabetic Complications",
Nutrients, 2016

Publication

18

Saikhu Akhmad Husen, Dwi Winarni, Firas Khaleyra, Septian Hary Kalqutny, Arif Nur Muhammad Ansori. "Activity assay of mangosteen (*Garcinia mangostana* L.) pericarp extract for decreasing fasting blood cholesterol level and lipid peroxidation in type-2 diabetic mice", AIP Publishing, 2017

Publication

<1 %

19

www.frontiersin.org

Internet Source

<1 %

20

Binbin Li, Zengyu Mi, Zhenghe Zhang. "Willingness of the New Generation of Farmers to Participate in Rural Tourism: The Role of Perceived Impacts and Sense of Place", Sustainability, 2020

Publication

<1 %

21

Uhl, F.M.. "UV curable epoxy acrylate-clay nanocomposites", European Polymer Journal, 200610

Publication

<1 %

22

worldwidescience.org

Internet Source

<1 %

23

www.dovepress.com

Internet Source

<1 %

24

dipot.ulb.ac.be

Internet Source

<1 %

25

Alessandro Pellis, James W. Comerford, Andrew J. Maneffa, Mika H. Sipponen, James H. Clark, Thomas J. Farmer. "Elucidating enzymatic polymerisations: Chain-length selectivity of *Candida antarctica* lipase B towards various aliphatic diols and dicarboxylic acid diesters", *European Polymer Journal*, 2018

Publication

<1 %

26

Bu-Yan Liao, Dan-Ye Zhu, Kiran Thakur, Ling Li, Jian-Guo Zhang, Zhao-Jun Wei. "Thermal and Antioxidant Properties of Polysaccharides Sequentially Extracted from Mulberry Leaves (*Morus alba* L.)", *Molecules*, 2017

Publication

<1 %

27

Wong, Tin W., and Nurjaya Sumiran. "Oral calcium pectinate-insulin nanoparticles: influences of alginate, sodium chloride and Tween 80 on their blood glucose lowering performance : Oral pectin-insulin nanoparticles", *Journal of Pharmacy and Pharmacology*, 2014.

Publication

<1 %

- | | | |
|----|--|------|
| 28 | repository.uhamka.ac.id
Internet Source | <1 % |
| 29 | research.aalto.fi
Internet Source | <1 % |
| 30 | www.apjtb.com
Internet Source | <1 % |
| 31 | "Alginates and Their Biomedical Applications",
Springer Science and Business Media LLC,
2018
Publication | <1 % |
| 32 | M. C. Lamas, C. Bregni, M. D'Aquino, J.
Degrossi, R. Firenstein. " Calcium Alginate
Microspheres of ", Drug Development and
Industrial Pharmacy, 2001
Publication | <1 % |
| 33 | Zefrizal Nurdin, Hilaire Tegnan. "Legal
Certainty in the Management of Agricultural
Land Pawning in the Matrilineal Minangkabau
Society, West Sumatra", Land, 2019
Publication | <1 % |
| 34 | jurnal.ugm.ac.id
Internet Source | <1 % |
| 35 | Lukas R.H. Gerken, Anna L. Neuer, Pascal M.
Gschwend, Kerda Keevend et al. "Scalable
Synthesis of Ultrasmall Metal Oxide Radio- | <1 % |

Enhancers Outperforming Gold", Chemistry of Materials, 2021

Publication

-
- 36 Zlatko Nedelko, Vojko Potocan. "Sustainability of Organizations: The Contribution of Personal Values to Democratic Leadership Behavior Focused on the Sustainability of Organizations", Sustainability, 2021 <1 %
Publication
-
- 37 www.researchsquare.com <1 %
Internet Source
-
- 38 I K Sumandiarsa, D G Bengen, J Santoso, H I Januar. " Nutritional composition and alginate characteristics of (*C. Agardh*, 1824) growth in Sebesi island coastal, Lampung-Indonesia ", IOP Conference Series: Earth and Environmental Science, 2020 <1 %
Publication
-
- 39 Sugiono Sugiono, Masruri Masruri, Teti Estiasih, Simon Bambang Widjarnako. " Structural and Rheological Characteristics of Alginate from Extracted by Twin Screw Extruder ", Journal of Aquatic Food Product Technology, 2019 <1 %
Publication
-
- 40 Tian-yang Wang, Qing Li, Kai-shun Bi. "Bioactive flavonoids in medicinal plants: <1 %

Structure, activity and biological fate", Asian
Journal of Pharmaceutical Sciences, 2018

Publication

-
- | | | |
|----|---|------|
| 41 | publications.waset.org
Internet Source | <1 % |
|----|---|------|
-
- | | | |
|----|---|------|
| 42 | repository.tnmgrmu.ac.in
Internet Source | <1 % |
|----|---|------|
-
- | | | |
|----|---|------|
| 43 | www.int-res.com
Internet Source | <1 % |
|----|---|------|
-
- | | | |
|----|---|------|
| 44 | Nouha Sari-Chmayssem, Samir Taha, Hiba Mawlawi, Jean-Paul Guégan, Jelena Jeftić, Thierry Benvegna. "Extracted and depolymerized alginates from brown algae <i>Sargassum vulgare</i> of Lebanese origin: chemical, rheological, and antioxidant properties", <i>Journal of Applied Phycology</i> , 2015
Publication | <1 % |
|----|---|------|
-
- | | | |
|----|---|------|
| 45 | Taratra Andrée Fenoradosoa. "Extraction and characterization of an alginate from the brown seaweed <i>Sargassum turbinarioides</i> Grunow", <i>Journal of Applied Phycology</i> , 05/14/2009
Publication | <1 % |
|----|---|------|
-
- | | | |
|----|--|------|
| 46 | Xuqiang Nie, Han Zhang, Xiujun Shi, Jiufeng Zhao, Yu Chen, Faming Wu, Jianwen Yang, Xiaohui Li. "Asiaticoside nitric oxide gel | <1 % |
|----|--|------|

accelerates diabetic cutaneous ulcers healing by activating Wnt/ β -catenin signaling pathway", International Immunopharmacology, 2020
Publication

47 biomarkerres.biomedcentral.com <1 %
Internet Source

48 dspace.lib.cranfield.ac.uk <1 %
Internet Source

49 pure.ulster.ac.uk <1 %
Internet Source

50 Nathalie Fiaschi-Taesch, Andrew F. Stewart, Adolfo Garcia-Ocaña. "Improving islet transplantation by gene delivery of hepatocyte growth factor (HGF) and its downstream target, protein kinase B (PKB)/Akt", Cell Biochemistry and Biophysics, 2007
Publication

51 Roya Abka Khajouei, Javad Keramat, Nasser Hamdami, Alina-Violeta Ursu et al. "Extraction and characterization of an alginate from the Iranian brown seaweed Nizimuddinia zanardini", International Journal of Biological Macromolecules, 2018
Publication

- | | | |
|----|--|------|
| 52 | Subramoniam, Appian. "Anti-Diabetes Mellitus Plants", Plants with Anti-Diabetes Mellitus Properties, 2016.
Publication | <1 % |
| 53 | Xiaojun Huang, Shaoping Nie, Hailan Cai, Guanya Zhang, Steve W. Cui, Mingyong Xie, Glyn O. Phillips. "Study on Dendrobium officinale O-acetyl-glucomannan (Dendronan): Part IV. Immunomodulatory activity in vivo", Journal of Functional Foods, 2015
Publication | <1 % |
| 54 | Xue Zhang, Maria Morits, Christopher Jonkergouw, Ari Ora et al. "Three-Dimensional Printed Cell Culture Model Based on Spherical Colloidal Lignin Particles and Cellulose Nanofibril-Alginate Hydrogel", Biomacromolecules, 2020
Publication | <1 % |
| 55 | baadalsg.inflibnet.ac.in
Internet Source | <1 % |
| 56 | theses.bham.ac.uk
Internet Source | <1 % |
| 57 | www.atlantis-press.com
Internet Source | <1 % |
| 58 | www.mdpi.org
Internet Source | <1 % |

59

www.science.gov

Internet Source

<1 %

60

Eduardo Noriega-Iribe, Laura Díaz-Rubio, Arturo Estolano-Cobián, Victor Wagner Barajas-Carrillo et al. "In Vitro and In Silico Screening of 2,4,5-Trisubstituted Imidazole Derivatives as Potential Xanthine Oxidase and Acetylcholinesterase Inhibitors, Antioxidant, and Antiproliferative Agents", *Applied Sciences*, 2020

Publication

<1 %

61

K Ameena, C Dilip, R Saraswathi, PN Krishnan, C Sankar, SP Simi. "Isolation of the mucilages from *Hibiscus rosasinensis* linn. and Okra (*Abelmoschus esculentus* linn.) and studies of the binding effects of the mucilages", *Asian Pacific Journal of Tropical Medicine*, 2010

Publication

<1 %

62

Lorena Anna Ditta, Estella Rao, Fiorenza Provenzano, Jesús Lozano Sánchez et al. "Agarose/ κ -carrageenan-based hydrogel film enriched with natural plant extracts for the treatment of cutaneous wounds", *International Journal of Biological Macromolecules*, 2020

Publication

<1 %

63

Mahmoud Soliman, Ahmed Abdelrahiem Sadek, Hani Nasser Abdelhamid, Kamal

<1 %

Hussein. "Graphene oxide-cellulose nanocomposite accelerates skin wound healing", Research in Veterinary Science, 2021
Publication

64

Nur Azmi R. Setyawidati, Maya Puspita, Awaludin H. Kaimuddin, Ita Widowati et al. "Seasonal biomass and alginate stock assessment of three abundant genera of brown macroalgae using multispectral high resolution satellite remote sensing: A case study at Ekas Bay (Lombok, Indonesia)", Marine Pollution Bulletin, 2018
Publication

<1 %

65

P P Anjani, E Damayanthi, Rimbawan, E Handharyani. " Antidiabetic potential of purple okra (L.) extract in streptozotocin-induced diabetic rats ", IOP Conference Series: Earth and Environmental Science, 2018
Publication

<1 %

66

Supaporn Noppakundilograt, Phianghathai Piboon, Wilaiporn Graisuwan, Roongkan Nuisin, Suda Kiatkamjornwong. "Encapsulated eucalyptus oil in ionically cross-linked alginate microcapsules and its controlled release", Carbohydrate Polymers, 2015
Publication

<1 %

67

Yashar Mehrbani Azar, Carola U Niesler, Mari van de Vyver. "Ex vivo antioxidant

<1 %

preconditioning improves the survival rate of bone marrow stem cells in the presence of wound fluid", Wound Repair and Regeneration, 2020

Publication

68

eprints.usq.edu.au

Internet Source

<1 %

69

www.e-sciencecentral.org

Internet Source

<1 %

70

Agoston Jerga, Aniruddha Raychaudhuri, Peter A. Tipton. " C5-Mannuronan Epimerase: Steady-State Kinetics and Characterization of the Product ", Biochemistry, 2006

Publication

<1 %

71

Fatemeh Ahmadkhani Khari, Marziyeh Khatibzadeh, Niyaz Mohammad Mahmoodi, Kamaladin Gharanjig. "Removal of anionic dyes from aqueous solution by modified alginate", Desalination and Water Treatment, 2013

Publication

<1 %

72

Kajal Chakraborty, Anusree Maneesh, Fasina Makkar. "Antioxidant Activity of Brown Seaweeds", Journal of Aquatic Food Product Technology, 2016

Publication

<1 %

73 Lilis Iskandar, Luis Rojo, Lucy Di Silvio, Sanjukta Deb. "The effect of chelation of sodium alginate with osteogenic ions, calcium, zinc, and strontium", *Journal of Biomaterials Applications*, 2019
Publication <1%

74 Lu Ren, Yacine Hemar, Conrad O. Perera, Gillian Lewis, Geoffrey W. Krissansen, Peter K. Buchanan. "Antibacterial and antioxidant activities of aqueous extracts of eight edible mushrooms", *Bioactive Carbohydrates and Dietary Fibre*, 2014
Publication <1%

75 Tatiana I. Imbs, Svetlana P. Ermakova, Olesya S. Malyarenko (Vishchuk), Vladimir V. Isakov, Tatiana N. Zvyagintseva. "Structural elucidation of polysaccharide fractions from the brown alga *Coccophora langsdorfii* and in vitro investigation of their anticancer activity", *Carbohydrate Polymers*, 2016
Publication <1%

76 Yashar Mehrbani Azar, Carola U. Niesler, Mari Vyver. "Ex vivo antioxidant preconditioning improves the survival rate of bone marrow stem cells in the presence of wound fluid", *Wound Repair and Regeneration*, 2020
Publication <1%

77	Internet Source	<1 %
78	bioresources.cnr.ncsu.edu Internet Source	<1 %
79	dsc.duq.edu Internet Source	<1 %
80	repositorium.sdum.uminho.pt Internet Source	<1 %
81	scitepress.org Internet Source	<1 %
82	www.scielo.br Internet Source	<1 %
83	"Nanotechnology in Skin, Soft Tissue, and Bone Infections", Springer Science and Business Media LLC, 2020 Publication	<1 %
84	Enamul Haque Mojumdar, Lone Bruhn Madsen, Henri Hansson, Ida Taavoniku et al. "Probing Skin Barrier Recovery on Molecular Level Following Acute Wounds: An In Vivo/Ex Vivo Study on Pigs", Biomedicines, 2021 Publication	<1 %
85	Miratul Khasanah, Alfa Akustia Widati, Usreg Sri Handajani, Masfah Raudlotus Shofiyyah, Sabrina Aulia Rakhma, Herwin Predianto. "Imprinted zeolite modified carbon paste	<1 %

electrode as a selective potentiometric sensor for blood glucose", AIP Publishing, 2020

Publication

86

Polysaccharides, 2015.

Publication

<1 %

87

Qi Ge, Liang Chen, Min Tang, Shu Zhang, Lanlan Liu, Lu Gao, Shangshang Ma, Ming Kong, Qin Yao, Fan Feng, Keping Chen.

"Analysis of mulberry leaf components in the treatment of diabetes using network pharmacology", European Journal of Pharmacology, 2018

Publication

<1 %

88

Sugiono Sugiono, Masruri Masruri, Teti Estiasih, Simon Bambang Widjanarko.

"Optimization of extrusion-assisted extraction parameters and characterization of alginate from brown algae (*Sargassum cristaefolium*)", Journal of Food Science and Technology, 2019

Publication

<1 %

89

ir.canterbury.ac.nz

Internet Source

<1 %

90

Ewelina Juszczuk, Piotr Kulinowski, Ewelina Baran, Artur Birczyński et al. "Spatiotemporal Analysis of Hydration Mechanism in Sodium Alginate Matrix Tablets", Materials, 2021

Publication

<1 %

91 Ha, Byung, Eun Shin, Jung-Eun Park, and Yun Shon. "Anti-Diabetic Effect of Balanced Deep-Sea Water and Its Mode of Action in High-Fat Diet Induced Diabetic Mice", *Marine Drugs*, 2013.

Publication

<1 %

92 Sara Seidelin Majidi, Yingchun Su, Mathias Lindh Jørgensen, Christoph Müller, Pourya Forooghi, Guangjun Nie, Menglin Chen. "Raleigh Instability-Driven Coaxial Spinning of Knotted Cell-Laden Alginate Fibers as Artificial Lymph Vessels", *ACS Applied Materials & Interfaces*, 2021

Publication

<1 %

93 Woan Sean Tan, Palanisamy Arulselvan, Shiew-Fern Ng, Che Norma Mat Taib, Murni Nazira Sarian, Sharida Fakurazi.

"Improvement of diabetic wound healing by topical application of Vicenin-2 hydrocolloid film on Sprague Dawley rats", *BMC Complementary and Alternative Medicine*, 2019

Publication

<1 %

94 repository.unair.ac.id

Internet Source

<1 %

Exclude quotes On

Exclude matches Off

Exclude bibliography On