

Interactions of primaquine and chloroquine with PEGylated phosphatidylcholine liposomes

by Andang Miatmoko

Submission date: 05-Oct-2021 10:50PM (UTC+0800)

Submission ID: 1665962840

File name: Miatmoko_et_al-2021-Scientific_Reports.pdf (1.78M)

Word count: 8065

Character count: 44146



OPEN Interactions of primaquine and chloroquine with PEGylated phosphatidylcholine liposomes

Andang Miatmoko[✉], Ira Nurjannah, Nuril Fadilatul Nehru, Noorma Rosita, Esti Hendradi, Retno Sari & Juni Ekowati

This study aimed to analyze the interaction of primaquine (PQ), chloroquine (CQ), and liposomes to support the design of optimal liposomal delivery for hepatic stage malaria infectious diseases. The liposomes were composed of hydrogenated soybean phosphatidylcholine, cholesterol, and distearoyl-*sn*-glycero-3-phosphoethanolamine-*N*-(methoxy[polyethyleneglycol]-2000), prepared by thin film method, then evaluated for physicochemical and spectroscopic characteristics. The calcein release was further evaluated to determine the effect of drug co-loading on liposomal membrane integrity. The results showed that loading PQ and CQ into liposomes produced changes in the infrared spectra of the diester phosphate and carbonyl ester located in the polar part of the phospholipid, in addition to the alkyl group (CH₂) in the nonpolar portion. Moreover, the thermogram revealed the loss of the endothermic peak of liposomes dually loaded with PQ and CQ at 186.6 °C, which is identical to that of the phospholipid. However, no crystallinity changes were detected through powder X-ray diffraction analysis. Moreover, PQ, with either single or dual loading, produced the highest calcein release profiles from the liposomes than that of CQ. The dual loading of PQ and CQ tends to interact with the polar head group of the phosphatidylcholine bilayer membrane resulted in an increase in water permeability of the liposomes.

Primaquine (PQ) is the only effective anti-malarial used for the treatment of sporozoites in the hepatic phase of malaria infectious disease. However, it lacks efficacy against the asexual form of *Plasmodium* spp. in blood, indicating that it can not be used as a monotherapy, but should be administered in combination with blood schizonticides¹⁻³. In addition, the use of PQ is limited by its tendency to cause serious side effects, including hemolysis in individuals deficient in glucose-6-phosphate dehydrogenase^{1,2,4-6}. Despite its currently limited therapeutic use because of widespread resistance⁷⁻⁹, the combined use of chloroquine (CQ), a blood schizonticide, reduces the toxicity of PQ while increasing its activity. A study by Fasinu et al.¹⁰ reported that CQ influences several metabolic pathways known to play a role in the activity and toxicity of PQ, encompassing the effect of hemolysis. In particular, CQ suppresses the number of metabolites generated through CYP2D6-mediated metabolism. Moreover, CQ changes the disposition and pharmacokinetic profiles¹¹, resulting in higher drug levels and tissue exposure. In addition, the combination is also used clinically in the treatment of *Plasmodium vivax* malaria, and CQ also enhances the sensitivity of *Plasmodium falciparum* to PQ¹². The use of liposomes as drug delivery carriers increases the activity of anti-malaria drugs¹³. However, PQ is known to influence the structure of the liposomal bilayer membrane. Basso et al.¹⁴ reported the existence of an electrostatic interaction between the negative charges of a phosphate group on the polar phospholipid portion of dimyristoylphosphatidylcholine (DMPC) and a positive nitrogen charge in the PQ structure. Furthermore, a hydrophobic interaction also occurs between the quinoline ring of PQ and the hydrocarbon chain of DMPC^{14,15}. Therefore, the existence of these two interactions leads to the insertion of PQ into the DMPC structure, thereby disrupting the arrangement and dynamics of the acyl chain rotation and resulting in enhanced fluidity of the bilayer membrane. Conversely, it was reported that CQ induces the opposite effect via its interaction with the polar part of dipalmitoylphosphatidylcholine (DPPC), causing the absorption of CQ molecules on the surface of the liposomes¹⁵⁻¹⁷. This inhibits the movement of the acyl chain, consequently enhancing the rigidity of the bilayer membrane¹⁶.

Changes in liposome membrane rigidity affect drug release^{18,19}, as denoted by the more rapid drug release from egg yolk phosphatidylcholine, which possesses a more fluid structure, than from the relatively rigid DPPC²⁰. Moreover, lipids constituted in a non-rigid liposomal membrane often cause leakage of entrapped drugs, a

Department of Pharmaceutical Sciences, Faculty of Pharmacy, Universitas Airlangga, Nanizar Zaman Joenoes Building, Campus C Unair, Mulyorejo 60115, Indonesia. ✉email: andang-m@ff.unair.ac.id

Formula	Particle size (nm)	Polydispersity index (PDI)	ζ-Potential (mV)	Encapsulation efficiency (%)	Loading capacity (%)
Lipo-PQ	114.0 ± 4.2	0.24 ± 0.04	-12.33 ± 2.98	80.65 ± 11.26	16.50 ± 3.70
Lipo-CQ	123.4 ± 5.9	0.31 ± 0.01	-16.38 ± 3.91	54.56 ± 10.59	6.05 ± 0.97
Lipo-PQCQ	130.8 ± 8.3	0.31 ± 0.01	-12.33 ± 2.98	7.17 ± 2.25 (PQ)	1.02 ± 0.37 (PQ)
				31.78 ± 3.85 (CQ)	4.52 ± 0.63 (CQ)

Table 1. Characteristics of liposomes loaded with primaquine/PQ (Lipo-PQ), chloroquine/CQ (Lipo-CQ), and both drugs (Lipo-PQCQ) following incubation at 60 °C for 20 min. Each value represents the mean ± SD (n = 3).

condition known to affect the therapeutic index^{18,19,21}. In this case, membrane rigidity is influenced by the characteristics of the lipid composition³⁵ employed, as well as the addition of cholesterol to the exterior of the liposomal membrane^{21,22}. Furthermore, drug release is potentially influenced by the presence of precipitation or the aggregation of drugs in the liposomes²³. A previous study reported the tendency for colloidal aggregate formation between drugs and polymers in liposomes which can slow drug release²⁴.

Combining two or more drugs within the same nanocarrier using a dual loading technique can control the drug release rate, thereby affecting the biodistribution and metabolism of each drug²⁵. A previous study under taken by the authors of this article revealed that the dual loading of PQ and CQ significantly influenced the efficiency of drug trapping and release²⁶. In single-loaded liposomes, the encapsulation efficiencies were 72% ± 4% for PQ and 56% ± 15% for CQ, whereas in co-loaded liposomes, they were 6% ± 1% and 31% ± 2%, respectively. In addition, liposomes co-loaded with PQ and CQ exhibited relatively slower drug release than those loaded with either drug alone. It has been reported that the encapsulation of two drugs in the same nanocarrier can modify the release profile of each when they both interact with the bilayer membrane²⁷. Optimal delivery to hepatocytes should constitute the main objective when treating a malarial sporozoite invasion. Both positive therapeutic effects and reduced hemolysis in cases of patients suffering from glucose-6-phosphate dehydrogenase deficiency should be produced. Therefore, the use of liposomes as drug carriers is indispensable, rendering an effective strategy for further liposome formulation essential in order to achieve high and stable drug encapsulation.

In the current study, the effect of dual-loaded PQ and CQ on the integrity of the liposomal bilayer membrane was analyzed in relation to changes in membrane rigidity. This evaluation involved determining the physicochemical characteristics and release profile of the fluorescent compound calcein as indicators of membrane leakage^{28–30}. Calcein was used because of the ease with which it is entrapped in the aqueous intraliposomal phase because of its low Log *P* value. In addition, calcein is hydrophilic and exhibits no interaction with the liposomal membrane³¹. Analyzing the integrity of the liposomal bilayer membrane is extremely important for observing the level of carrier leakage which is positively correlated with stability during distribution through systemic circulation before reaching the hepatocytes. It is anticipated that the data obtained will prove useful for evaluating changes in the membrane structure of liposomes containing PQ and CQ.

5 Results and discussion

This study aimed to provide information related to the effect of PQ and CQ co-loading on the integrity of the bilayer membrane of liposomes. This analysis should be beneficial for designing optimal PQ and CQ delivery systems for malaria therapy, especially with regard to the hepatic phase. The liposomes were analyzed to determine their physicochemical characteristics and assess their calcein release profiles to confirm the integrity of the liposomal membrane. The physicochemical characteristics were specifically, evaluated using FTIR spectroscopy, P-XRD, and DTA. These evaluations were performed to analyze the interaction between the drugs and the lipid membrane of the liposomes^{32,33}.

In a previous study, the drug-to-lipid ratios of PQ and CQ were optimized during the drug loading process²⁶, in consideration of the dose ratios of both drugs in clinical practice^{34–36}. In this study, a saturated phospholipid, i.e. HSPC, was used as the lipid component and the liposomes were prepared under equal conditions. Moreover, citrate buffer pH 5.0 was employed as the hydrating solution since low pH may result in hydrolysis of phospholipid. In the previous report referred to above, a change in pH of the citrate buffer from 4.0 to 5.0 reduced drug loading with the result that only 35% of PQ and 69% of CQ was encapsulated in the liposomes^{37,38}. Moreover, the report showed that incubating the mixtures at a higher temperature than *T_m* of phospholipid, i.e. 60 °C, reduced the encapsulation efficiencies of PQ and CQ due to the increase in membrane water permeability causing a decrease in pH gradient during heating^{37,38}. All liposomes were similar with regard to particle size, PDI, and ζ-potential, reflecting the fact that loading PQ and CQ had no significant effects on their physical characteristics. However, when PQ was dually loaded with CQ into liposomes, the encapsulation efficiency decreased significantly, as shown in the authors' previous study²⁶. However, there were differences in their spectroscopic and crystallinity profiles, as demonstrated by the findings of this study.

Physical characteristics of the liposomes. The particle size, PDI, ζ-potential, drug encapsulation efficiency, and loading capacity of Lipo-PQ, Lipo-CQ, and Lipo-PQCQ are presented in Table 1. The results revealed no significant differences in the obtained values, as particle size, PDI, and ζ-potential ranging from 114.0 to 130.8 nm, 0.24–0.31, and -16.38 to -12.33 mV, respectively. Following dual loading of these two drugs, the encapsulation efficiencies decreased significantly from approximately 80 to 7% and 54 to 31% respectively for

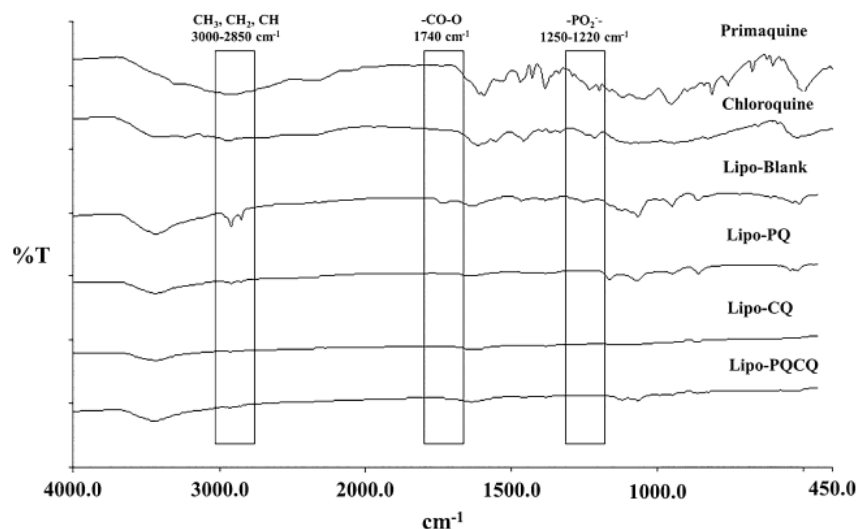


Figure 1. Fourier-transform infrared spectra of primaquine, chloroquine, blank liposomes (Lipo-Blank), primaquine-loaded liposomes (Lipo-PQ), chloroquine-loaded liposomes (Lipo-CQ), and liposomes loaded with both primaquine and chloroquine (Lipo-PQCQ) analyzed using the KBr pellet method.

PQ and CQ. The loading capacities were approximately 16% and 6% for Lipo-PQ and Lipo-CQ, but there were significant reductions in the amounts of PQ and CQ loaded into Lipo-PQCQ which stood at only 1% and 4% in each case. While PQ is soluble in water³⁹, its solubility is still almost 10–30 times lower than that of CQ which is categorized as freely water soluble⁴⁰. The solubility of both drugs has been known to be affected by pH^{39,40}. The contrasting solubility probably influences the intraliposomal physical condition of drugs after active loading using a pH gradient which may affect the drug loading. However, in the²⁶ study, the drugs i.e. PQ and CQ were added as drug solutions in PBS pH 7.4 (the outer liposomal phase) with citrate buffer pH 5 as the intraliposomal phase, in order to ensure that solubility exerts a minimal influence on the research results. Moreover, the transmission electron microscopy (TEM) images reveal that no drug aggregates were observed inside the liposomes, as presented in Supplementary Fig. S1. These results show that both PQ and CQ are still soluble in the intraliposomal media, thus providing no or minimal effects of drug solubility on membrane integrity. These results were similar to those of the previous study²⁶ proving that dual loading of PQ and CQ affects drug encapsulation without changing particle size or ζ -potentials. Consequently, physicochemical analysis is required. Having identified the typical interactions, appropriate further courses of action would be decided on for optimal dual delivery of PQ and CQ in cases of malaria.

Analysis of the physicochemical characteristics of the liposomes. FTIR profiles of the liposomes. In this study, FTIR analysis was used to determine the interactions of PQ and CQ with the liposomal membrane by observing the absorption band in the wavenumber ranges of particular functional groups. This included the diester phosphate (R-PO₂-R') and carbonyl ester (R-CO-O-R') located in the polar part of the HSPC phospholipid, as well as the alkyl group (CH₂) in the nonpolar portion^{41,42}. Lipo-PQ, Lipo-CQ, and Lipo-PQCQ were analyzed for their spectra identification using FTIR, and their profiles were compared with those of Lipo-Blank, free PQ, and free CQ. As shown in Fig. 1, in accordance with the wavenumbers of each functional group listed in Table 2, variations in the absorption intensity of functional groups were observed among the liposomes. The FTIR spectrum of Lipo-PQ exhibited absorption bands with reduced intensities in the wavenumber ranges of carbonyl ester and diester phosphate groups compared with the findings for Lipo-Blank. It has been reported that PQ interacts electrostatically with lipid polar head group causing local acyl chain disorder and less densely packed bilayer membrane gel. Moreover, the quinoline ring of PQ inserts between the acyl chain of the hydrophobic tail of phospholipids causes membrane fluidity^{4,15}. Therefore, the primaquine has probably been completely concealed inside the liposomes, producing the similar FTIR spectra of the Lipo-Blank and Lipo-PQ.

Meanwhile, Lipo-CQ and Lipo-PQCQ featured no phosphate and carbonyl group bands at 1740 cm⁻¹ and 1230 cm⁻¹, which reflect the interfacial and head region of the bilayer membrane⁴³. Hence, it was assumed that interaction probably occurred between the drugs and liposomes rendering them undetectable.

Furthermore, the CH₃, CH₂, and CH bonds of Lipo-CQ and Lipo-PQCQ exhibited weaker absorption bands than those of Lipo-Blank and Lipo-PQ. The absorption band of the alkyl group possibly serves as an indicator of the lipid sequence which reflects the order of arrangement. The shift to a higher wavenumber, reduction in intensity, and widening of the absorption band were indicative of an increase in the gauche conformation of the aliphatic lipid chain⁴². The FTIR spectrum also revealed a decline in intensity of Lipo-PQ compared with those of Lipo-CQ and Lipo-PQCQ, indicating an increase in the gauche conformation of its hydrocarbon chain. Thus,

Functional groups	Wavenumber (cm ⁻¹)						
	Ref	Prima-quine	Chloro-quine	Lipo-Blank	Lipo-PQ	Lipo-CQ	Lipo-PQCQ
O-H/N-H stretching	3550–3200	3297	3411; 3236	3442	3441	3441	3437
CH ₃ , CH ₂ , CH stretching	3000–2850	2968; 2945; 2883	2969; 2935; 2850	2956; 2919; 2851	2920; 2851	2924	2923
R-CO-OR' (carbonyl ester)	1740	–	–	1738	1739	–	–
C=C stretching	1630–1680	–	–	1636	1636	1632	1638
C-C ring stretching (quinolone)	1612	1612	1614	–	–	–	–
C-N stretching	1558	1533	1552	–	–	–	–
CH ₂ , CH ₃ bending	1470–1350	1469; 1430; 1385	1458; 1393; 1368	1467; 1384	1384	1458; 1384	1457; 1384
R-PO ₃ ⁻ -R' (diester phosphate)	1250–1220	1234	1245	1254	1253	–	–
C-O stretching	1250–970	1165	1132	1120	1165	1121	1121
P-O Asymmetric stretching	1058	1050	1065	1067	1070	1074	1066
N ⁺ -CH ₃ (choline)	970	–	–	–	–	–	–
=C-H, =CH ₂	995–880	953; 899	942; 907; 881	951; 863	950; 861	953; 863	952; 865

Table 2. The peak absorbance value of the infrared spectra of free primaquine (PQ), free chloroquine (CQ), blank liposomes (Lipo-Blank), primaquine-loaded liposomes (Lipo-PQ), chloroquine-loaded liposomes (Lipo-CQ), and liposome co-loaded with primaquine and chloroquine (Lipo-PQCQ).

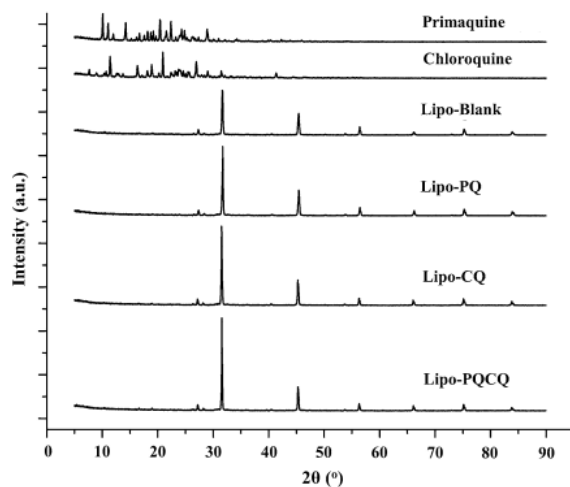


Figure 2. Powder X-ray diffraction analysis of primaquine, chloroquine, blank liposomes (Lipo-Blank), primaquine-loaded liposomes (Lipo-PQ), chloroquine-loaded liposomes (Lipo-CQ), and liposomes loaded with both primaquine and chloroquine (Lipo-PQCQ).

the arrangement and density of the hydrocarbon chain had changed, possibly reflecting increased membrane fluidity⁴⁴.

P-XRD profiles of the liposomes. The diffractograms of the liposomes were obtained using P-XRD. As shown in Fig. 2, the P-XRD pattern of the free PQ and free CQ exhibited several sharp peaks indicative of crystallinity. However, these crystal patterns were absent from the diffractograms of Lipo-PQ, Lipo-CQ, and Lipo-PQCQ, as well as Lipo-Blank. The X-ray diffractogram patterns of liposomes displayed sharp peaks showing a high degree of crystallinity and all these samples had peaks identical to one another, indicating a similar degree of crystallinity.

DTA profiles of the liposomes. In addition, the effects of PQ and CQ on the changes in the physical properties of liposomes were also supported by the DTA thermograms. The DTA results of liposomal membranes are contained in Figs. 3 and 4. As shown in Fig. 3, two endothermic peaks were observed for HPSC at 77.0 °C

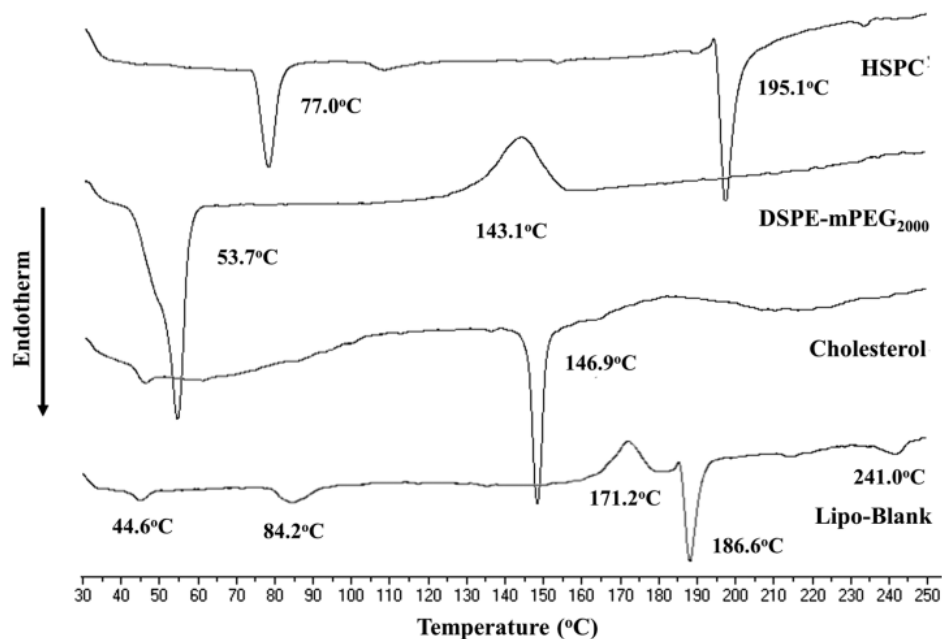


Figure 3. Differential thermal analysis of hydrogenated soybean phosphatidylcholine (HSPC), distearoyl-sn-glycero-3-phosphoethanolamine-N-(methoxy[polyethylene glycol]-2000) (DSPE-mPEG2000), cholesterol, and blank liposomes (Lipo-Blank).

and 195.1 °C, one endothermic peak and one exothermic peak were found for DSPE-mPEG₂₀₀₀ at 53.7 °C and 143.1 °C, respectively, and a single endothermic peak was identified for cholesterol at 146.9 °C. Moreover, endothermic peaks were identified at 44.6 °C, 84.2 °C, 186.6 °C, and 241.0 °C for Lipo-Blank. Meanwhile, following liposome formation, the peaks in the Lipo-Blank thermogram were identical to those of each of the lipid components, although some melting point shifts were identified.

Figure 4 presents the DTA thermograms of drug-loaded liposomes, free PQ, and free CQ. PQ had a sharp endothermic peak at 200.2 °C and a broad peak at 71.0 °C. Conversely, two sharp endothermic peaks were found at 188.5 °C and 216.6 °C for CQ. The drug-encapsulated liposomes displayed significant changes compared with those of the free drugs. Lipo-PQ had no identical endothermic peak to that of PQ. Moreover, compared with the findings for Lipo-Blank, the endothermic peak at 186.6 °C was not present, while a new endothermic peak appeared at 244.7 °C. There were also peak shifts at 44.0 °C and 81.2 °C. Moreover, in the thermogram of Lipo-CQ, the endothermic peak at 44.0 °C had disappeared, whereas an identical peak observed for Lipo-Blank had shifted to 183.8 °C. Lipo-CQ also had no identical peak to that of CQ, but a weak broad endothermic peak appeared at approximately 210 °C.

Meanwhile, Lipo-PQCQ experienced broad endothermic peaks at 62.1 °C and 75.3 °C and a sharp peak at 239.1 °C. However, the peak at 186.6 °C was absent. The thermogram peaks of Lipo-PQCQ were identical to those of PQ and Lipo-PQ.

There were shifts and losses of endothermic peaks in both the Lipo-PQ and Lipo-CQ thermograms compared with the findings in the Lipo-Blank thermogram. Furthermore, the endothermic peak displayed a major transition of the crystalline gel-liquid phase within the liposomes which is gelatinous at higher temperatures⁴⁵. In addition, the Lipo-PQCQ thermogram demonstrated the loss of the endothermic peak at 186.6 °C, identical to that for HSPC observed in the Lipo-Blank thermogram. The loss of the endothermic peak identical to that of HSPC was also observed in the Lipo-PQ thermogram, but not in the Lipo-CQ thermogram. The loss or decline of this peak is indicative of an increase in the distance between membranes which can reduce the strength of the phospholipid arrangement in the gel phase^{14,15}. This change is usually accompanied by a reduction in membrane rigidity together with decreased van der Waals bonds between acyl chains and phospholipids^{45,46}. Therefore, Lipo-PQCQ may experience diminished strength of its phospholipid arrangement as denoted by a liquid phase, resulting in increased fluidity of the bilayer membrane of the liposomes.

NMR spectra of liposomes. Data obtained via NMR analysis are proton signals which include chemical shifts and multiplicity, as well as signal integration. From the results of ¹H NMR, both CQ and PQ experienced interactions with liposomes.

The ¹H NMR spectrum of Lipo-Blank featured chemical shifts at 3.02 (s, 9H) and 3.82 ppm (m, 2H), which reflected the proton signals of C₁₃ and C₁₄, respectively, which bound to N atoms in the polar head of lipids in the bilayer (Fig. 5A). Moreover, the signals of C_{20,20'} bound to the CH₃ group underwent a chemical shift at 0.70 ppm

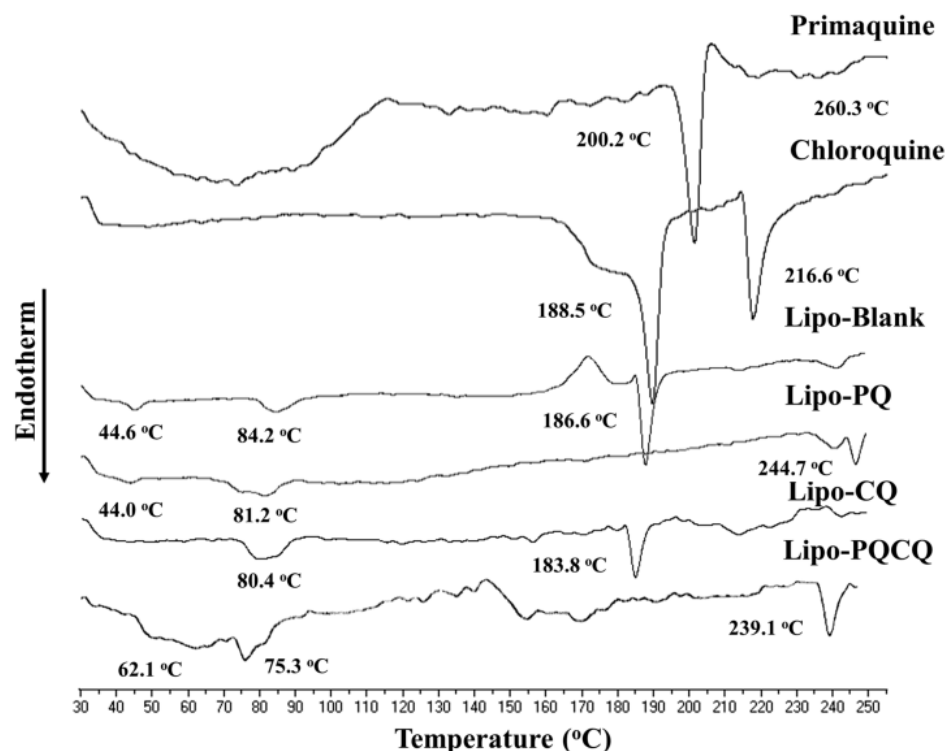


Figure 4. Differential thermal analysis of blank liposomes (Lipo-Blank), primaquine-loaded liposomes (Lipo-PQ), chloroquine-loaded liposomes (Lipo-CQ), and liposomes loaded with both primaquine and chloroquine (Lipo-PQCQ).

(m, 3H). The proton signals of alkyl (C–C) groups bound to an acyl group was observed for C_{1-10} and $C_{1'-10'}$ with a chemical shift at 1.09 ppm (m, 40H). In addition, the proton signals of C_{15} and $C_{15'}$ experienced chemical shifts at 2.14 (m, 2H) and 1.41 ppm (m, 2H), respectively. In addition, the proton signals of C_{12} and $C_{12'}$ appeared at 2.01 (m, 2H) and 1.67 ppm (m, 2H), respectively. These signals reflect the hydrocarbon chain as the hydrophobic part of the lipid bilayer. C–O groups which were observed at C_{15} , C_{16} , C_{17} , and C_{18} , appeared as chemical shifts at 5.10 (m, 1H), 4.10 (m, 2H), 3.48 (m, 2H), and 3.40 ppm (m, 2H), respectively.

However, the NMR spectra of Lipo-PQ and Lipo-CQ were similar to those of Lipo-Blank, as shown in Fig. 5B and C. However, dual loading of PQ and CQ into liposomes resulted in the appearance of the proton signals of the aromatic quinoline ring of PQ, whereas that of CQ had weak signal intensity, as shown in Fig. 5D. Some proton signals were noted for the aromatic ring of PQ. The proton signals of C_1 bound to N and C_2 atoms appeared as chemical shifts at 8.53 (m, 1H) and 7.49 ppm (m, 1H), respectively. Moreover, the chemical shift at 8.16 ppm (d, $J = 7.1$ Hz, 1H) indicated that C_3 was coupled to the proton of C_2 . The proton signals of C_4 and C_6 in the aromatic ring appeared as chemical shifts at 7.49 (m, 1H) and 6.65 ppm (d, $J = 7.3$ Hz, 1H), respectively, coupled with N7, whereas the C_5 methoxy group was represented by the chemical shift at 3.07 (s, 3H). The N7 proton signal appeared as a chemical shift at 6.25 ppm (m, 1H). The NMR spectra provided evidence that signal intensity of the aromatic quinoline ring was stronger for PQ than for CQ. This indicates that PQ had an important role in the fluidity of the membrane.

Profile of calcein release from liposomes. The effect of dual drug loading on membrane integrity was supported by the profiles of calcein release from the liposomes which was higher for Lipo-PQCQ and Lipo-PQ than for Lipo-CQ, as presented in Fig. 6. The results illustrated that the Lipo-CQ had the lowest percent calcein release of 7% after 48 h. Conversely, the percent calcein release for Lipo-PQ and Lipo-PQCQ was relatively similar, ranging from 17 to 20%. It is known that drug release from liposomes increases with increasing fluidity of the membrane³¹. Therefore, it has been established that the dual loading of PQ and CQ affected the fluidity of liposomes.

The physicochemical characteristics of the liposomal membrane and calcein release profile revealed that Lipo-PQ had relatively higher fluidity than Lipo-CQ leading to increased calcein release. Furthermore, the decreased integrity observed in Lipo-PQCQ was attributable to the increased membrane fluidity resulting from the interactions of PQ and CQ with the phospholipid bilayer. However, in a previous study, dual loading of PQ and CQ resulted in slower drug release compared with that in single drug-loaded liposomes²⁶. Calcein is a polyanionic

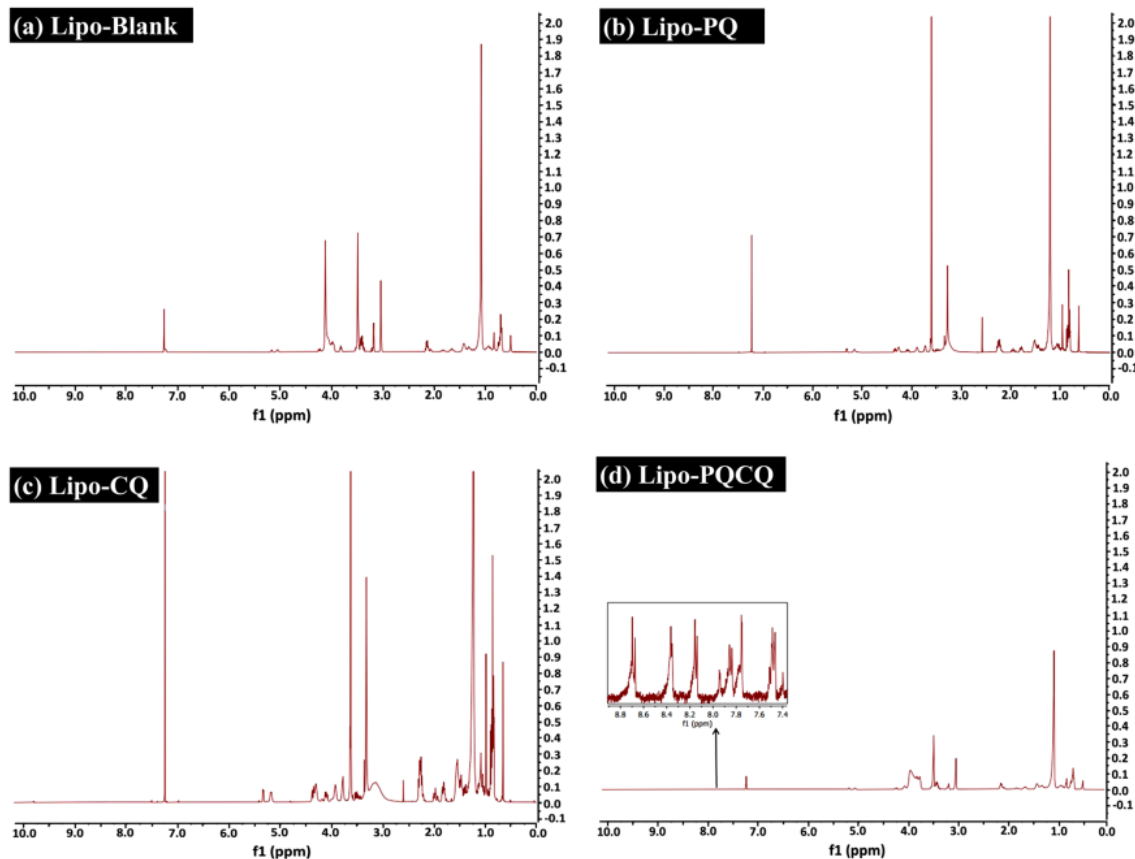


Figure 5. ^1H nuclear magnetic resonance spectra of blank liposomes (Lipo-Blank), primaquine-loaded liposomes (Lipo-PQ), chloroquine-loaded liposomes (Lipo-CQ), and liposomes loaded with both primaquine and chloroquine (Lipo-PQCQ) in CDCl_3 at 400 MHz.

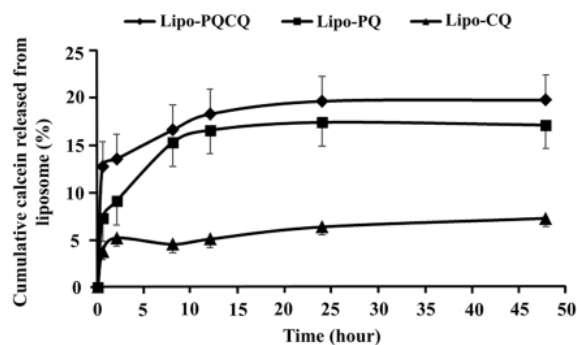


Figure 6. Profiles of calcein release from primaquine-loaded liposomes (Lipo-PQ), chloroquine-loaded liposomes (Lipo-CQ), and liposomes loaded with both primaquine and chloroquine (Lipo-PQCQ) in phosphate-buffered saline (pH 7.4) at 37°C .

molecule with negative surface potential charges which mainly diffuses through the phospholipid bilayer³¹. The burst release of calcein during the first hour of this study could be due to the higher amount of unionized calcein molecules in the low pH of the intraliposomal phase containing citrate buffer pH 5.0⁴⁷. This would, in turn, cause the release of a larger amount of calcein in the outer phase. The previous study of calcein release from liposomes also indicated that approximately 20–25% of calcein release from liposomes occurs in buffer pH 7.4.

Component	Formulation			
	Lipo-Blank	Lipo-PQ	Lipo-CQ	Lipo-PQCQ
PQ	–	1.00	–	1.66
CQ	–	–	3.33 mg	1.66 mg
HSPC	1.4 mg	5.94 mg	5.94 mg	5.94 mg
DSPE-mPEG ₂₀₀₀	1.94 mg	1.94 mg	1.94 mg	1.94 mg
Cholesterol	2.13 mg	2.13 mg	2.13 mg	2.13 mg

Table 3. Formulation of blank and drug-loaded liposomes. PQ primaquine, CQ chloroquine, HSPC hydrogenated soybean phosphatidylcholine, DSPE-mPEG₂₀₀₀ distearoyl-*sn*-glycero-3-phosphoethanolamine-N-(methoxy[polyethylene glycol]-2000).

is lower than that the 40–50% released from the liposome in pH 4.0 over a period of 48 hours⁴⁸. However, due to the high intrinsic permeability of protons through the lipid bilayer, H³⁺ ions will permeate from the acidic intraliposomal phase to the exterior until a state of equilibrium is reached. This resulted in no further calcein release to that observed in the early phase^{49,50}. It has been reported³¹ that calcein release is limited by lipid packing order³¹ and drug interaction within the bilayer membrane⁵¹. The stronger the interaction between the drug and lipid, the less calcein will be desorbed leading to burst effects. In this study, the interaction between PQ, CQ, and liposomes was observed, resulting in burst release of calcein from liposomes.

Moreover, as confirmed by the NMR and FTIR spectra, interaction could occur between PQ, CQ, and liposomes resulting in similar calcein release profiles of Lipo-PQ and Lipo-PQCQ, although the use of CQ could rigidify the bilayer membrane^{16,52}. This may be attributable to the differences in chemical characteristics between calcein and PQ/CQ. Further²⁴ research evaluating the molecular interaction and changes in liposomes structure is required to confirm the results of this study. These findings will provide some insights into the design of liposomes for delivering the combination of PQ and CQ specifically for hepatic stage malaria.

Conclusions

As delivery of PQ in the early stages of sporozoite invasion of the liver largely determines the success of preventing blood stage malaria infection, a strategy combining PQ load with CQ, a blood schizontocide, in liposomes offers strong therapeutic efficacy as well as reduced drug toxicities. However, this study reveals that dual drug loading of PQ and CQ into PEGylated liposomes greatly affects liposomal membrane fluidity. Changes in the FTIR spectrum intensities and DTA profiles were indicative of those in the gauche conformation of the hydrocarbon chain of the phospholipid, and of increased calcein release from liposomes which indicate the fluidity of the bilayer membrane of the liposomes. These results suggest that further studies on designing a theoretical model for enhancing liposome stability, further by using optimizing liposome formulation or other strategies to reduce membrane fluidity, are imperative to support the development of strategies for the liposomal delivery of drugs targeting hepatic stage malaria.

Methods

Materials. Primaquine bisphosphate (PQ) was purchased from Sigma-Aldrich (Rehovot, Israel), while Chloroquine diphosphate (CQ) was obtained¹⁶ Sigma-Aldrich (Gyeonggi-do, South Korea). Hydrogenated soybean phosphatidylcholine (HSPC) and 1,2-distearoyl-*sn*-glycero-3-phosphoethanolamine-N-(methyl polyethyleneglycol)-2000 (DSPE-mPEG₂₀₀₀), with an average molecular weight of 2800, were procured from Nof Corporation⁵¹ (Tokyo, Japan). Cholesterol was obtained from Wako Inc., Ltd. (Osaka, Japan). Calcein was acquired from Nacalai Tesque Inc. (Kyoto, Japan). KH₂PO₄, Na₂HPO₄, chloroform, and methanol were purchased from Merck Inc. (Darmstadt, Germany). Sephadex® G-50 was obtained from Sigma-Aldrich (Steinheim, Germany). Other reagents and materials used were of the finest grade available.

Preparation of liposomes. The liposomes were prepared by means of thin-film hydration²⁶ using the formula listed in Table 3. All lipid components, including HSPC⁸, cholesterol, and DSPE-mPEG₂₀₀₀, were initially dissolved in chloroform before being homogeneously mixed in a round-bottom flask. The organic solvent was subsequently evaporated using a rotary evaporator to form a thin lipid layer which was then hydrated with citrate buffer (pH 5.0) and extruded to produce liposomes of 100 nm⁴³ size. The extrusion process consisted³² of passing through three membranes with various pore sizes; the first with a pore size of 400 nm, the second with a pore size of 200 nm and the third with a pore size of 100 nm. Each step involved passing liposomes³³ through a polycarbonate membrane in 30 repeated cycles by means of an extruder kit with a heating block (Avanti Mini-Extruder, Avanti Polar Lipid Inc., Alabama, USA) at 55–60 °C. Furthermore, each drug was consistently loaded using a pH gradient method. The liposomal outer phase was replaced by passing the liposomes through a Sephadex® G-50 column saturated with phosphate-buffered saline (PBS, pH 7.4). The mixture was then mixed with PQ and CQ solution and incubated² 20 min at 60 °C. This was followed by separation of the PQ- and CQ-loaded liposomes from the free drugs using a Sephadex® G-50 column (Sigma-Aldrich).

The molar ratio of HSPC:DSPE-mPEG₂₀₀₀:cholesterol was 59:5:36. Primaquine and chloroquine were added by considering the weight ratios of the drugs to the lipid components of the liposomes, which were 1:10 for primaquine:total lipid in primaquine-loaded liposomes (Lipo-PQ), 1:3 for chloroquine:total lipid in

chloroquine-loaded liposomes (Lipo-CQ), and 1:1:6 for primaquine:chloroquine:total lipid in liposomes loaded with primaquine and chloroquine (Lipo-PQCQ).

Termination of particle size and ζ -potential of liposomes. The preparation was evaluated for particle size and polydispersity index (PDI) via dynamic light scattering and ζ -potential was determined via electrophoresis light scattering using a Nano C Particle Analyzer at room temperature (25 °C). Approximately 100 μ l of liposomes were diluted with 3 ml of distilled water and then placed into a cuvette to determine the particle size, PDI, and ζ -potential.

Evaluation of encapsulation efficiency and drug loading capacity. After PQ, CQ, and their combination (PQCQ) had been loaded into liposomes, the mixtures were eluted through a Sephadex® G-50 column with PBS pH 7.4 to separate free drugs from their encapsulated counterparts. The samples were then lysed with methanol (50%, v/v), with PQ and CQ subsequently being determined by means of UV spectrophotometric method as previously reported²⁶.

The encapsulation efficiency (EE) and loading capacity (LC) were calculated using Eqs. (1) and (2) respectively^{26,38}:

$$EE(\%) = \frac{\text{Amount of drug encapsulated}}{\text{Amount of drug encapsulated} + \text{Amount of free drug}} \times 100, \quad (1)$$

$$LC(\%) = \frac{\text{Amount of drug encapsulated}}{\text{Total amount of drug} + \text{Total amount of liposomal components}} \times 100 \quad (2)$$

Spectroscopy and crystallography of the liposomes. Fourier transform infrared (FTIR) spectroscopy of liposomes. The FTIR profiles of liposomes were analyzed using an FTIR spectrophotometer Shimadzu, Kyoto, Japan). The freeze-dried liposomes were finely crushed and mixed with potassium bromide at a weight ratio of 1:100. The mixture was then pressed in a mechanical mold to form thin and translucent pellets, which were subsequently examined at wavenumbers of 4000–450 cm^{-1} . The results of the infrared spectra obtained for the samples were compared with the literature values.

Powder X-ray diffraction (P-XRD) analysis of liposomes. P-XRD analysis was performed using a PRD instrument (Phillips X'Pert PRO PANalytical, Netherlands). Freeze-dried liposomes were placed in a container and flattened. This process was performed under the following conditions: Cu metal anode, Ka filter, voltage of 40 kV, 30 mA, and 2θ of 5°–90°.

Differential thermal analysis (DTA) of liposomes. A DTA instrument (Mettler Toledo FP 85, Switzerland) was used to perform a DTA. The dried liposomes were placed in aluminum crucibles and subsequently heated from 30 to 300 °C at a rate of 5 °C/min.

Nuclear magnetic resonance (NMR) analysis of liposomes. The ¹H NMR spectra of blank liposomes (Lipo-Blank) and liposomes loaded with PQ (Lipo-PQ), CQ (Lipo-CQ), and both drugs (Lipo-PQCQ) were analyzed using JEOL 400 ECA spectrophotometer (JEOL, Tokyo, Japan) at 400 MHz³³. Approximately 5 mg of freeze-dried samples were dissolved in CDCl₃ to produce a concentration of 10 mg/ml with the data integration subsequently analyzed by computer using JEOL Delta v5.04.

Calcein release test as an indicator of membrane leakage. Preparation of calcein-loaded liposomes. The liposomes were composed of HSPC, cholesterol, and DSPE-mPEG₂₀₀₀ at a molar ratio of 55:40:5 using the thin-layer method. The lipid layer formed was then hydrated with a citrate buffer pH 5.0 containing 17 mM calcein followed by the extrusion process using a 100-nm polycarbonate membrane. At the next stage, the calcein-loaded liposomes were separated from free calcein by passing the liposomes through a Sephadex® G-50 column saturated with PBS. The eluted liposomes were mixed with PQ and CQ solution, followed by incubation at 60 °C for 20 min. Finally, to obtain liposomes loaded with calcein and PQ and/or CQ, the liposomes were passed through a Sephadex® G-50 column saturated with PBS.

Calcein release study. Calcein release was studied using the dialysis method²⁴. Liposomes containing equivalent amount of 2 mM calcein were inserted into the Spectra Por® 7 dialysis membrane with a MWCO of 3500 Da. PBS pH 7.4 was used as the release medium with an agitation speed of 400 rpm at 37 °C. Sampling was subsequently conducted after 0.5, 1, 2, 4, 8, 12, 24, and 48 h, with each sample replaced with the same volume of PBS pH 7.4, heated at 37 °C. The cumulative amount of calcein released from liposomes was determined using a GloMax® Multi + Detection System (Promega) in the fluorescence mode at $\lambda_{\text{ex}} = 490 \text{ nm}$ and $\lambda_{\text{em}} = 530 \text{ nm}$ ⁵⁴.

Because of medium dilution during the release test procedure, the quantified amount of calcein was corrected using the dilution factor contained in Eq. (3), as follows⁵⁵:

$$C_n = C'_{n-1} + \frac{a}{b} \sum_{i=1}^{n-1} C_s \quad (3)$$

Description: C_n : measured percent drug release at time point n after correction; C'_{n-1} : measured percent drug release at time point $n-1$ before correction; C_s : measured percent drug release at time point $n-1$; a : volume of the obtained sample (ml); b : volume of released medium (ml).

Statistical analysis. All data were obtained from three replicates and presented as the mean \pm SD. In addition, differences were further analyzed using one-way analysis of variance followed by the least significant difference test. Significance was indicated by $p < 0.05$.

Ethical conduct of research statement. This article does not contain any studies with human and animal subjects performed by any of the authors.

Received: 20 February 2021; Accepted: 2 June 2021

Published online: 14 June 2021

References

- Hill, D. R. *et al.* Primaquine: report from CDC expert meeting on malaria chemoprophylaxis I. *Am. J. Trop. Med. Hyg.* **75**, 402–415 (2006).
- Chu, C. S. & White, N. J. Management of relapsing *Plasmodium vivax* malaria. *Expert Rev. Anti Infect. Ther.* **14**, 885–900 (2016).
- Fernández-Busquets, X. Novel strategies for *Plasmodium*-targeted drug delivery. *Expert Opin. Drug Deliv.* **13**, 912–922 (2016).
- Burgoine, K. L., Bancone, G. & Nosten, F. The reality of using primaquine. *Malar. J.* **9**, 376 (2010).
- Marcisin, S. R., Reichard, G. & Pybus, B. S. Primaquine pharmacology in the context of CYP 2D6 pharmacogenomics: current state of the art. *Pharmacol. Ther.* **161**, 1–10 (2016).
- Fernando, D., Rodrigo, C. & Rajapakse, S. Primaquine in vivax malaria: an update and review on management issues. *Malar. J.* **10**, 351 (2011).
- Raphemot, R., Posfai, D. & Derbyshire, E. R. Current therapies and future possibilities for drug development against liver-stage malaria. *J. Clin. Investig.* **126**, 2013–2020 (2016).
- Sibley, C. H. & Price, R. N. Monitoring antimalarial drug resistance: applying lessons learned from the past in a fast-moving present. *Int. J. Parasitol. Drugs Drug Resist.* **2**, 126–133 (2012).
- Browning, D. J. Pharmacology of chloroquine and hydroxychloroquine. In *Hydroxychloroquine and Chloroquine Retinopathy* (ed. Browning, D. J.) 35–63 (Springer, 2014). <https://doi.org/10.1007/978-1-4939-0597-3>.
- Fasinu, P. S. *et al.* Pathway-specific inhibition of primaquine metabolism by chloroquine/quinine. *Malar. J.* **15**, 466 (2016).
- Pukrittayakamee, S. *et al.* Pharmacokinetic interactions between primaquine and chloroquine. *Antimicrob. Agents Chemother.* **58**, 3354–3359 (2014).
- Egan, T. J. & Kaschula, C. H. Strategies to reverse drug resistance in malaria. *Curr. Opin. Infect. Dis.* **20**, 598–604 (2007).
- Omwoyo, W. N. *et al.* Preparation, characterization, and optimization of primaquine-loaded solid lipid nanoparticles. *J. Nanomed.* **9**, 3865–3874 (2014).
- Basso, L. G. M., Rodrigues, R. Z., Naal, R. M. Z. G. & Costa-Filho, A. J. Effects of the antimalarial drug primaquine on the dynamic structure of lipid model membranes. *Biochim. Biophys. Acta Biomembr.* **1808**, 55–64 (2011).
- Barroso, R. P., Basso, L. G. M. & Costa-Filho, A. J. Interactions of the antimalarial amodiaquine with lipid model membranes. *Chem. Phys. Lipids* **186**, 68–78 (2015).
- Ghosh, A. K., Basu, R. & Nandy, P. Lipid perturbation of liposomal membrane of dipalmitoyl phosphatidylcholine by chloroquine sulphate—a fluorescence anisotropic study. *Colloids Surf. B Biointerfaces* **4**, 1–4 (1995).
- Ferrari, V. & Cutler, D. J. The pH-dependence of chloroquine uptake by phosphatidylcholine vesicles. *J. Pharm. Pharmacol.* **38**, 761–763 (1986).
- Eldin, N. E. *et al.* Encapsulation in a rapid-release liposomal formulation enhances the anti-tumor efficacy of pemetrexed in a murine solid mesothelioma-xenograft model. *Eur. J. Pharm. Sci.* **81**, 60–66 (2016).
- Eldin, N. E., Elnahas, H. M., Mahdy, M. A.-E. & Ishida, T. Liposomal pemetrexed: formulation, characterization and in vitro cytotoxicity studies for effective management of malignant pleural mesothelioma. *Biol. Pharm. Bull.* **38**, 461–469 (2015).
- Gürsoy, A., Kut, E. & Özkirimli, S. Co-encapsulation of isoniazid and rifampicin in liposomes and characterization of liposomes by derivative spectroscopy. *Int. J. Pharm.* **271**, 115–123 (2004).
- Kulkarni, S. B., Betageri, G. V. & Singh, M. Factors affecting microencapsulation of drugs in liposomes. *J. Microencapsul.* **12**, 229–246 (1995).
- Takechi-Haraya, Y., Sakai-Kato, K. & Goda, Y. Membrane rigidity determined by atomic force microscopy is a parameter of the permeability of liposomal membranes to the hydrophilic compound calcein. *AAPS PharmSciTech* **18**, 1887–1893 (2017).
- Gubernator, J. Active methods of drug loading into liposomes: recent strategies for stable drug entrapment and increased in vivo activity. *Expert Opin. Drug Deliv.* **8**, 565–580 (2011).
- Miatmoko, A., Kawano, K., Yoda, H., Yonemochi, E. & Hattori, Y. Tumor delivery of liposomal doxorubicin prepared with poly-L-glutamic acid as a drug-trapping agent. *J. Liposome Res.* **27**, 99–107 (2017).
- Ashley, J. D. *et al.* Dual carfilzomib and doxorubicin-loaded liposomal nanoparticles for synergistic efficacy in multiple myeloma. *Mol. Cancer Ther.* **15**, 1452–1460 (2016).
- Miatmoko, A. *et al.* Dual loading of primaquine and chloroquine into liposome. *Eur. Pharm. J.* **66**, 18–25 (2019).
- Ingebrigtsen, S. G., Nata, Ş., Albuquerque, C. D., Jacobsen, C. & Holsæter, A. M. Successful co-encapsulation of benzoyl peroxide and chloramphenicol in liposomes by a novel manufacturing method—dual asymmetric centrifugation. *Eur. J. Pharm. Sci.* **97**, 192–199 (2017).
- Shimanouchi, T., Ishii, H., Yoshimoto, N., Umakoshi, H. & Kuboi, R. Calcein permeation across phosphatidylcholine bilayer membrane: effects of membrane fluidity, liposome size, and immobilization. *Colloids Surf. B Biointerfaces* **73**, 156–160 (2009).
- Chen, J. *et al.* Influence of lipid composition on the phase transition temperature of liposomes composed of both DPPC and HSPC. *Drug Dev. Ind. Pharm.* **39**, 197–204 (2013).
- Hatzi, P., Mourtas, S., Klepetsanis, P. G. & Antimisiaris, S. G. Integrity of liposomes in presence of cyclodextrins: effect of liposome type and lipid composition. *Int. J. Pharm.* **333**, 167–176 (2007).

31. Maherani, B., Arab-Tehrany, E., Kheirloom, A., Geny, D. & Linder, M. Calcein release behavior from liposomal bilayer; influence of physicochemical/mechanical/structural properties of lipids. *Biochimie* **95**, 2018–2033 (2013).
32. Cabral, E. C. M., Zollner, R. L. & Santana, M. H. A. Preparation and characterization of liposomes entrapping allergenic proteins. *Braz. J. Chem. Eng.* **21**, 137–146 (2004).
33. Li, H., Zhao, T. & Sun, Z. Analytical techniques and methods for study of drug–lipid membrane interactions. *Rev. Anal. Chem.* **37**, 1–23 (2017).
34. Gonzalez-Ceron, L. *et al.* Effectiveness of combined chloroquine and primaquine treatment in 14 days versus intermittent single dose regimen, in an open, non-randomized, clinical trial, to eliminate *Plasmodium vivax* in southern Mexico. *Malar. J.* **14**, 436 (2015).
35. World Health Organization. *Guidelines for the Treatment of Malaria. Guidelines for the Treatment of Malaria* (WHO Press, 2015). [https://doi.org/10.1016/0035-9203\(91\)90261-V](https://doi.org/10.1016/0035-9203(91)90261-V).
36. Baird, J. K. *et al.* Short report: therapeutic efficacy of chloroquine combined with primaquine against *Plasmodium falciparum* in northeastern Papua, Indonesia. *Am. J. Trop. Med. Hyg.* **66**, 659–660 (2002).
37. Stensrud, G., Sande, S. A., Kristensen, S. & Smistad, G. Formulation and characterisation of primaquine loaded liposomes prepared by a pH gradient using experimental design. *Int. J. Pharm.* **198**, 213–228 (2000).
38. Qiu, L., Jing, N. & Jin, Y. Preparation and in vitro evaluation of liposomal chloroquine diphosphate loaded by a transmembrane pH-gradient method. *Int. J. Pharm.* **361**, 56–63 (2008).
39. Nair, A. *et al.* Biowaiver monographs for immediate-release solid oral dosage forms: primaquine phosphate. *J. Pharm. Sci.* **101**, 936–945 (2012).
40. Verbeeck, R. K., Junginger, H. E., Midha, K. K., Shah, V. P. & Barends, D. M. Biowaiver monographs for immediate release solid oral dosage forms based on biopharmaceutics classification system (BCS) literature data: chloroquine phosphate, chloroquine sulfate, and chloroquine hydrochloride. *J. Pharm. Sci.* **94**, 1389–1395 (2005).
41. Pawlikowska-Pawlega, B. *et al.* Characteristics of quercetin interactions with liposomal and vacuolar membranes. *Biochim. Biophys. Acta* **1838**, 254–265 (2014).
42. Cieřlik-Boczula, K. *et al.* Interaction of quercetin, genistein and its derivatives with lipid bilayers—an ATR IR-spectroscopic study. *Vib. Spectrosc.* **62**, 64–69 (2012).
43. Ezer, N., Sahin, I. & Kazanci, N. Alliin interacts with DMPC model membranes to modify the membrane dynamics: FTIR and DSC studies. *Vib. Spectrosc.* **89**, 1–8 (2017).
44. Blanco, A. & Blanco, G. Chapter 5—lipids. In *Medical Biochemistry* (eds Blanco, A. & Blanco, G.) 99–119 (Academic Press, 2017). <https://doi.org/10.1016/B978-0-12-803550-4.00005-7>.
45. Yokota, D., Moraes, M. & Pinho, S. C. Characterization of lyophilized liposomes produced with non-purified soy lecithin: a case study of casein hydrolysate microencapsulation. *Braz. J. Chem. Eng.* **29**, 325–335 (2012).
46. Yusuf, H., Nugraheni, R. W., Setyawan, D. & Rosita, N. Phase behavior of dried—DDA liposomal formulation dispersed in HPMC Matrix in the presence of saccharides. *Int. J. PharmTech Res.* **10**, 50–56 (2017).
47. Parmentier, J., Becker, M. M. M., Heintz, U. & Fricker, G. Stability of liposomes containing bio-enhancers and tetraether lipids in simulated gastro-intestinal fluids. *Int. J. Pharm.* **405**, 210–217 (2011).
48. Han, S.-M. *et al.* Improvement of cellular uptake of hydrophilic molecule, calcein, formulated by liposome. *J. Pharm. Investig.* **48**, 595–601 (2018).
49. Cullis, P. R., Bally, M. B., Madden, T. D., Mayer, L. D. & Hope, M. J. pH gradients and membrane transport in liposomal systems. *Trends Biotechnol.* **9**, 268–272 (1991).
50. Lasic, D. D., Ceh, B., Guo, L., Frederik, P. M. & Barenholz, Y. Transmembrane gradient driven phase transitions within vesicles: lessons for drug delivery. *Biochim. Biophys. Acta* **1239**, 145–156 (1995).
51. Calvagno, M. G. *et al.* Effects of lipid composition and preparation conditions on physical-chemical properties, technological parameters and in vitro biological activity of gemcitabine-loaded liposomes. *Curr. Drug Deliv.* **4**, 89–101 (2007).
52. Zidovetski, R., Sherman, I., Cardenas, M. & Borcard, D. B. Chloroquine stabilization of phospholipid membranes against dialcylglycerol-induced perturbation. *Biochem. Pharmacol.* **45**, 183–189 (1993).
53. Tjahjandarie, T. S., Saputri, R. D., Hasanah, U., Rachmadiarti, F. & Tanjung, M. 5,7-Dihydroxy-3,6-dimethoxy-3',4'-methylendioxyflavon. *Molbank* **M1007**, 1–4 (2018).
54. Chen, Y. *et al.* A low-molecular-weight heparin-coated doxorubicin-liposome for the prevention of melanoma metastasis. *J. Drug Target.* **23**, 335–346 (2015).
55. Aronson, H. Correction factor for dissolution profile calculations. *J. Pharm. Sc.* **82**, 3549 (1993).

Acknowledgements

The authors are grateful to Dr. Harsasi Setyawati at Faculty of Science and Technology, Airlangga University for her insightful comments and suggestions for spectroscopy analysis.

Author contributions

A.M.: (1) conception and design of the work, data acquisition, data analysis and interpretation; (2) critically revising the article for important intellectual content; (3) Final approval of the version to be published; (4) Agreement to be accountable for all aspects of the work in ensuring that questions related to the accuracy or integrity of the work are appropriately investigated and resolved. I.N.: (1) data acquisition; (2) Drafting the article; (3) Final approval of the version to be published; (4) Agreement to be accountable for all aspects of the work in ensuring that questions related to the accuracy or integrity of the work are appropriately investigated and resolved. N.F.N.: (1) data acquisition; (2) Final approval of the version to be published; (3) Agreement to be accountable for all aspects of the work in ensuring that questions related to the accuracy or integrity of the work are appropriately investigated and resolved. N.R.: (1) data analysis and interpretation; (2) critically revising the article for important intellectual content; (3) Final approval of the version to be published; (3) Agreement to be accountable for all aspects of the work in ensuring that questions related to the accuracy or integrity of the work are appropriately investigated and resolved. E.H.: (1) data analysis and interpretation; (2) Final approval of the version to be published; (3) Agreement to be accountable for all aspects of the work in ensuring that questions related to the accuracy or integrity of the work are appropriately investigated and resolved. R.S.: (1) data analysis and interpretation; (2) Final approval of the version to be published; (3) Agreement to be accountable for all aspects of the work in ensuring that questions related to the accuracy or integrity of the work are appropriately investigated and resolved. J.E.: (1) data analysis and interpretation; (2) Final approval of the version to be published; (3) Agreement to be accountable for all aspects of the work in ensuring that questions related to the accuracy or integrity of the work are appropriately investigated and resolved.

Funding

This study was supported by a Preliminary Research on Excellence in Higher Education Institutions (Penelitian Dasar Unggulan Perguruan Tinggi, PDUPT) Grant No.6/E/KPT/2019 provided by the Ministry of Research, Science, and Technology, Republic of Indonesia.

Competing interests

The authors declare no competing interests.

Additional information

Supplementary Information The online version contains supplementary material available at <https://doi.org/10.1038/s41598-021-91866-0>.

Correspondence and requests for materials should be addressed to A.M.

Reprints and permissions information is available at www.nature.com/reprints.

Publisher's note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2021

Interactions of primaquine and chloroquine with PEGylated phosphatidylcholine liposomes

ORIGINALITY REPORT

12%

SIMILARITY INDEX

7%

INTERNET SOURCES

11%

PUBLICATIONS

0%

STUDENT PAPERS

PRIMARY SOURCES

- 1** A. Miatmoko, H. R. Salim, S. M. Zahro, F. Annuryanti, R. Sari, E. Hendradi. "Dual Loading Of Primaquine And Chloroquine Into Liposome", European Pharmaceutical Journal, 2019
Publication 2%
- 2** www.tandfonline.com
Internet Source 1%
- 3** Raditya Weka Nugraheni, Dwi Setyawan, Helmy Yusuf. "Physical Characteristics of Liposomal Formulation Dispersed in HPMC Matrix and Freeze-Dried Using Maltodextrin and Mannitol as Lyoprotectant", Pharmaceutical Sciences, 2017
Publication 1%
- 4** content.sciendo.com
Internet Source 1%
- 5** www.thno.org
Internet Source <1%

6

uknowledge.uky.edu

Internet Source

<1 %

7

stella.repo.nii.ac.jp

Internet Source

<1 %

8

Jun Chen, Dong Cheng, Jun Li, Yong Wang, Jian-xin Guo, Zhi-peng Chen, Bao-chang Cai, Tao Yang. "Influence of lipid composition on the phase transition temperature of liposomes composed of both DPPC and HSPC", Drug Development and Industrial Pharmacy, 2012

Publication

<1 %

9

Kamal Dua, Kavita Pabreja, Malipeddi Ramana. "Aceclofenac topical dosage forms: In vitro and in vivo characterization", Acta Pharmaceutica, 2010

Publication

<1 %

10

hal.univ-lorraine.fr

Internet Source

<1 %

11

Liu, Mei, Wei Li, Caroline A. Larregieu, Meng Cheng, Bihan Yan, Ting Chu, Hui Li, and Sheng-jun Mao. "Development of Synthetic Peptide-Modified Liposomes with LDL Receptor Targeting Capacity and Improved Anticancer Activity", Molecular Pharmaceutics, 2014.

Publication

<1 %

12 M.A. Awwal, M.F.R. Guzella, T.V. Silva. <1 %
"Chemical treatment of simulated solution of
evaporator concentrate for immobilization in
bitumen", Waste Management, 1996
Publication

13 Kenji Okano, Yasuhisa Yamamoto, Hiroyuki
Takano, Tsuyoshi Aketo, Kohsuke Honda,
Hisao Ohtake. "A simple technology for
phosphorus recovery using acid-treated
concrete sludge", Separation and Purification
Technology, 2016 <1 %
Publication

14 Sharad Visht, Rajendra Awasthi, Ravi Rai,
Pradhi Srivastav. "Development of
Dehydration-Rehydration Liposomal System
Using Film Hydration Technique Followed by
Sonication", Current Drug Delivery, 2014 <1 %
Publication

15 digitalcommons.usu.edu <1 %
Internet Source

16 www.faqs.org <1 %
Internet Source

17 pubs.rsc.org <1 %
Internet Source

18 export.arxiv.org <1 %
Internet Source

19

www.mdpi.com

Internet Source

<1 %

20

Camila Morais Gonçalves da Silva, Leonardo Fernandes Fraceto, Michelle Franz-Montan, Verônica Muniz Couto et al. " Development of egg PC/cholesterol/ -tocopherol liposomes with ionic gradients to deliver ropivacaine ", Journal of Liposome Research, 2015

Publication

<1 %

21

Epstein, H.. "Number-concentration of nanoparticles in liposomal and polymeric multiparticulate preparations: Empirical and calculation methods", Biomaterials, 200602

Publication

<1 %

22

patents.google.com

Internet Source

<1 %

23

DalSpace.library.dal.ca

Internet Source

<1 %

24

Mariane C. B. Lira, Marigilson P. Siqueira-Moura, Hercília M. L. Rolim-Santos, Fábio C. S. Galetti et al. " uptake and antimycobacterial activity of liposomal usnic acid formulation ", Journal of Liposome Research, 2009

Publication

<1 %

25

Sakai-Kato, Kumiko, Kunie Nanjo, Toru Kawanishi, Haruhiro Okuda, and Yukihiro Goda. "Effects of lipid composition on the

<1 %

properties of doxorubicin-loaded liposomes",
Therapeutic Delivery, 2015.

Publication

26

Stensrud, G.. "Formulation and characterisation of primaquine loaded liposomes prepared by a pH gradient using experimental design", International Journal of Pharmaceutics, 20000405

Publication

27

repositorio-aberto.up.pt

Internet Source

28

www.freepatentsonline.com

Internet Source

29

www.science.gov

Internet Source

30

"Abstracts for 6th Central European Symposium on Pharmaceutical Technology and Biotechnology", European Journal of Pharmaceutical Sciences, 200505

Publication

31

Advances in Delivery Science and Technology, 2015.

Publication

32

Advances in Experimental Medicine and Biology, 2014.

Publication

<1 %

<1 %

<1 %

<1 %

<1 %

<1 %

<1 %

33

Duehrkop, Claudia, Gero Leneweit, Christoph Heyder, Karin Fromell, Katarina Edwards, Kristina N. Ekdahl, and Bo Nilsson.

"Development and characterization of an innovative heparin coating to stabilize and protect liposomes against adverse immune reactions", Colloids and Surfaces B Biointerfaces, 2016.

Publication

<1 %

34

Hsiao-Wen Huang, Edward M. Goldberg, Raphael Zidovetzki. "Ceramide Modulate Protein Kinase C Activity and Perturb the Structure of Phosphatidylcholine/Phosphatidylserine Bilayers", Biophysical Journal, 1999

Publication

<1 %

35

Ling Chen, Rong Liang, Yihan Wang, Wallace Yokoyama, Maoshen Chen, Fang Zhong. "Characterizations on the Stability and Release Properties of β -ionone Loaded Thermosensitive Liposomes (TSLs)", Journal of Agricultural and Food Chemistry, 2018

Publication

<1 %

36

Nabil El Kateb, Luc Cynober, Jean Claude Chaumeil, Gilles Dumortier. "L-cysteine encapsulation in liposomes: Effect of phospholipids nature on entrapment

<1 %

efficiency and stability", Journal of
Microencapsulation, 2008

Publication

37

V. Saroglou. "Synthesis, liposomal formulation and thermal effects on phospholipid bilayers of leuprolide", Journal of Peptide Science, 01/2006

Publication

<1 %

38

Wenli Zhang, Guangji Wang, James R. Falconer, Bruce C. Baguley et al. "Strategies to Maximize Liposomal Drug Loading for a Poorly Water-soluble Anticancer Drug", Pharmaceutical Research, 2014

Publication

<1 %

39

discovery.dundee.ac.uk

Internet Source

<1 %

40

docs.com

Internet Source

<1 %

41

ijpsr.com

Internet Source

<1 %

42

link.springer.com

Internet Source

<1 %

43

repositorium.sdum.uminho.pt

Internet Source

<1 %

44

scholar.ufs.ac.za

Internet Source

<1 %

45

test.dovepress.com

Internet Source

<1 %

46

www.yumpu.com

Internet Source

<1 %

47

zone.biblio.laurentian.ca

Internet Source

<1 %

48

Bligh, E. G., and W. J. Dyer. "A RAPID METHOD OF TOTAL LIPID EXTRACTION AND PURIFICATION", *Canadian Journal of Biochemistry and Physiology*, 1959.

Publication

<1 %

49

Robert J Commons, Julie A Simpson, Kamala Thriemer, Georgina S Humphreys et al. "The effect of chloroquine dose and primaquine on Plasmodium vivax recurrence: a WorldWide Antimalarial Resistance Network systematic review and individual patient pooled meta-analysis", *The Lancet Infectious Diseases*, 2018

Publication

<1 %

50

Yang, Mimi M., William R. Wilson, and Zimei Wu. "pH-Sensitive PEGylated liposomes for delivery of an acidic dinitrobenzamide mustard prodrug: Pathways of internalization, cellular trafficking and cytotoxicity to cancer cells", *International Journal of Pharmaceutics*, 2017.

<1 %

51

Yuki Takechi-Haraya, Masaki Matsuoka, Hirotaka Imai, Kenichi Izuts, Kumiko Sakai-Kato. "Detection of material-derived differences in the stiffness of egg yolk phosphatidylcholine-containing liposomes using atomic force microscopy", Chemistry and Physics of Lipids, 2020

<1 %

Publication

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

Interactions of primaquine and chloroquine with PEGylated phosphatidylcholine liposomes

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7

PAGE 8

PAGE 9

PAGE 10

PAGE 11

PAGE 12
