



devi rianti &lt;devi-r@fkg.unair.ac.id&gt;

---

**Resubmission of submitted manuscript after minor correction.**

1 message

---

**Anvpublications@anvpublication.org** <Anvpublications@anvpublication.org>

Sat, Jun 5, 2021 at 12:42 PM

To: "devi-r@fkg.unair.ac.id; kristantowahyudi76@gmail.com; herlinadamayanti49@gmail.com; tansza.permata@fkg.unair.ac.id; aristikadinar@gmail.com; ardiyans@gmail.com;" &lt;anita-y@fkg.unair.ac.id&gt;, devi-r@fkg.unair.ac.id

**Research Journal of Pharmacy and Technology**Paper ID: **21528200227883833** Date of Submission: **28-May-2021**Paper Title: **The characteristics and potency of limestone-based carbonate hydroxyapatite to viability and proliferation of human umbilical cord mesenchymal stem cell**Authors: **Devi Rianti; Wahyudi Kristanto; Herlina Damayanti; Tansza Setiana Putri; Aristika Dinaryanti; Ardiyansyah Syahrom; Anita Yuliaty**

Dear Author(s),

Thanks for submission of paper at enlisted journals of 'A & V Publications'. In the manuscript, it is compulsory to cite references of the related articles from journals of A&V Publications. Therefore, we are requested you to kindly cite / refers at least ten published manuscript from the enlisted journals. The link of published articles is embedded at the bottom of this mail, which you would to click and select any ten manuscripts as applicable to the submitted manuscript.

After citing the related articles, please resubmit the revised manuscript at article submission portal within 7 days.

[Click here to view the simalar works as yours.](#)

Please Login to account from which you have submitted the article, for more details. ([Click Here to Login Now.](#) )

Thanks for your kind submission of manuscript.

**Editor****This is auto generated mail. Please do not reply.**



**Gmail**

Compose

Mail

99+

Inbox 16,437

Starred

Snoozed

Important

Sent

Drafts 51

Categories

More

Labels

- Follow up
- Misc
- Priority

Search: rjpt

2 of 7

Wed, Aug 10, 2022, 2:35 PM

**devirianti** <devi-r@fkg.unair.ac.id>  
to editor.rjpt

Dear Editor In Chief of **RJPT**,

I hope this email finds you well.

My name is Devi Rianti, the author of a published paper in your journal entitled 'The Characteristics and Potency of Limestone-based carbonate hydroxyapatite to Viability and Proliferation of Human Umbilical Cord Mesenchymal Stem Cell' with below details:

- Tmp PID : 21528200227883833
- Pub. Paper ID : 2022-15-5-62
- DOS : 28-05-2021
- DOP : 27-07-2022
- Volume : 15
- Issue : 5

I want to see the final pdf but I could not access the PDF through the An V publication account. when I download in the published article section, it stated: something went wrong. Can you send me the pdf paper version through email as I need it to show it to my university as a proof that I have published my article in your journal? Thank you so much for your understanding

Sincerely yours,

Devi Rianti



**Research Journal of Pharmacy and Technology Monika Daharwal** <editor.rjpt@gmail.com>

Aug 10, 2022, 6:28 PM



to me ▾

Pl find attachement

\*\*\*

--

Editor,

Research Journal of Pharmacy and Technology,

**RJPT** House, Lokmanya Grih Nirman Society,

Rohanipuram, In-front of Sector- 1,

Pt. Deendayal Upadhyay Nagar,

Raipur 492 010. (CG) India.

Phone No. +919406051618

[www.ajrconline.org](http://www.ajrconline.org)

[www.anvpublication.org](http://www.anvpublication.org)

[www.rjptonline.org](http://www.rjptonline.org)

[www.asianpharmaonline.org](http://www.asianpharmaonline.org) <<http://www.asianpharmapress.org>>

Show All





6 of 7 < >

## Manuscript progress query External Inbox x



**devi rianti** <devi-r@fkg.unair.ac.id>  
to editor.rjpt

Aug 13, 2021, 4:31 AM ☆ ↶ ⋮

Dear Editor in chief of Research Journal of Pharmacy and Technology

On behalf of the authors, I would like to ask regarding our submitted manuscript entitled "The characteristics and potency of limestone-based carbonate hydroxyapatite to viability and proliferation of human umbilical cord mesenchymal stem cell" with Paper ID: 21528200227883833

I have resubmitted the revised journal as the answer of editorial board comment "In order to improve the quality of the paper you just go through the below link and cite atleast 10 articles from the list, that have similar works as of yours. The link is...".

But after the resubmission, the paper progress still under editorial review since 9 June 2021.

Is there other problem regarding the revised manuscript that need further editorial revision?

Thank you very much for your kind understanding. Looking forward to your reply.

Sincerely,

Devi Rianti



6 of 7 < >



**Research Journal of Pharmacy and Technology Monika Daharwal** <editor.rjpt@gmail.com>

Aug 13, 2021, 3:17 PM



to me ▾

Dear Author,  
Your article has been Sent to Reviewers. Comments still awaited.  
thanks  
editor.

\*\*\*

---

Editor,  
Research Journal of Pharmacy and Technology,  
**RJPT** House, Lokmanya Grih Nirman Society,  
Rohanipuram, In-front of Sector- 1,  
Pt. Deendayal Upadhyay Nagar,  
Raipur 492 010. (CG) India.  
Phone No. +919406051618

[www.ajronline.org](http://www.ajronline.org)

[www.anvpublication.org](http://www.anvpublication.org)

[www.rjptonline.org](http://www.rjptonline.org)

[www.asianpharmaonline.org](http://www.asianpharmaonline.org) <<http://www.asianpharmapress.org>>

**Gmail**

Compose

Mail

- Inbox 16,437
- Starred
- Snoozed
- Important
- Sent
- Drafts 51
- Categories
  - More
- Labels
  - Follow up
  - Misc
  - Priority

Search: rjpt

Active

SMART

5 of 7

**Dear Author,**  
**Regards**

The submitted manuscript is ready for publication in Research Journal of Pharmacy and Technology **(RJPT) Vol. 15 Issue 5, May 2022.**

The gallery proof of the paper is attaching herewith for any necessary correction if required, please convey by E. Mail as in the attached format before **May 26, 2022.**

Thanking you,

Yours truly,

Editor

Gallery Proof of published article in **RJPT\_15\_5\_2022**

...

**2 Attachments** • Scanned by Gmail

----- Forwarded message -----

From: <[pt@uthm.edu.my](mailto:pt@uthm.edu.my)>

Date: Tue, 14 Sept 2021 at 13:45

Subject: [ijie] Editor Decision

To: Anita Yuliaty <[anitayuli651@gmail.com](mailto:anitayuli651@gmail.com)>, Devi Rianti <[devirianti@gmail.com](mailto:devirianti@gmail.com)>, Geo Fanny <[geofanny@gmail.com](mailto:geofanny@gmail.com)>, Rania Vivian Nathania <[raniavivian@gmail.com](mailto:raniavivian@gmail.com)>, Alqomariyah Eka Purnamasari <[ekapurnamasari@gmail.com](mailto:ekapurnamasari@gmail.com)>, Rifayinqa Ruyani Putri <[rifayinqa@gmail.com](mailto:rifayinqa@gmail.com)>, Helal Soekartono <[helal@gmail.com](mailto:helal@gmail.com)>, Soebagio Soebagio <[soebagio43@gmail.com](mailto:soebagio43@gmail.com)>, Ardiyansyah Syahrom <[ardiyans@gmail.com](mailto:ardiyans@gmail.com)>

Anita Yuliaty, Devi Rianti, Geo Fanny, Rania Vivian Nathania, Alqomariyah Eka Purnamasari, Rifayinqa Ruyani Putri, Helal Soekartono, Soebagio Soebagio, Ardiyansyah Syahrom:

We have reached a decision regarding your submission to International Journal of Integrated Engineering, "The The characteristics, swelling ratio and water content percentage of chitosan-gelatin/limestone-based carbonate hydroxyapatite composite scaffold: chitosan-gelatin/limestone-based carbonate hydroxyapatite composite scaffold".

Our decision is to: Accept Submission subject to revision required as in the reviewer report.

Prof. Madya Ir. Dr. Rubita binti Sudirman

[rubita@utm.my](mailto:rubita@utm.my)



Date: March 30, 2022

**Research Journal of Pharmacy and Technology**

Paper ID:21528200227883833

Author's Name:Devi Kianti, Wahyudi Kristanto, Herlina Damayanti, Tansza Setiana Putri, Aristika Dinaryanti, Ardiyansyah Syahrom, Anita Yuliati

Paper Title: The characteristics and potency of limestone-based carbonate hydroxyapatite to viability and proliferation of human umbilical cord mesenchymal stem cell



**Acceptance of Manuscript**

With reference to your article titled 'The characteristics and potency of limestone-based carbonate hydroxyapatite to viability and proliferation of human umbilical cord mesenchymal stem cell' Author by Devi Rianti, Wahyudi Kristanto, Herlina Damayanti, Tansza Setiana Putri, Aristika Dinaryanti, Ardiyansyah Syahrom, Anita Yuliati. We wish to bring to your kind notice the following:

- We acknowledge the receipt of the above mentioned article.
- The above mentioned article has been sent to the reviewer of expert comments.
- The above mentioned article have been accepted for publication in Year : 2022, Vol: 15, Issue: 6 of the journal.

Thanking you for submission of manuscript

Yours sincerely,



**Editor in Chief**

**Note:**

1. To verify the originality of this e-article please visit the following link:

[http://www.aandvpub.com/org/Doc/initial\\_Acceptance.aspx?ID=21528200227883833](http://www.aandvpub.com/org/Doc/initial_Acceptance.aspx?ID=21528200227883833)



**RESEARCH ARTICLE**

**The Characteristics and Potency of Limestone-based carbonate hydroxyapatite to Viability and Proliferation of Human Umbilical Cord Mesenchymal Stem Cell**

**Devi Rianti<sup>1</sup>, Wahyudi Kristanto<sup>2</sup>, Herlina Damayanti<sup>2</sup>, Tansza S. Putri<sup>1</sup>, Aristika Dinaryanti<sup>3</sup>, Ardiyansyah Syahrom<sup>4\*</sup>, Anita Yuliati<sup>1\*</sup>**

<sup>1</sup>Department of Dental Material, Faculty of Dental Medicine, Airlangga University, Jl. Mayjen. Prof. Dr. Moestopo No. 47, Surabaya 60132, Indonesia

<sup>2</sup>Balai Besar Keramik Indonesia, Jl Jend. Ahmad Yani No 392, Bandung 40272, Indonesia

<sup>3</sup>Stem Cell Research and Development Center, Institute of Tropical Disease - Airlangga University Gd. Lembaga Penyakit Tropis Lt.1, Kampus C Universitas Airlangga Jln. Mulyorejo Surabaya 60115, Indonesia.

<sup>4</sup>Medical Devices and Technology Centre (MEDITEC), Institute of Human Centered and Engineering (iHumEn), Universiti Teknologi, Malaysia, 81310 UTM Skudai, Johor, Malaysia

\*Corresponding Author E-mail: [anita-y@fkg.unair.ac.id](mailto:anita-y@fkg.unair.ac.id), [ardiyans@gmail.com](mailto:ardiyans@gmail.com)

**ABSTRACT:**

**Background:** Limestone primarily consists of CaCO<sub>3</sub> (calcium carbonate), which have a similarity to one of human bone component, hydroxyapatite (HA), an element of apatite group (Ca<sub>10</sub>(PO<sub>4</sub>)<sub>6</sub>(OH)<sub>2</sub>). There were several setbacks in the use of artificial hydroxyapatite in the bone repair process; one of them was its relatively higher crystallinity level compared to those of human bone apatite. The addition of carbonate element to hydroxyapatite could improve its characteristics, such as increasing the solubility, decreasing the crystallinity, and changing the morphology of the crystal. That caused carbonate hydroxyapatite is preferable to help in the bone repair process. **Aims:** This study aimed to find the effect of limestone-based CHA on viability and proliferation of hUMSCs, thus discovering the potential of CHA as a bone graft biomaterial candidate derived from limestone. **Methods:** This study used FTIR, EDX, and XRD assays to CHA powder sample derived from limestone found in Padalarang and Cirebon extracted by BBK. Two grams of the sample were placed in the sample holder and examined by computer software. EDX assay was conducted three times in three different points, and the means were recorded. In the XRD assay, a carbon tip was put to the sample holder to allow sample attachment. The recorded data was compared to JCPDS data. Toxicity and proliferation examination of CHA were conducted through MTT assay in human umbilical cord mesenchymal stem cell (hUCMSC) cell lines with four different doses: 50µg/ml, 25µg/ml, 12.5µg/ml, and 6,25µg/ml. **Results:** Limestone-based CA has hydroxyl (OH<sup>-</sup>), phosphate (PO<sub>4</sub><sup>2-</sup>), and carbonate (CO<sub>3</sub><sup>2-</sup>) functional groups. It has crystal particle formation and consists of O, Ca, and P elements. The result of the MTT assay showed limestone-based CHA is not toxic in all concentrations and has the proliferative ability. There were significant differences between the control and treatment groups. **Conclusion:** CHA has OH<sup>-</sup>, PO<sub>4</sub><sup>2-</sup>, and CO<sub>3</sub><sup>2-</sup> function group. It has crystal particle formation and O, Ca, and P elements as its composition, with a Ca/P ratio of 1,67. It shows no toxicity to hUCMSC in all doses and has the ability to stimulate hUCMSC proliferation.

**KEYWORDS:** Carbonate Hydroxyapatite, Limestone, Medicine, Cytotoxicity, Mesenchymal Stem Cells.

**INTRODUCTION:**

Bone grafting technic is often used for periodontal defect, apicoectomy, osteogenesis distraction, and sinus lifting in dentistry<sup>1</sup>. Periodontal disease prevalence in all ages in Indonesia is 96,58%<sup>2,3</sup>. Based on WHO data in 2018, severe periodontal diseases resulting in bone

defect and tooth loss were found in 15-20% of middle age groups of 35-44 years old<sup>2</sup>. The demand for bone graft in the US amasses to more than 1.5 millions graft every year<sup>4</sup>, even doubled in 2020<sup>5,6</sup>. Autograft is a gold standard of the bone graft, but its availability is limited, thus to meet the high demand of bone graft, many researchers try to discover alternative material sources for the bone graft. Regenerative medicine has become a great advancement in medicine technology, especially in tissue and organ failure treatment<sup>7</sup>.

Several notable characteristics of bone graft are: having osteogenic, osteoinductive, and osteoconductive characteristics; able to stimulate neo-angiogenesis; showing no antigenic beam reaction, teratogenic and carcinogenic; having sufficient quantities for the supplies; showing good mechanical strength; having minimal morbidity risk; possessing hydrophilic characteristic; and easy to handle with a minimal budget<sup>8,9</sup>. It also needs to be non-toxic, stimulate cell attachment and proliferation<sup>10</sup>, have good solubility, and appropriate degradation corresponds to bone remodeling timeline<sup>10-12</sup>.

A recent study showed that hydroxyapatite (HA) could be extracted from limestone, which primarily consists of calcium carbonate ( $\text{CaCO}_3$ ), as an alternative material for human bone defect replacement in medicine.  $\text{CaCO}_3$  has a similarity to one of human bone component, hydroxyapatite (HA), an element of apatite group ( $\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$ )<sup>13</sup>.

Hydroxyapatite is widely used in medicine for artificial bone and to fill the osteoporosis bone. Despite its biocompatible, non-toxic, and osteoconductive characteristics, HA shows a limitation in the bone repair process as it has higher crystallinity than human bone apatite<sup>14,15</sup>. According to previous studies, the addition of carbonate elements to hydroxyapatite could improve its characteristics, such as increasing the solubility, decreasing the crystallinity, and changing the morphology of the crystal<sup>16</sup>.

Carbonate hydroxyapatite (CHA) is a nonstoichiometric version of HA<sup>17</sup>. Carbonate substitution on its crystal structure is known to weaken apatite structure and increase its solubility, resulting in CHA being more chemically similar to human bone.<sup>18</sup> Compared to HA, CHA has more distinct advantages in bone remodeling<sup>16</sup>. The chemical formula of CHA is  $\text{Ca}_{10}(\text{PO}_4\text{CO}_3)_6(\text{OH})_2$  with a Ca/P ratio of 1.6-2.0<sup>16</sup>.

Limestone-based CHA from Cirebon, West Java, extracted by Balai Besar Keramik (BBK) Indonesia, has a potential application as bio-ceramic material in the medical field for a bone substitute in bone defect

therapy. As a medical biomaterial candidate, it needs to pass several requirements, and one of the essential characteristics is the biocompatibility<sup>19,20</sup>.

Biocompatibility examination in this study was conducted through cytotoxicity assay to quantify cell viability and cell proliferation, using MTT assay. MTT assay is a sensitive, quantitative, and reliable coulometric assay to quantify cell viability, cell proliferation, and cell activity. MTT assay relies on mitochondrial dehydrogenase in the living cell, reducing the yellow-colored MTT to purple-colored formazan crystal. The number of cell formation was accounted through spectrophotometry to show the number of the living cell<sup>12</sup>.

The general procedure in tissue engineering uses the cell-based methodology approach, for example, by combining bioceramic scaffold with adult stem cell. Adult mesenchymal stem cells (MSC) can differentiate into various mesenchymal cell lineages, including cartilage and bone<sup>21</sup>. One of the sources of MSC is human umbilical cord mesenchymal stem cell (hUCMSC) originated from umbilical cord tissue<sup>22</sup>. The hUCMSC can be easily isolated and stored as it was a disposable tissue without any ethical issues<sup>22</sup>. It also can differentiate faster than BM-MSC<sup>13</sup>, which made hUCMSC more preferable for this study.

As carbonate apatite is a bioceramic with bone substitute/bone graft material potential in dentistry<sup>14</sup>, there is a necessity to identify its mechanical characteristics through FTIR, SEM, EDX, XRD, and biocompatibility characteristics, such as its cytotoxicity and proliferation ability in hUCMSC, before its clinical use in regenerative dentistry.

Thus, this study aimed to find the effect of limestone-based CHA on the viability and proliferation of hUMSCs, thus discovering the potential of CHA as a bone graft biomaterial candidate derived from limestone.

## MATERIALS AND METHODS:

### CHA synthesis:

The base material of HA was obtained from HA synthetization with the wet precipitation method. The carbonate source was obtained from  $\text{CaCO}_3$  (Cirebon, Jawa Barat, Indonesia) and  $\text{MgCO}_3$  (Brataco, Surabaya, Indonesia). Dry mechanosynthesis was done in single HA, HA- $\text{CaCO}_3$  combination with a ratio of 6.67:1, and HA- $\text{MgCO}_3$  combination with a ratio of 6.67:1. Each material was ground in a 5kg size of porcelain pot mill using 25-30mm size porcelain milling balls with the ratio of material: ball at 1:1. The rotation speed use for dry mechanosynthesis was 80rpm for 48 h.

**Fourier Transform Infrared Spectroscopy (FTIR) assay procedure:**

Limestone-based CHA was prepared. After switching on the FTIR program (Shimadzu Corporation, Kyoto, Japan), FTIR 8400s option was chosen on the menu column. The scaffold sample was put on the sample holder and positioned in the interferometer of the FTIR tool (Shimadzu Corporation, Kyoto, Japan). BKG start button was clicked to start the examination. CALC menus were optioned to see the peak number as the result of the spectra. The setting noise level was set at 0,1 and the threshold at 7,8. Those setting was to determine the appearances of the result data. The result of the FTIR was a graphic that needs to be consulted to the peak table (SOP from Shimadzu 2007).

**Scanning Electron Microscope Electron connected to Dispersive X-ray Spectroscopy (SEM EDX) assay procedure:**

SEM EDX assay was done by put 2 grams of CHA sample on the pin holder with a carbon tip to allow the attachment of the sample. The prepared sample was then inserted into the EDX tool (EDAX AMATEK Inc., Pennsylvania, USA). In the computer, SEM software was opened, and beam on was started to begin the vacuum for 5 minutes. After vacuuming, the examination point was decided, and both SEM and EDX software were linked to collect the data from the sample.

**X – Ray Diffraction (XRD) assay procedure:**

The monitor of the XRD tool was circled the 2 gram of sample in the position of  $2\theta$  angles. The monitor was paralleled to allow its axis to go through with the appropriate angles to the rotation axis of the sample. The result of X-ray diffraction was printed to the paper with the radiation sources of Cu, KA, and filtered with nickel. The obtained data was compared to Joint Committee Powder Diffraction Standard (JCPDS). Diffraction value with diffraction intensity and angle was analyzed to determine the crystal structure by comparing to *Inorganic Crystal Structure Database* (ICSD) data for the tested sample<sup>16,23</sup>.

**hUCMSC isolation procedure:**

The procedures of this study were ethically approved with IRB no. 205/HRECC.FODM/V/2019. The umbilical cord was obtained from *section cesarian* deliveries. The cord was cut to 0.5mm<sup>3</sup> fragments after the vena and arteries were dissected. Enzymatic digestion through trypsinization using 0.25% trypsin was done for 40 minutes at 37°C, and after being centrifuged, the supernatant was discarded. That process was repeated twice. After trypsinization, the sample was put into PBS solution containing 0,75mg/ml collagenase type IV (Sigma-Aldrich, St. Louis, MO, USA) and 0,075 mg/ml DNAase I (Takara Bio, Shiga, Japan), incubated

at 37°C for 60 minutes before being stirred in magnetic stirrer at 37°C. The mixture was filtered with 100µm filter to obtain pellet cell suspension.<sup>17</sup>

**hUCMSC culture:**

Cell culture was conducted in accordance to the protocol in the Stem Cell laboratories, Institute of Tropical Disease, Universitas Airlangga. Cells were planted with  $1 \times 10^6$  cell/cm<sup>2</sup> density and were put into culture tubes. The growth medium contained  $\alpha$ -modified essential medium ( $\alpha$ -MEM), 20% fetal bovine serum (FBS) (Biowest), penicillin/streptomycin 100U (Sigma-Aldrich, St. Louis, MO, USA), and amphotericin (Sigma-Aldrich, St. Louis, MO, USA). The cultures were incubated in CO<sub>2</sub> 5% incubator at 37°C. The growth medium was replaced every two days. After 80-90% confluence was achieved, the attached cell was transferred to other culture plates with  $1 \times 10^4$  cell/cm<sup>2</sup> density with a growth medium for the expansion.<sup>18</sup>

**hUCMSC characterization:**

**a) Immunocytochemistry:**

The mesenchymal stem cell characterization was defined using immunohistochemistry examination. The monolayer cell was turned into single cell through the trypsinization process. After trypsin addition, centrifugation at 1600 rpm was done for 5 minutes. One ml of DMEM-LG growth medium was added to the cell pellet, and after resuspension, 20µl of the cell was planted to special object-glass. Object glass was put into a box with wet paper, and incubation was done for 1 hour at 37°C. After the incubation, the cell was fixated using formaldehyde 3% for 15minutes at room temperature. After that, it was washed in PBS four times, dried, blocked with PBS containing 1% serum for 15 minutes at room temperature, before being rewashed in PBS four times, then dried. Each sample was added with CD45 or CD105 antibody, labeled by FIT-C, and incubated at 37°C for 45 minutes. After being washed in PBS four times, water droplets surrounding the object-glass were dries using tissue. After dropping 50% glycerin on the object-glass, the cell was observed using a fluorescence microscope at 40x magnification. It was positive if fluorescence was observed in the cell and negative if there was nothing<sup>19,22</sup>.

**b) Viability and proliferation assay of hUCMSC:**

A viability cell assay procedure was conducted using MTT assay. Before the assay, CHA was sterilized using ultraviolet (UV). On the microplate, each well was added with 200µl medium and  $5 \times 10^4$  cells, following by incubation for 1x 24 hours at 37°C with 5% CO<sub>2</sub> humidity.

CHA sample was immersed in the medium for 1x24 hours and stored in the refrigerator at 4°C before the assay. Cell viability was observed after the sample has

24 hours of contact with *hUCMSC*, while proliferation was observed after 72 hours of contact at 37°C with 5% CO<sub>2</sub> humidity. MTT (Thermo Fisher Scientific, USA) was then administered for 25 µl on each well followed by incubation for 4 hours at 37°C with 5% CO<sub>2</sub> humidity. The solution on each well was discarded, and 200 µl DMSO was added to dilute the crystals. Purple formazan was observed on each well using the inverted microscope. The microplate was then put into an ELISA reader (Bio-Rad, USA) with a 595 nm wavelength for the final result of optical density (OD).<sup>20</sup> To decide the viability and proliferation rate of *hUCMSC* (%), the following formula was used<sup>24,25</sup>:

$$\% \text{ cell viability} = \frac{\text{OD of treatment group+media}}{\text{OD of cell group+media}} \times 100$$

**RESULTS:**

**FITR assay:**

CHA has functional groups of hydroxyl (-OH), phosphate (PO<sub>4</sub><sup>3-</sup>), and carbonate (CO<sub>3</sub><sup>2-</sup>). The wavenumbers of the -OH function group was around 3700 – 3600 cm<sup>-1</sup>, 3550 – 3500 cm<sup>-1</sup>, and 300-1700 cm<sup>-1</sup>. The PO<sub>4</sub><sup>3-</sup> function group, has wavenumbers of 1100 – 950 cm<sup>-1</sup>. Wavenumbers of CO<sub>3</sub><sup>2-</sup> function group, was 1450 – 1410 cm<sup>-1</sup> and 880 – 800 cm<sup>-1</sup>.<sup>26</sup>

The result of FITR for CHA was in the form of the peaks on transmittance (%) to wavenumbers (cm<sup>-1</sup>) graph. CHA from BBK showed -OH bonding at the peak of 3649.65 cm<sup>-1</sup>. PO<sub>4</sub><sup>3-</sup> was found at the peak of 961.62 cm<sup>-1</sup>, 1026.48 cm<sup>-1</sup>, and 1086.79 cm<sup>-1</sup>. While CO<sub>3</sub><sup>2-</sup> was shown by the peak at 1425.12 cm<sup>-1</sup> as shown on Figure 1.

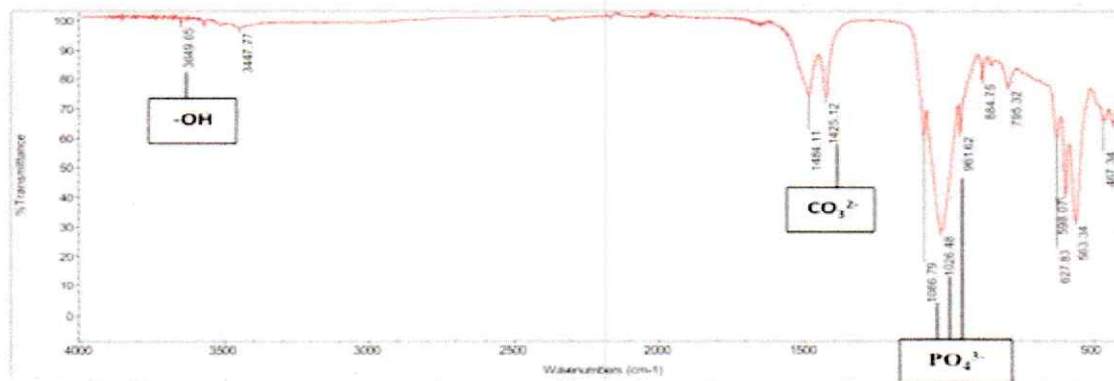


Figure 1. FTIR assay result of CHA.

**SEM assay:**

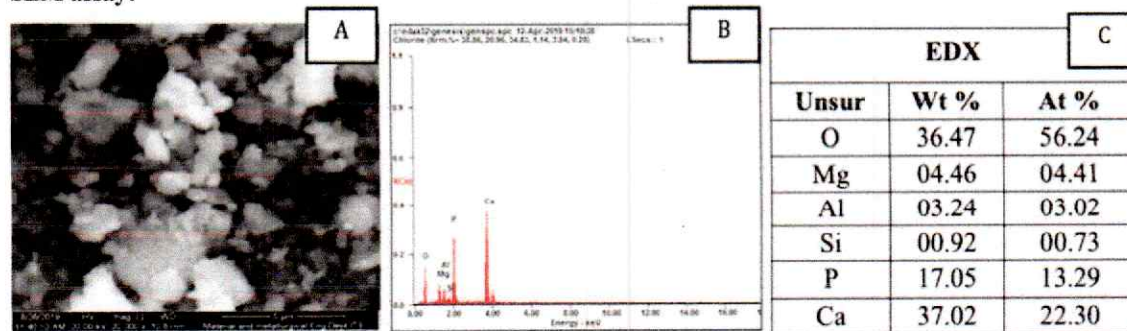


Figure 2. (A) The result of SEM assay for CHA at 20,000x magnification, (B) EDX CHA, (C) the element contents of CHA.

Figure 2A shows the graphic result of the SEM assay for CHA samples extracted by BBK Indonesia. The graphic (see Figure 2B) is the energy comparison graphic using kilo electron volt (keV) as its unit, while the X-ray intensity used kilo count (kCnt) unit. The graphic shows CHA BBK contains oxygen (O), magnesium (Mg), aluminum (Al), silicate (Si), phosphor (P), and calcium (Ca). The percentage of each element contained by CA can be seen in Figure 2C, with the highest percentage is

38, 40 Wt % for Ca and the lowest is 00.92% for Si. The Ca/P ratio of molar is 1.67 (22.30 At% for Ca and 13.29 At % for P).

**XRD assay:**

The result of the XRD assay for limestone-based CHA can be seen in Figure 3. It shows a graphic pattern with a firm peak which can be interpreted that the sample has crystals formation.

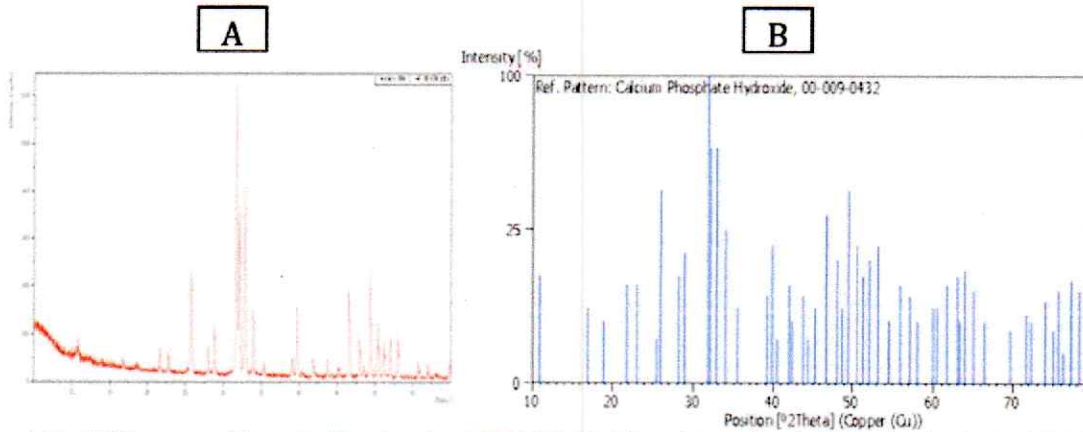


Figure 3. The XRD assay graphic result of limestone-based CHA (A), Joint Committee on Powder Diffraction Standards (JCPDS) with code 00-009-0432(B).

**Characterization of hUCMSC:**

The characterization of hUCMSC was done using immunohistochemistry with the FIT-C label. The immunohistochemistry examination showed a negative result for CD45, a hematopoietic stem cell marker. Both CD90 and CD 105 staining showed a strong expression of positive MSC under the fluorescence microscope. The hUCMSC characterization using CD 45, CD 90, and CD 105 markers under fluorescence microscope at 40X magnification.

**Table 1. The viability and proliferation percentage of hUCMSC after direct exposure of limestone-based CHA**

No	CHA concentration	N	hUCMSC viability 24 h			hUCMSC Proliferation 72 h		
			Mean OD	SD	% Viable cell	Mean OD	SD	% Viable cell
1	50 µg/ml	5	0.59	3.89	101.70	0.77	2.55	113.61
2	25 µg/ml	5	0.53	4.83	89.92	0.67	1.22	97.34
3	12.5 µg/ml	5	0.52	4.82	87.76	0.65	1.58	95.22
4	6.25 µg/ml	5	0.49	5.58	81.84	0.64	2.55	93.75

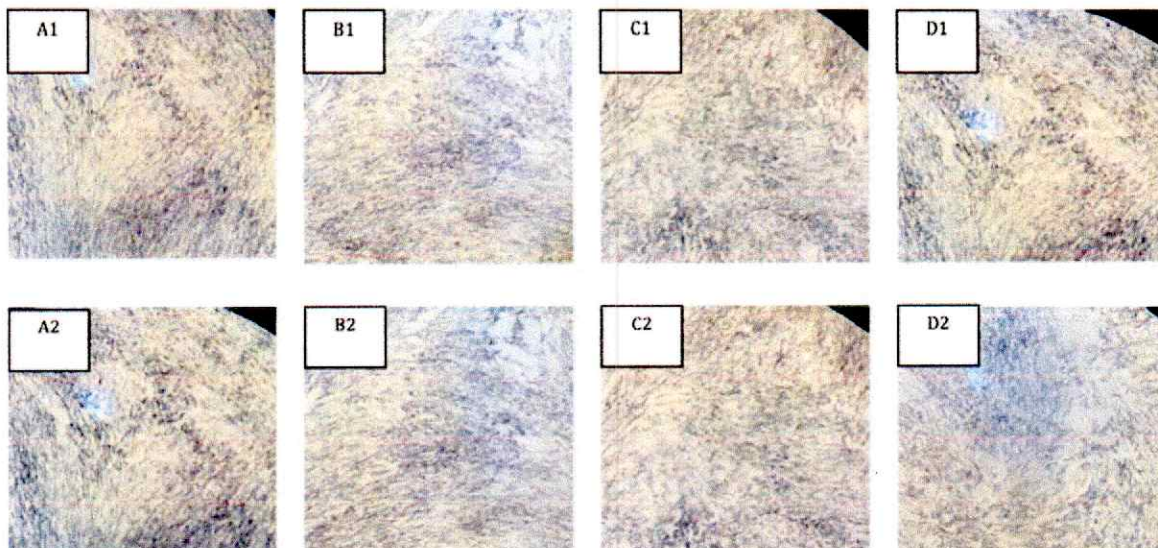


Figure 4. Microscopic photo of MTT assay for the treatment group after exposed with: CHA 50 µg/ml for 24 h (A1) and for 72 h (A2); CHA 25 µg/ml for 24 h (B1) and for 72 h (B2); CHA 12,5 µg/ml for 24 h (C1) and for 72 h (C2); CHA 6,25 µg/ml for 24 h (D1) and for 72 h (D2).

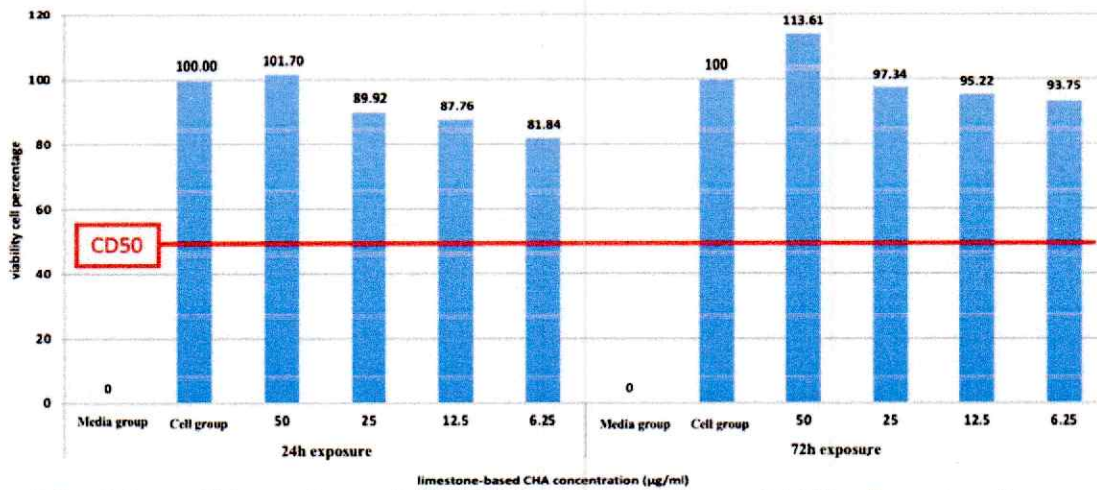


Figure 5. Correlation graphic between limestone-based CHA concentration and the mean of viability cell percentage after exposure for 24 h and 72 h.

Based on Table 1, the highest mean of viability cell percentage was found in cells exposed with CHA 50  $\mu\text{g/ml}$  for 24 h (101,70%) and for 72 h (113.61%). In contrast, the lowest was found in the cell exposed with CHA 6.25  $\mu\text{g/ml}$  for 24 h (81.84%) and 72h (93.75%).

The graphic in Figure 7 showed the viability cell percentage of all treatment groups higher than 50% ( $\text{CD}_{50}$ ), and the number went higher with higher concentration and longer contact duration. The analysis of one-way ANOVA continued with post hoc Tukey HSD assays demonstrated significant differences between each treatment

**DISCUSSION:**

The characteristic assays of CHA in this study aimed to analyze the functional group, particle formation, contents, and cytotoxicity of limestone-based CHA. This study also observed the proliferation of hUCMSC after exposure to limestone-based CHA. FTIR assay meant to identify the presence of hydroxyl (-OH), phosphate ( $\text{PO}_4^{3-}$ ), and carbonate ( $\text{CO}_3^{2-}$ ) functional groups<sup>23</sup>. CHA in FTIR assay showed the presence of OH bonds for the peak in  $3649.65\text{ cm}^{-1}$ . Phosphate was observed by the appearance of peaks in  $961.62\text{ cm}^{-1}$ ,  $1026.48\text{ cm}^{-1}$ , and  $1086.79\text{ cm}^{-1}$ . Carbonate was identified with the peak in  $1425.12\text{ cm}^{-1}$ . The hydroxyl formation group was recorded by the typical peak in the region of  $3800\text{-}3200\text{ cm}^{-1}$ , originated from the hydrated inorganic compounds. Hydrated inorganic compounds were the result of the production process of hydroxyapatite with water addition, which lead to the water molecule on the crystal structure of those materials producing a peak due to the stretching and bending of O-H bonds. Phosphate groups ( $\text{PO}_4^{3-}$ ) in FTIR assay observed from the presence of peaks in the phosphate bond range, which was  $1100\text{ - }950\text{ cm}^{-1}$ <sup>26</sup>.

Based on the XRD assay, there was a clear graphic for each peak, and it has the same peak pattern compared to JCPDS, which means the particle formation of those materials was crystal formation. The comparison result between the XRD assay of CHA and JCPDS data has similar positioning. Based on those similarities, it can be concluded that limestone-based CHA was in accordance with standard data of JCPDS for diffraction groups of apatite mineral (CaOH) from hydroxy calcium phosphate compound with reference code of 00-009-0432. The result of the XRD assay on CHA was supported by the study of CHA using hydrothermal treatment, which resulted in the carbonation reaction resulted in more peaks. This finding demonstrated that the crystal of CHA from the carbonation reaction was largely produced but in a smaller size. HA was fully transformed into CHA after 72 h of carbonation. The result of carbonation was expected to show a good tissue reaction for biomedical application<sup>9</sup>.

The composition of limestone-based CHA containing oxygen (O), calcium (Ca), and phosphor (P) was proved by EDX assay. Based on the result of EDX, CHA BBK Indonesia contains oxygen (O), magnesium (Mg), aluminum (Al), silicate (Si), phosphor (P), and calcium. The percentage of each element in CHA can be observed in figure 2(C). Calcium has the highest concentration with 38,40 Wt %, while the lowest was Si with 00,92%. The comparison of Ca/P molar were 22,30 At % and 13,29 At %, thus the Ca/P ratio was 1,67 (Figure 2).

Cell viability is an important marker in the tissue engineering concept, as this assay was conducted to observe the toxicity of the tested material. This study conducted viability and proliferation assays on hUCMSC after exposed to limestone-based CHA at four different concentrations: 50  $\mu\text{g/ml}$ , 25  $\mu\text{g/ml}$ , 12,50  $\mu\text{g/ml}$ , and

6,25µg/ml. The viable cell showed an active metabolism of mitochondria by turning MTT into a purple-colored formazan product (Figure 6 and 7). The dead cell lost its capability to turn MTT into formazan; thus, the color intensity formed by formazan could become the living cell marker<sup>27</sup>.

Limestone-based CHA extracted by BKK in the concentration of 50 – 6,25µg/ml has a viability cell percentage higher than 50%, which according to CD<sub>50</sub>, all concentrations showed no toxicity. It was supported by a previous study that claimed that through cytology, the biocompatibility standard of biomaterial was 60%, which means a biomaterial considered biocompatible is the percentage of the viable cell after exposure and contact is more than 60%<sup>28</sup>. Other research used IC<sub>50</sub> standard as biocompatibility standard of biomaterial. The IC<sub>50</sub> standard stated that a biomaterial is compatible if the viable cell percentage after exposure and contact was 50%<sup>24,25,29-31</sup>. The high viability cell percentage in this study can be resulted by the high ratio of Ca/P in CHA. Based on the results of this study, higher concentration of calcium resulted in higher proliferation. Limestone-based CHA from Padalarang and Cirebon extracted by BKK has a Ca/P ratio of 1.67, similar to the Ca/P ratio of human bone, in the range of 1,33-1,67<sup>9,32</sup>. A high concentration of Ca will increase the expression of the Ca channel, increased cell proliferation. Calcium sensing receptor (CaSR) can detect the changing of external Ca<sup>2+</sup> concentration and activate the Ca channel to increase e Ca<sup>2+</sup> influx. A higher concentration of Ca<sup>2+</sup> will result in a higher influx, which stimulates cell proliferation as the cellular response<sup>33,34</sup>.

Cell viability increased possibly due to cellular activity with similar conduct as the cellular activity happened in the human body when extracellular matrix (ECM) interacted with cell<sup>35</sup>. The living cell could not directly interact with foreign material. Those interactions need adhesive molecule proteins such as fibronectin (FN), vitronectin (VN), fibrinogen (FG), and laminin (LN). Adhesive molecule protein *in vivo* was obtained from physiological fluid adsorption, while *in vitro*, it was obtained from protein adsorption from media culture. The adsorbed adhesive molecule protein produced a protein layer on the CHA surface which played an essential role in cell and biomaterial bone graft interaction<sup>18</sup>.

## CONCLUSION:

CHA from BBK Indonesia has -OH, PO<sub>4</sub><sup>3-</sup>, CO<sub>3</sub><sup>2-</sup> functional groups. It has crystal particle formation containing O, Ca, and P elements with a CA/P ratio of 1,67. All concentrations tested showed no toxicity to hUCMSC and had the ability to stimulate the proliferation of hUCMSC.

## CONFLICT OF INTEREST:

The authors have no conflicts of interest regarding this investigation.

## ACKNOWLEDGMENTS:

The authors would like to thank Faculty of Dental Medicine Universitas Airlangga to fund this research through "Penelitian Unggulan Fakultas" Internal Research Funding Grant No. 1408/UN3/2019.

## REFERENCES:

1. Kunert-Keil C, Gredes T, Gedrange T. Biomaterials Applicable for Alveolar Sockets Preservation: In Vivo and In Vitro Studies. In: Turkyilmaz I, editor. Implant Dentistry - The Most Promising Discipline of Dentistry. Shanghai: InTech; 2011; pp. 17–52.
2. Alex Jahangir BA, Nunley RM, Mehta S, Sharan A, Washington Health Policy Fellows T. Bone-graft substitutes in orthopaedic surgery. AAOS Now 2008:5–9.
3. Nugraha AP, Rezkita F, Puspitaningrum S, Luthfimaedah MS, Narnada B, Prahasanti C, et al. Gingival Mesenchymal Stem Cells and Chitosan Scaffold to Accelerate Alveolar Bone Remodelling in Periodontitis: A Narrative Review. Research Journal of Pharmacy and Technology 2020; 13:2502–6.
4. Amini AR, Adams DJ, Laurencin CT, Nukavarapu SP. Optimally porous and biomechanically compatible scaffolds for large-area bone regeneration. Tissue Engineering - Part A 2012; 18:1376–88. doi: 10.1089/ten.tea.2011.0076.
5. Leveugood SKL, Zhang M. Chitosan-based scaffolds for bone tissue engineering. Journal of Materials Chemistry B 2014; 2:3161–84. doi: 10.1039/c4tb00027g.
6. Kosachan N, Jaroenworarluck A, Jiemsirilers S, Jinawath S, Stevens R. Hydroxyapatite nanoparticles formed under a wet mechanochemical method. Journal of Biomedical Materials Research - Part B Applied Biomaterials 2017; 105:679–88. doi: 10.1002/jbm.b.33590.
7. Radhika G, Reddy P, Venkatesh P, Reddy R. An overview on regenerative medicine. Research Journal of Pharmacy and Technology 2010; 3:727–8.
8. Linhart W, Peters F, Lehmann W, Schwarz K, Schilling A, Amling M, et al. Biologically and chemically optimized composites of carbonated apatite and polyglycolide as bone substitution materials. J Biomed Mater Res 2001; 54:162–71. doi: 10.1002/1097-4636(200102)54:2<162::AID-JBM2>3.0.CO;2-3.
9. Ana ID, Matsuya S, Ishikawa K. Engineering of Carbonate Apatite Bone Substitute Based on Composition-Transformation of Gypsum and Calcium Hydroxide. Engineering 2010; 2:344–52. doi: 10.4236/eng.2010.25045.
10. Anderson J. Biocompatibility and the Relationship to Standards: Meaning and Scope of Biomaterials Testing. In: Ducheyne P, Kirkpatrick KEH, Hutmacher DW, Grainger JW, Kirkpatrick CJ, editors. Comprehensive Biomaterials. Oxford: Elsevier Science; 2017; pp. 7–29.
11. Dewi AII, Ana ID. The use of hydroxyapatite bone substitute grafting for alveolar ridge preservation, sinus augmentation, and periodontal bone defect: A systematic review. Heliyon 2018; 4:1–30. doi: 10.1016/j.heliyon.2018.e00884.
12. Ibrahim MS, El-Wassefy NA, Farahat DS. Biocompatibility of dental biomaterials. In: Biomaterials for Oral and Dental Tissue Engineering. Elsevier Inc.; 2017; pp. 117–40.
13. Duya P, Bian Y, Chu X, Zhang Y. Stem cells for reprogramming: Could hUMSCs be a better choice? Cytotechnology 2013; 65:335–45. doi: 10.1007/s10616-012-9489-3.
14. Wahyudi K, Edwin F, Sofyaningsih N. Sintesis dan Karakterisasi Bone Ash Sintetik dari Bahan Alam. Jurnal Keramik dan Gelas Indonesia 2016; 25:46–58.
15. Sriram K, Vishnupriya V, Gayathri R. Review on the role of Nanotechnology in Dentistry and Medicine. Research Journal of



- Pharmacy and Technology 2016; 9:1249.
16. Munasir M, Triwikantoro T, Zainuri M, Darminto D. Uji XRD dan XRF pada Bahan Mineral (Batuan dan Pasir) Sebagai Sumber Material Cerdas (CaCO<sub>3</sub> dan SiO<sub>2</sub>). *Jurnal Penelitian Fisika dan Aplikasinya (JPFA)* 2012; 2:20-9. doi: 10.26740/jpfa.v2n1.p20-29.
  17. Han YF, Tao R, Sun TJ, Chai JK, Xu G, Liu J. Optimization of human umbilical cord mesenchymal stem cell isolation and culture methods. *Cytotechnology* 2013; 65:819-27. doi: 10.1007/s10616-012-9528-0.
  18. Rantam FA. *Stem Cell Mesenchymal, Hematopoetik, Dan Model Aplikasi*. 2nd ed. Surabaya: Airlangga University Press. 2014.
  19. Chen X, Zhang ZY, Zhou H, Zhou GW. Characterization of mesenchymal stem cells under the stimulation of Toll-like receptor agonists. *Development Growth and Differentiation* 2014; 56:233-44. doi: 10.1111/dgd.12124.
  20. Yulianti A, Kartikasari N, Munadzirah E, Rianti D. The profile of crosslinked bovine hydroxyapatite gelatin chitosan scaffolds with 0.25% glutaraldehyde. *Journal of International Dental and Medical Research* 2017; 10:151-5.
  21. Patyar S. Role of Stem Cells in treatment of different Diseases. *Research Journal of Pharmacy and Technology* 2018; 11:3667-78.
  22. Azeem S, Raj S, Kajal K, Thiagarajan P. Umbilical Cord Stem Cells: A Review. *Research Journal of Pharmacy and Technology* 2018; 11:2709-14.
  23. Dubey N, Dubey N, Mehta RS, Saluja AK, Jain DK. Preparation and Physico-chemical Characterization of Kushta-e-sadaf. A Traditional Unani Formulation. *Research Journal of Pharmacy and Technology* 2008; 1:182-6.
  24. Kangraikar VA, Kulkarni AR. In Vitro Cytotoxic Activity of Alcoholic Extract of *Aristolochia indica*. *Research Journal of Pharmacy and Technology* 2013; 6:8.
  25. Singh MK, Prathapan A, Nagori K, Ishwarya S, Raghu KG. Cytotoxic and Antimicrobial Activity of Methanolic Extract of *Boerhaavia diffusa* L. *Research Journal of Pharmacy and Technology* 2010; 3:1061-3.
  26. Stuart BH. *Infrared Spectroscopy: Fundamentals and Applications*. Chichester: John Wiley & Sons, Ltd. 2005.
  27. van Meerloo J, Kaspers GJL, Cloos J. Cell Sensitivity Assays: The MTT Assay. In: Clifton NJ, editor. *Methods in Molecular Biology*. 731. *Methods Mol Biol*; 2011; pp. 237-45.
  28. Siswanto D, Aminatun I, Astuti SD. Sintesis Hidroksiapatit Dari Tulang Sotong Untuk Aplikasi Bone Repair. Universitas Airlangga. 2010.
  29. Kumala S, Septisetyani EP, Meiyanto E. Fraksi n-butanolik kapang endofit Buah Makasar meningkatkan efek apoptosis doxorubusin pada sel MCF-7. *Majalah Farmasi Indonesia* 2009; 20:42-7.
  30. Momin MAM, Rashid MM, Urmu KF, Rana MS. Phytochemical Screening and Investigation of Antioxidant and Cytotoxicity Potential of different extracts of selected Medicinal Plants of Bangladesh. *Research Journal of Pharmacy and Technology* 2013; 6:1042.
  31. Chauhan R, D'Souza HL, Shabnam RS, Abraham J. Phytochemical and cytotoxicity analysis of seeds and leaves of *Adenanthera pavonina*. *Research Journal of Pharmacy and Technology* 2015; 8:198-203.
  32. Terzioğlu P, Ögüt H, Kalemtaş A. Natural calcium phosphates from fish bones and their potential biomedical applications. *Materials Science and Engineering C* 2018; 91:899-911. doi: 10.1016/j.msec.2018.06.010.
  33. Telli C, Serper A, Dogan AL, Guc D. Evaluation of the cytotoxicity of calcium phosphate root canal sealers by MTT assay. *Journal of Endodontics* 1999; 25:811-3. doi: 10.1016/S0099-2399(99)80303-3.
  34. Borowiec AS, Bidaux G, Pigat N, Goffin V, Bernichtein S, Capiod T. Calcium channels, external calcium concentration and cell proliferation. *European Journal of Pharmacology* 2014; 739:19-25. doi: 10.1016/j.ejphar.2013.10.072.
  35. Gugutkov D, Altankov G, Rodriguez Hernández JC, Monleón Pradas M, Salmerón Sánchez M. Fibronectin activity on substrates with controlled - OH density. *Journal of Biomedical Materials Research - Part A* 2010; 92:322-31. doi: 10.1002/jbm.a.32374.