



# ACS OMEGA

pubs.acs.org/omega


Volume 6, Issue 20

May 29, 2021

$O_2$

$O_2$

$O_2$

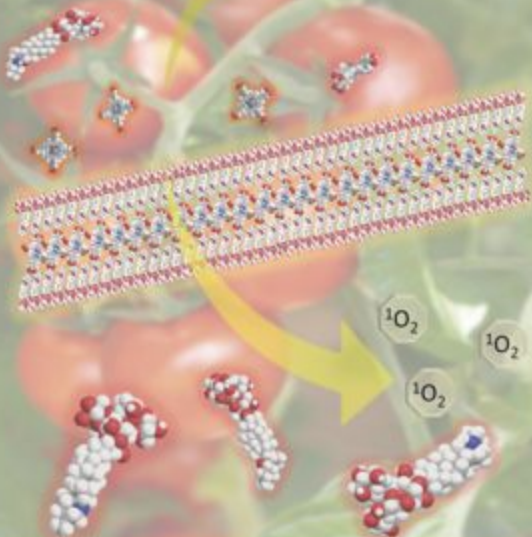

$^{16}O_2$

$^{16}O_2$

$^{16}O_2$

# Comparison Direct Synthesis of Hyaluronic Acid-Based Carbon Nanodots as Dual Active Targeting and Imaging of HeLa Cancer Cells

Yu-Yu Aung, Aswandi Wibrianto, Jefry S. Sianturi, Desita K. Ulfa, Satya. C. W. Sakti, Irzaman Irzaman, Brian Yulianto, Jia-yaw Chang, Yaung Kwee, and Mochamad Z. Fahmi\*

Cite This: <https://doi.org/10.1021/acsomega.1c01287>

Read Online


ACCESS |

Metrics & More

Article Recommendations

Supporting Information

**ABSTRACT:** The present study explores the potential of carbon nanodots (CDs) synthesized from hyaluronic acid using microwave-assisted and furnace-assisted methods as bioimaging agents for cancer cells. The investigation on the effect of microwave-assisted and furnace-assisted times (2 min and 2 h) on determining CD character is dominantly discussed. Various CDs, such as HA-P1 and HA-P2 were, respectively, synthesized through the furnace-assisted method at 270 °C for 2 min and 2 h, whereas HA-M1 and HA-M2 were synthesized with the microwave-assisted method for 2 min and 2 h, respectively. Overall, various CDs were produced with an average diameter, with the maximum absorption of HA-P1, HA-P2, HA-M1, and HA-M2 at 234, 238, 221, and 217 nm, respectively. The photoluminescence spectra of these CDs showed particular emissions at 320 nm and excitation wavelengths from 340 to 400 nm. Several characterizations such as X-ray photoelectron spectroscopy, Fourier-transform infrared spectroscopy, X-ray diffraction, and Raman spectroscopy reveal the CD properties such as amorphous structures, existence of D bands and G bands, and hydrophilic property supported with hydroxyl and carboxyl groups. The quantum yields of HA-M1, HA-M2, HA-P1, and HA-P2 were 12, 7, 9, and 23%, respectively. The cytotoxicity and in vitro activity were verified by a cell counting kit-8 assay and confocal laser scanning microscopy, which show a low toxicity with the percentage of living cells above 80%.

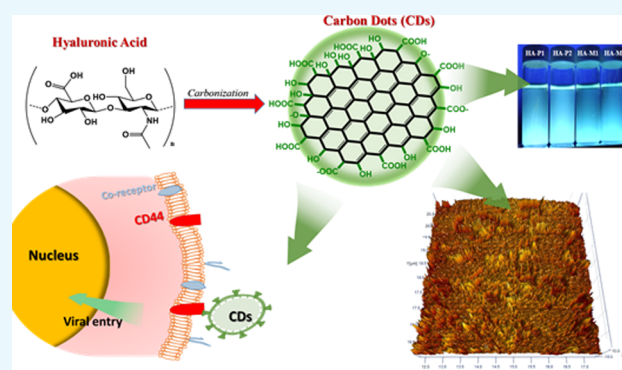

## 1. INTRODUCTION

Over the past 3 decades, cancer has been a common major problem and became one of the leading death causes in every country of the world.<sup>1</sup> In 2018, the International Agency for Research on Cancer predicted that 18.1 million new cancer cases and 9.6 million deaths will be reached in 5 years, the so-called 5-year prevalence, which is estimated to be 43.8 million.<sup>2</sup> Thus, several intensive attempts are being made for the development of therapies as worth as early diagnosis procedures. General cancer treatments that may be applied are surgery, chemotherapy, or radiotherapy. However, they are not effective due to the failure of early diagnosis, insufficient on-targeted drug delivery, systemic toxicity, and lack of real-time monitoring of therapeutic responses in cancer treatment.<sup>3</sup> Therefore, early detection of cancer is important to determine treatments that should be given to cancer patients.

Many efforts have been focused on the disease through innovative approaches in the biomedical field by recent advances in nanotechnology. The researchers are developing nanoparticles as smart tools for molecular imaging to determine the molecular-level detection of cancer. Nanoparticles are excellent optical probes that have fluorescent


activity and passive targeting ability for light-scattering-based bioimaging and biomolecular detection.<sup>4,5</sup>

Various nanoparticles used for optical fluorescence imaging including mesoporous silica nanoparticles,<sup>6</sup> carbon nanotubes,<sup>7</sup> nanodiamonds,<sup>8</sup> semiconductor quantum dots (QDs),<sup>9</sup> gold nanoparticles,<sup>10</sup> and graphene<sup>11</sup> have been extensively studied for biomedical applications. Carbon-based QDs (also called carbon nanodots, CDs) have gained the attention of researchers due to their properties such as a small size of less than 10 nm, good hydrophilicity, biocompatibility, low cytotoxicity, fluorescence emission, chemical stability, easy synthesis, and other physicochemical properties.<sup>12</sup> Their optical properties and fluorescence emissions in the near-infrared spectral region make them a superior candidate for

Received: March 10, 2021

Accepted: April 29, 2021

Scheme 1. Illustration of the Synthesis of HA CDs and Their Internalization Mechanism on HeLa Cancer Cells

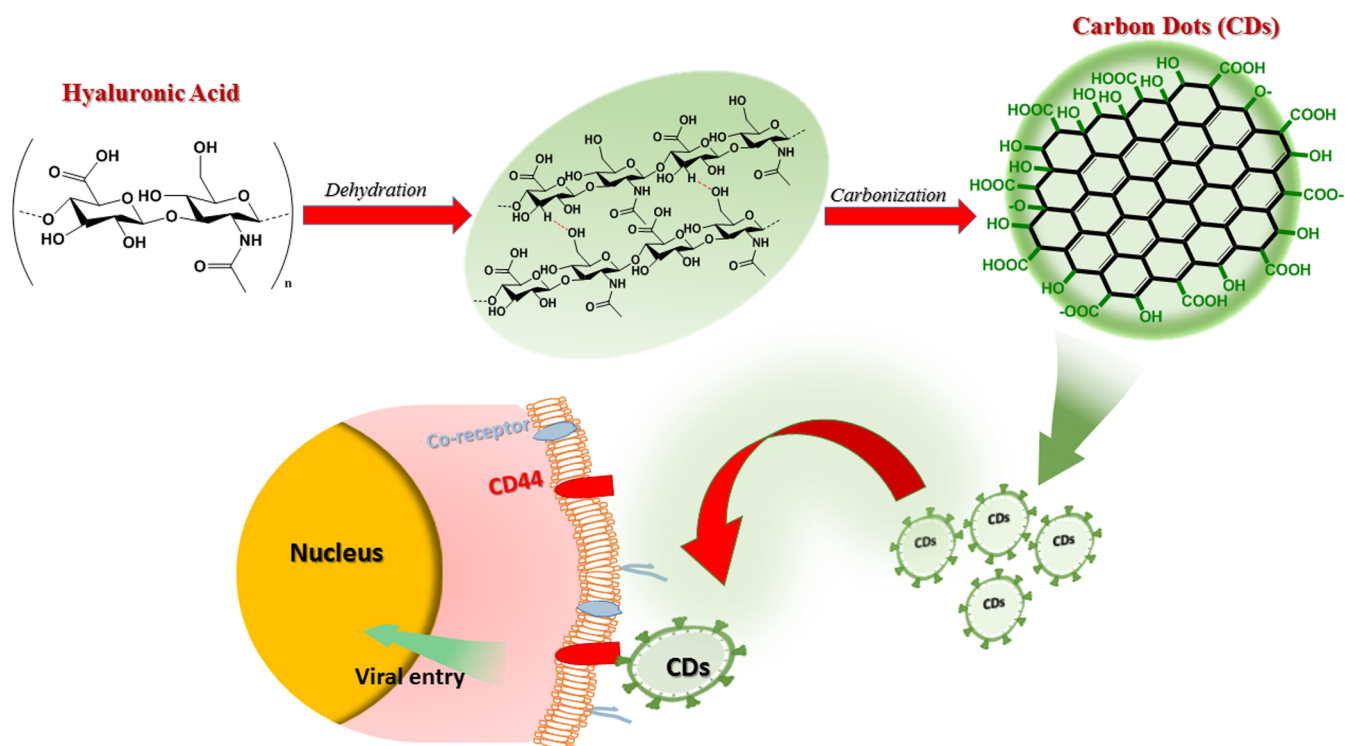

biomedical applications, especially for bioimaging cancer detection, compared to other nanoparticles.<sup>13</sup>

CDs can be synthesized from several materials such as amino acids,<sup>14</sup> monosaccharides, polysaccharides,<sup>15</sup> citric acid,<sup>16</sup> and hyaluronic acid (HA).<sup>17</sup> Biomass polysaccharides are well-known as natural biopolymers, which are considered as water and energy storage, structural materials, and plants' suppliers. In recent advances, natural linear polysaccharide-based materials were used to synthesize many CDs due to their desirable properties such as non-toxicity, biodegradability, biocompatibility, non-immunogenicity, polymeric nature, and excellent hydrophilicity, which allow them to be widely used as prognostic molecules and in the treatment of various human and animal diseases.<sup>18,19</sup> Among various biomass-derived polysaccharides, HA is one of the carbon source precursors with multiple acid and hydroxyl groups set as a linear long-chain polymer, ubiquitous with a glycosaminoglycan group in the mammalian tissue and extracellular matrix.<sup>20,21</sup> In previous studies on cancer cells, HA is bound to a cluster-determinant 44 (CD44) receptor for targeting and activating over-expression in all cancer cells, which has high affinity as a desirable receptor compared to normal body cells. It indicated that HA can be a potential material for future applications in clinical cancer therapy and detection.<sup>22</sup>

CDs can be synthesized by two methods: top-down and bottom-up. However, top-down methods require external energy to break down relatively huge carbon molecules into smaller carbogenic parts based on physical approaches, such as arc-discharge,<sup>23</sup> arc-produced,<sup>24</sup> laser ablation,<sup>25</sup> electro-oxidation,<sup>26</sup> and electrochemical methods.<sup>27</sup> Meanwhile, bottom-up methods used carbon precursors to synthesize CDs based on chemical approaches. Bottom-up methods are simpler, and it is feasible to control experimental conditions with low-cost starting materials and experimental apparatus. Bottom-up methods include ultrasound-assisted,<sup>27,28</sup> pyro-


lysis,<sup>29</sup> hydrothermal,<sup>30</sup> and microwave-assisted methods.<sup>31</sup> Among the above methods, the application of microwave- and furnace-assisted methods promoted simple, rapid, and efficient processes.<sup>12</sup> In terms of the application of HA as CD sources, recent studies have reported the application of the hydrothermal method on the synthesis of CDs using HA.<sup>32–34</sup> Even though the obtained CDs work successfully on theranostics of tumor cells, the hydrothermal method offering a multi-step, complicated synthesis process can also be attributed to those reports. These conditions motivate us to explore more applications of microwave- and furnace-assisted methods for CD synthesis. Moreover, the study on the application of HA in nanomaterial research predominantly just explores its function as a cancer-cell-targeting agent, and the synthesis of HA-based CDs has not been clearly explored yet. In scope of effectiveness, it has become a crucial aspect to create a simple and fast synthesis route on preparing CDs as excellent theranostic agents.

In the present research, CDs were synthesized using HA as a carbon source through, while also comparing, microwave- and furnace-assisted methods for their use as a HeLa marker. The as-prepared CDs were further characterized to determine the structure, fluorescence, and bioimaging application. The toxicity of CDs was measured using a cell counting kit-8 (CCK-8) assay, and the CD fluorescence imaging on HeLa cells was acquired by confocal laser scanning microscopy (CLSM). Other optical and structural characterizations on CDs were also determined, including X-ray diffraction (XRD), Fourier-transform infrared (FTIR) spectroscopy, Raman spectroscopy, X-ray photoelectron spectroscopy (XPS), and UV-vis spectroscopy.

## 2. RESULTS AND DISCUSSION

The comprehensive mechanism of CD formation involves dehydration and carbonization in the progress of microwave-

and furnace-assisted experiments using HA as shown in Scheme 1. We designed HA as carbon precursors, while sodium hydroxide was used to activate the formation of CDs through regular dehydration, followed by carbonization. The existence of NaOH encourages any electronegative site of HA to support removal of water through first dehydration and further carbonization to form graphene oxide-like structures on CDs. HA has a high affinity as desirable receptors for targeting and activating overexpression in cancer cells due to its ability to bond with CD44 receptors. The CD formation was proven by the emission of luminescence of CDs under UV light (Figure 1a). This phenomenon came surely from electron movement on the orbital state of CDs.

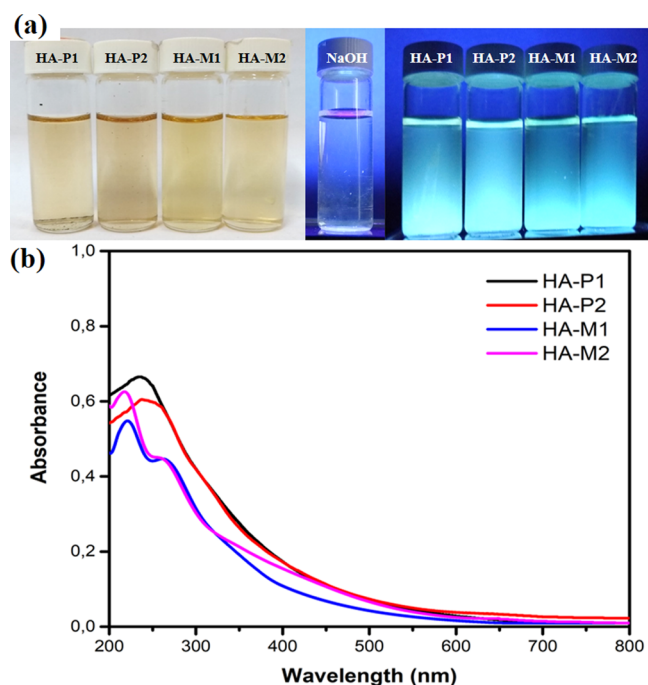


**Figure 1.** (a) Photograph of HA CDs taken under 320 nm UV light. (b) UV-vis spectra of furnace-assisted CDs, which are referred to as HA-P1 (black line) and HA-P2 (red line). UV-vis spectra of the microwave-assisted CDs, referred to as HA-M1 (blue line) and HA-M2 (purple line).

All CD emissions are mainly influenced by the  $sp^2$  hybridization by the conjugation bond in the core of CDs and the functional and chromophore groups on the surface of CDs.<sup>35,36</sup> In order to investigate the qualitative analysis of the surface state and the conjugation bond of CDs, further analysis results are illustrated in Figure 1b. The UV-vis absorption spectra of CDs showed a broad absorption band in the range of 200–800 nm. The spectra for HA-M1 and HA-M2 both show two typical absorption maximum peaks at approximately 217 and 283 nm. Meanwhile, HA-P1 and HA-P2 exhibited absorption peak of the  $\pi-\pi^*$  transition of the  $sp^2$  carbon core or C=C bonds at 262 nm and that of the  $n-\pi^*$  transition of C=O bonds at 284 nm.<sup>37</sup> It confirmed that CDs have a typical aromatic  $\pi$  system similar to the polycyclic aromatic hydrocarbon structure.<sup>19</sup> In general, CDs obtained a maximum absorption wavelength range of 260–320 nm.<sup>38</sup> The CDs are relatively more efficient at high absorption wavelengths. Their absorption characteristics are different from each other, which depend on surface passivation and functional groups of CDs.<sup>39</sup>


For further investigation on the optical properties of CDs, we assess photoluminescence (PL) spectra of pure HA (Figure 2a) utilizing furnace-assisted CDs (Figure 2b,c) and microwave-assisted CDs (Figure 2d,e). This analysis aims to acquire the emission wavelength, emission characteristics, and quantum yield (QY) value of compared CDs. For all samples, fluorescence occurred at around 410–445 nm by applying  $\lambda_{ex} = 320$  nm, which also emitted a strong light-blue color.<sup>33</sup> The alteration of the excitation wavelength from 420 to 510 nm caused the PL peak of CDs to shift at a longer wavelength with a maximum intensity, which tends to form a red-shift emission (Figure 2f).<sup>32</sup> The transition of the lowest unoccupied molecular orbital to the highest occupied molecular orbital can be observed by the PL spectra. Among these CDs synthesized with varied methods, the maximum intensity emission of HA-P2 was found at a wavelength of 502 nm. The optical properties of CDs have different excitation wavelengths, with different QY values. Using rhodamine 6G (R6G) as a reference, the QY has been calculated as 95%.<sup>40</sup> The QYs of HA-M1, HA-M2, HA-P1, and HA-P2 were obtained as 12, 7, 9, and 23%, respectively. It can be observed that the QY of HA-P2 was the highest compared to that of other CDs and the previous studies as mentioned in Table S1. The PL properties of CDs were used as parameters to study the PL mechanism of these CDs, which were important to reach the highest PL of CDs.<sup>41</sup>

FTIR analysis was next implemented to verify functional groups identified on the CDs. FTIR spectra of bare HA, HA-M1, HA-M2, HA-P1, and HA-P2 are shown in Figure 3. The characteristic absorption bands of O–H and N–H stretching vibrations show a peak at  $3353\text{ cm}^{-1}$ . The absorption peak represents stretching vibrations of carboxylic ( $\text{COO}^-$ ) groups at  $2933\text{ cm}^{-1}$ . The peaks were related to the asymmetric and symmetric stretching vibrations of carboxyl acid groups on the CD surface at around  $1645\text{--}1341\text{ cm}^{-1}$ . The carboxyl stretching vibration group was stronger than the others on the CD structure. The peaks can be observed because of the C–H stretching vibrations and bending of  $sp^2$  to  $sp^3$  of the C–H group at  $1049\text{ cm}^{-1}$ . This peak was stronger on HA-M1 than that on others.<sup>42</sup> It was confirmed that the surface of CDs contains hydrophilic functional groups such as carboxyl and hydroxyl groups. Based on these, CDs have good water solubility.<sup>19</sup> All samples were investigated even further using XPS in order to acquire the composition of elements and percentages and detailed chemical bonding of the samples. As shown in Figure 4, the C 1s spectra of HA-P and HA-M reveal three similar types of carbon bonds, such as  $sp^3$  carbon ( $284\text{ eV}$ ),  $sp^2$  carbon ( $\sim 285\text{ eV}$ ), and C–O ( $\sim 287\text{ eV}$ ). It indicates that CDs HA-M and HA-P have conjugated structures of C=C and C=O, carboxylic groups, and also hydroxyl groups.<sup>43</sup> The N 1s spectra showed two peaks such as C–NH ( $399.4\text{ eV}$ ) and N–(C=O) peaks ( $\sim 400\text{ eV}$ ), which correspond to pyrrolic/pyridinic and graphitic N, respectively. The O 1s spectra of HA-P1 and HA-M1 showed two peaks such as C–O ( $\sim 531\text{ eV}$ ) and C=O ( $533\text{ eV}$ ) peaks. This shows that CDs are highly soluble and stable in an aqueous solution because of their oxygen-rich structure.<sup>44</sup> The results are in accordance with the XPS analysis, which shows hydrophilic groups such as –OH, –NH<sub>2</sub>, and COO– on the surface of as-synthesized CDs.<sup>45</sup>

XRD analysis (Figure S1, Supporting Information) showed a broad peak in the diffractogram range between  $20$  and  $30^\circ$  for HA-M1. In contrast, HA-M2, HA-P1, and HA-P2 showed low

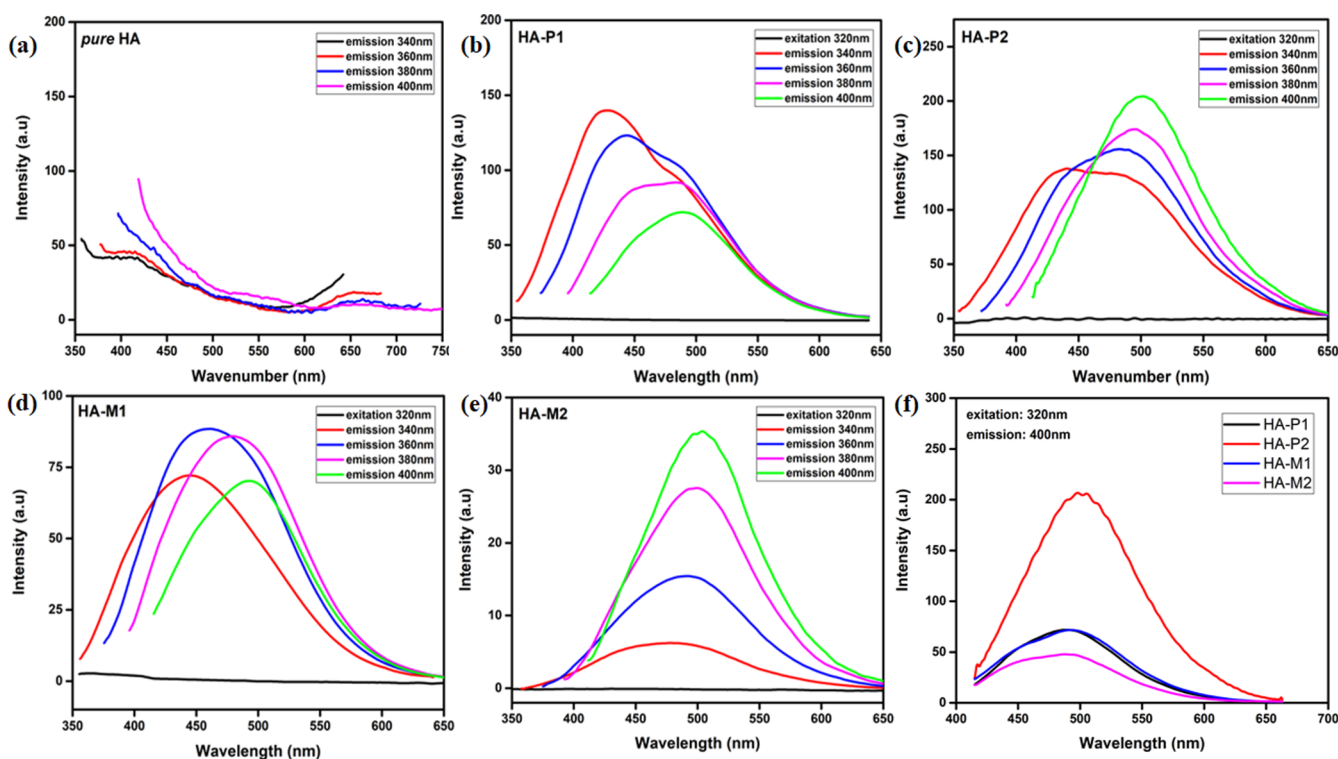

**Figure 2.** PL spectra of (a) pure CDs, (b) HA-P1, (c) HA-P2, (d) HA-M1, and (e) HA-M2 at varied values of  $\lambda_{\text{ex}}$ . (f) PL spectra of all CDs prepared by furnace-assisted and microwave-assisted methods at a  $\lambda_{\text{ex}}$  of 320 nm and a  $\lambda_{\text{em}}$  of 400 nm.

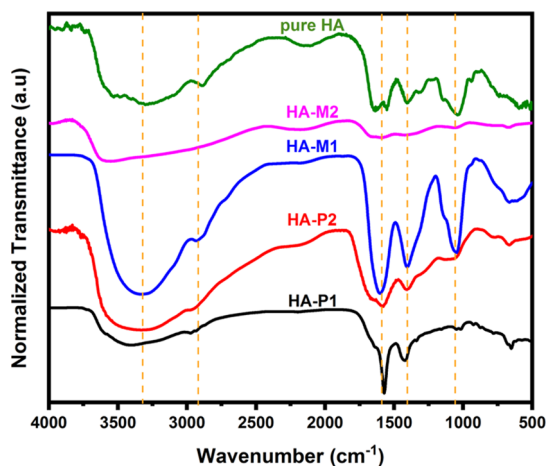


**Figure 3.** IR data of pure HA (green line), microwave-assisted CDs HA-M2 (purple line) and HA-M1 (blue line), and furnace-assisted CDs HA-P2 (red line) and HA-P1 (black line).

significant peaks to prove the crystallinity of CDs at these ranges. The peaks of CDs represent the amorphous carbon phase at a  $2\theta$  of about  $22.7^\circ$ .<sup>46,47</sup> Further analysis to determine the existence of graphene-like structures on HA CDs was performed using Raman spectroscopy (Figure 5a). Raman spectra showed the D bands of HA-M1, HA-M2, HA-P1, and HA-P2 at 1354, 1358, 1344, and 1371  $\text{cm}^{-1}$ , respectively, which are attributed to the  $\text{sp}^3$ -hybridized formation of CDs.<sup>48</sup> In addition, the G bands of HA-M1, HA-M2, HA-P1, and HA-P2 at 1557, 1577, 1570, and 1570  $\text{cm}^{-1}$ , respectively, refer to the presence of carbon with the  $\text{sp}^2$  hybridization on CDs.<sup>49</sup> The appearance of the D band and G band on the surface of CDs leads to the formation of amorphous carbon.<sup>50</sup> Moreover,

the  $I_{\text{D}}/I_{\text{G}}$  ratios of all samples were measured in order to define the defect on CDs. The  $I_{\text{D}}/I_{\text{G}}$  ratios of HA-M1, HA-M2, HA-P1, and HA-P2 were obtained as 0.84, 0.70, 0.70, and 0.66, respectively. All CDs exhibited a decreasing number of D bands and an increasing number of G bands, demonstrating the disorderedness of  $\text{sp}^3$  and  $\text{sp}^2$  hybridizations that simply induced the formation of graphite structures or thinner graphene sheets.<sup>51</sup> The morphology of CDs was identified by atomic force microscopy (AFM) in order to discover the size distribution of CDs. The size distribution of HA-P2 is significantly calculated using ImageJ, where the mean diameter size is about 7 nm (Figure S2, Supporting Information). Furthermore, the three-dimensional (3D) topography of HA-P2 then displayed an average height of below 10 nm (Figure S3b), which means that HA-P2 is categorized in CDs.<sup>52–54</sup>

**2.1. In Vitro Evaluation of CDs.** Further observations of all CDs related to biomedical application were obtained by inspecting the capability of each CD for the staining of HeLa cell lines. The CCK-8 assay was conducted to determine the cytotoxicity of CDs. Figure 6 shows the cell viability of HA-M1, HA-M2, HA-P1, and HA-P2 under various concentrations. The result shows that HA-P2 has the maximum cell viability of 116.92% at 100  $\mu\text{g}/\text{mL}$ . Meanwhile, HA-M2 shows minimum cytotoxicity with a cell viability of 91.28% at 5  $\mu\text{g}/\text{mL}$ . The percentage of cell viability of samples was more than 80%, which indicates that the as-synthesized CDs had low toxicity.<sup>55</sup> Other studies (ISO 10993-5) have identified the cell viability in the range 80–120%, referring to the low toxicity on cells.<sup>56,57</sup> The cytotoxicity of the sample was compared with that of the untreated control with a cell viability of 100%. The cytotoxicity enhancement data have been intensively explored in determining the 50% cytotoxic concentration, or commonly called  $\text{CC}_{50}$ , of each of the varied CDs (Figure S3, Supporting Information). The fitting curve shows that for CDs HA-M1,

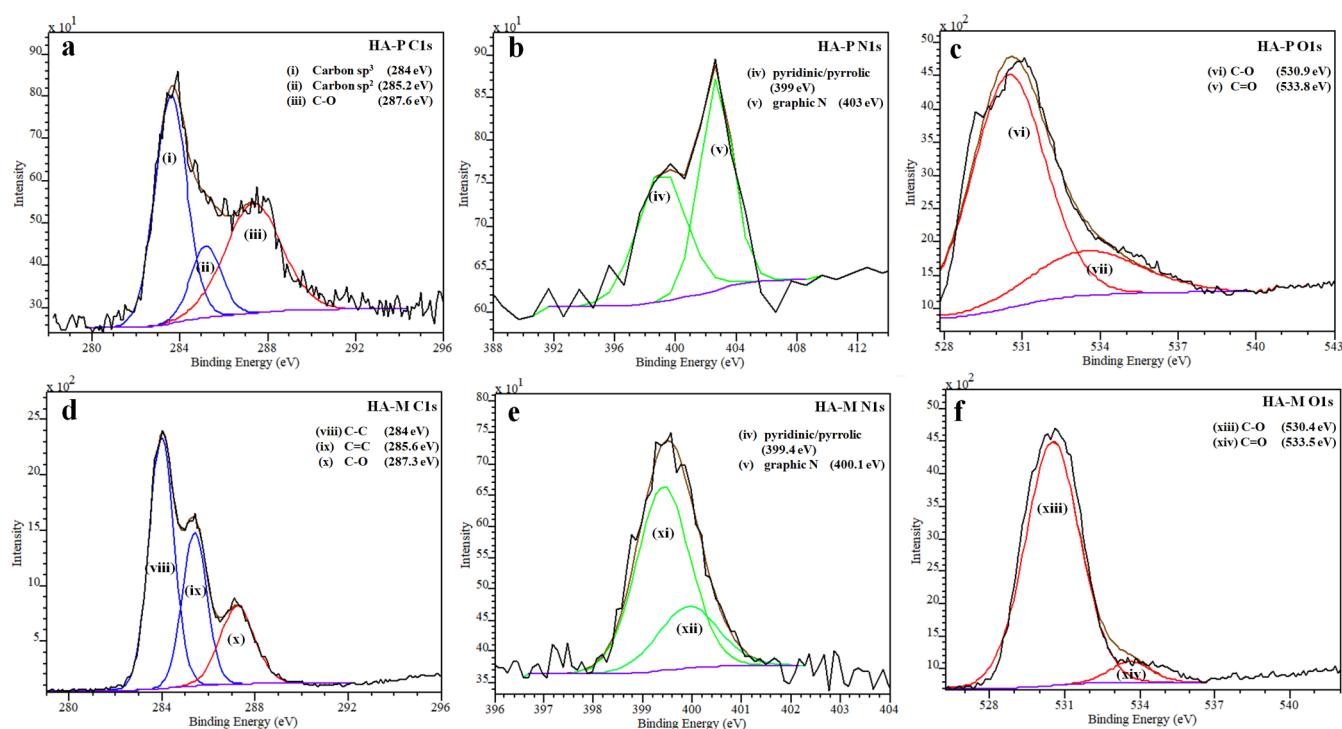

**Figure 4.** XPS spectra of microwave-assisted HA-M CDs: (a) C 1s, (b) N 1s, and (c) O 1s regions. XPS spectra of furnace-assisted HA-P CDs: (d) C 1s, (e) N 1s, and (f) O 1s regions.

HA-M2, HA-P1, and HA-P2,  $CC_{50}$  values are 1673, 54590, 2722, and 68587  $\mu\text{g}/\text{mL}$ , respectively. Based on the result, the obtained CDs can be safely used in vitro and potentially applied for in vivo bioimaging studies even at high concentrations.<sup>58</sup>

CLSM evaluation was used to further investigate the capabilities of CDs as in vitro bioimaging agents. The HeLa cells incubated with HA-M1, HA-M2, HA-P1, and HA-P2 show excellent green fluorescence around an excitation wavelength of 488 nm (Figure 7), which demonstrates the outstanding cell selectivity of HA CDs as well as consistency in surface binding and absorption of CDs by cells.<sup>59,60</sup> Furthermore, the z-stacking mode in CLSM was also used in proving CDs in the cell cytoplasm. From the data in Figure S4, Supporting Information, it can be observed that the accumulation of CDs in cells constitutes an active targeting package as well as an endocytosis process to make them exist in the cell cytoplasm. Thus, the result exhibits an excellent fluorescence imaging of CDs, which has remarkably high photostability and biocompatibility.

### 3. CONCLUSIONS


Herein, we have synthesized CDs from HA using microwave-assisted and furnace-assisted methods. The resulting CDs have excellent fluorescence properties, high photostability, and biocompatibility that possess the potential for bioimaging and anti-cancer effects. The result shows that HA-P2 has a higher value of QY and cell viability than the other CDs. Luminescence and biocompatibility properties of CDs were confirmed by CLSM on HeLa cells and the CCK-8 assay, respectively. Thus, the one-pot-synthesized HA-based CDs that target CD44 HeLa cancer cells could be a promising way to improve cancer treatments.

### 4. EXPERIMENTAL SECTION

**4.1. Materials.** HA (97%), sodium hydroxide (NaOH, 99.8%), hydrogen chloride (HCl, 37%), ethanol (99.5%), Dulbecco's modified Eagle's medium (DMEM, high glucose), fetal bovine serum (FBS), and phosphate buffered saline (PBS) were purchased from Sigma-Aldrich Inc. CCK-8 was purchased from MedChemExpress Ltd. All chemicals were used directly without any specific purification.

**4.2. Synthesis of CDs.** In the present study, CD synthesis was similar to that described in the latest work with some variations,<sup>36</sup> namely, microwave-assisted and furnace-assisted methods. In the microwave-assisted method, 10 mg of HA was added to 300  $\mu\text{L}$  of NaOH 0.1 N to form a dispersed solution. The mixture was stirred until a homogeneous and colorless gel was obtained. The mixture was then put into a microwave irradiation equipment (450 W) and continuously heated for 2 min (obtained CDs were marked HA-M1) and 2 h (obtained CDs were marked HA-M2). In the furnace-assisted method, about 10 mg of HA was heated at 270  $^{\circ}\text{C}$  for 2 min (obtained CDs were marked HA-P1) and 2 h (obtained CDs were marked HA-P2). Then, all CD products were purified by a dialysis process using a 1 kDa MWCO dialyzer (Orange Scientific) using deionized water for 24 h.

**4.3. Cytotoxicity Evaluation of CDs.** The breast cancer cells (HeLa cells) were seeded in a 96-well plate and cultured in DMEM (at a density of  $3 \times 10^4$  cells/ $\mu\text{L}$ ) containing 10% (v/v) FBS, 1% penicillin–streptomycin, and 1% 2 mM L-glutamine at 37  $^{\circ}\text{C}$  and 5%  $\text{CO}_2$ . After 24 h of incubation, the media were removed and washed three times with PBS. Then, carbon QDs were added to each well with varying concentrations, that is, 1, 2, 3, 5, 25, 100, and 400  $\mu\text{g}/\text{mL}$ . Untreated cells were used as a negative control by adding solvents only. Thereafter, the formazan crystal was formed by adding 10  $\mu\text{L}$  of the CCK-8 reagent to each well and

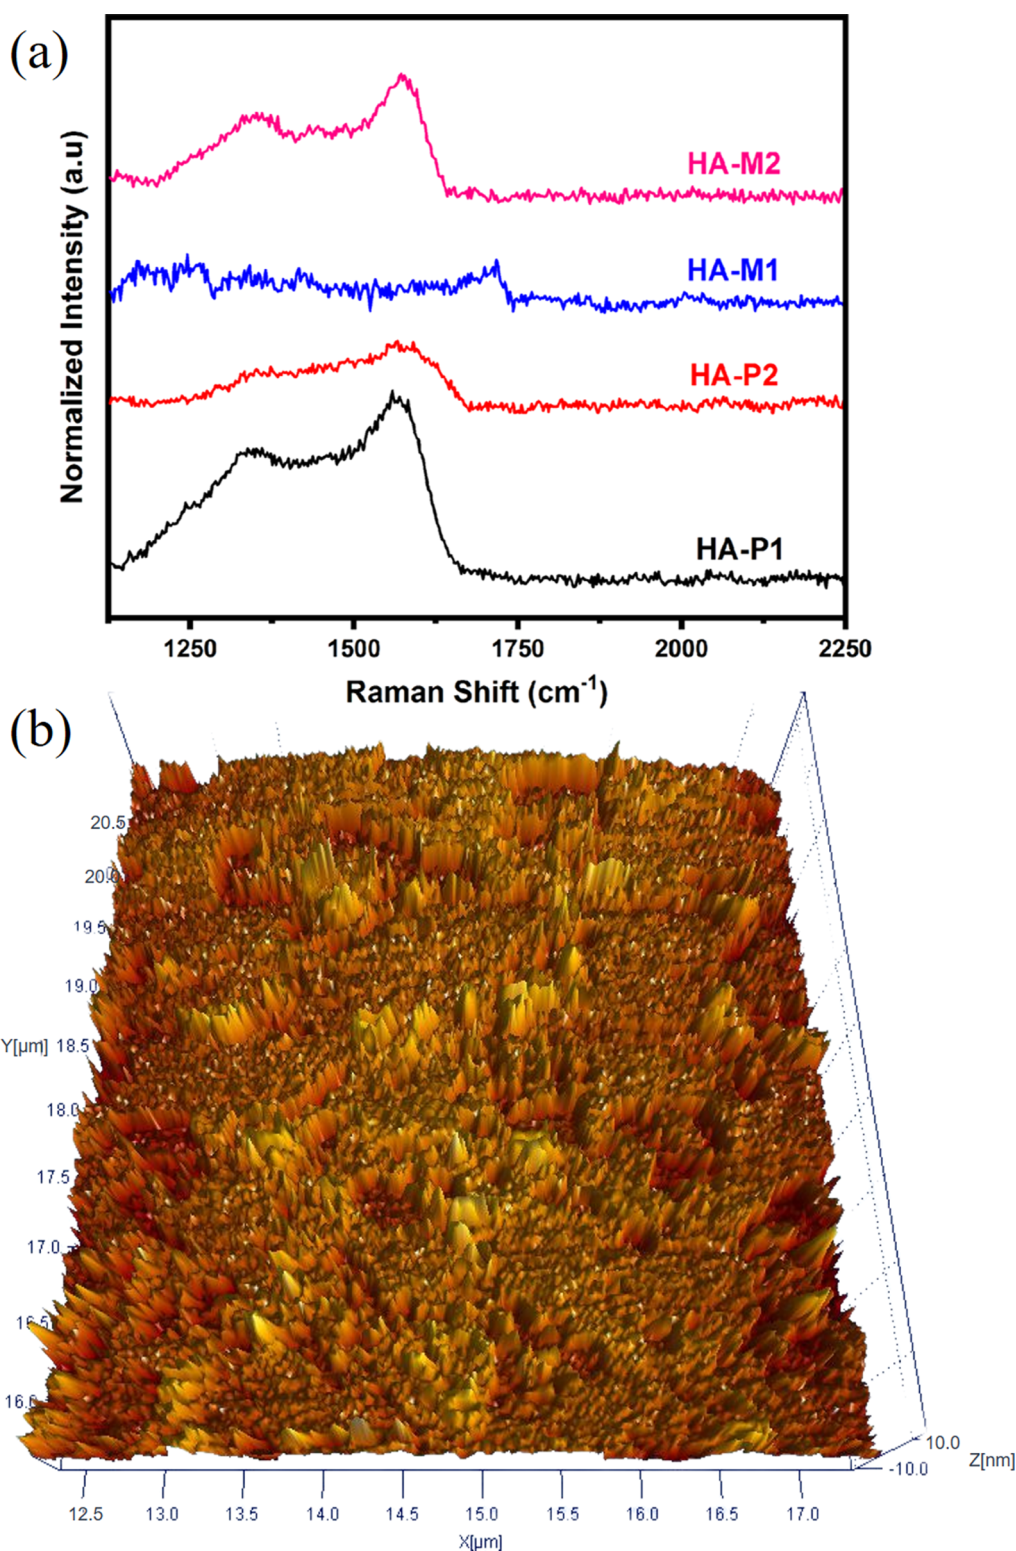


**Figure 5.** (a) Raman spectra of microwave-assisted CDs HA-M2 (purple line) and HA-M1 (blue line) and furnace-assisted CDs HA-P2 (red line) and HA-P1 (black line). (b) 3D topography of HA-P2.

incubating for 4 h. The reaction was stopped by adding a stopper reagent and then measuring the absorbance at 580 nm by an ELISA microplate reader.

**4.4. Confocal Microscopic Imaging.** The breast cancer cells (HeLa cells) were cultured by the CCK-8 assay (MedChemExpress, New Jersey, USA) in DMEM and incubated for 24 h. After that, they were incubated with CDs

for 60 min. HeLa cells were washed three times with PBS to remove uninterpretable nanoparticles and fixed with 70% alcohol for 10 min at room temperature. A confocal laser scanning microscope, TCS SP2 (Leica Microsystems, USA), was used to take the cell images at an excitation wavelength of 488 nm.

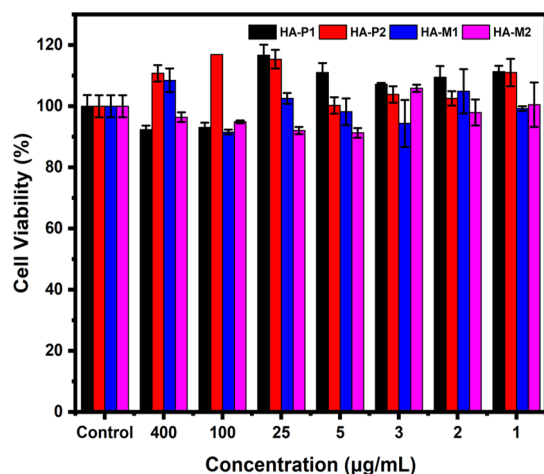

**Figure 6.** Varied concentrations of CDs HA-P1 (black bar), HA-P2 (red bar), HA-M1 (blue bar), and HA-M2 (purple bar). All data are represented as mean  $\pm$  SD with  $n = 3$ .

**4.5. Characterization.** An X-ray diffractometer [Ultima IV Rigaku, USA, 18 kW with the rotating anode source Cu  $K_{\alpha 1}$  line ( $\lambda = 1.54 \text{ \AA}$ )] was used to identify the crystal structure of CDs. Raman spectra [MRS-320 Raman Instrument system (Horiba Ltd, Japan)] identified the molecular interaction of CDs at an excitation wavelength of 532 nm. A Fourier transform infrared spectrophotometer [model IR Tracer-100 (Shimadzu, Japan)] was used to analyze the functional groups of CDs with the wavenumber ranging from 4000 to 400  $\text{cm}^{-1}$  using the potassium bromide (KBr) pellet technique. A X-ray photoelectron spectrometer [Escalab 250Xi spectrometer with an Al  $K\alpha$  radiation ( $h\nu = 1486.6 \text{ eV}$ )] determined the composition of CDs. A spectrofluorometer (FluoroMax-4) and a UV–vis spectrophotometer (Shimadzu UV-1800) were used to measure fluorescence and absorbance spectra, respectively. The PL of the HA CDs was measured comparatively by

referring to rhodamine 6G [R6G, QY (95%)]; the % QY of HA CDs was determined by the following equation

$$\text{QY} = \text{QY}_{\text{R6G}} \left( \frac{I_{\text{CDs}}}{I_{\text{R6G}}} \right) \left( \frac{A_{\text{CDs}}}{A_{\text{R6G}}} \right) \left( \frac{\eta_{\text{water}}}{\eta_{\text{ethanol}}} \right)^2$$

where  $I$ ,  $A$ , and  $\eta$  are the integral PL intensity, UV absorbance and the optical density, and solvent reflective index, respectively.

**4.6. Statistical Assessment.** The  $\text{CC}_{50}$  of CDs was determined using the dose–response model (nonlinear fitting) of the Origin software (version 8.0724, OriginLab Inc., Northampton, MA). All data were obtained in triplicate, with the sample  $t$ -test performed on some data.

## ■ ASSOCIATED CONTENT

### Supporting Information


The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsomega.1c01287>.

XRD diffractograms of HA-based CDs HA-M1, HA-M2, HA-P1, and HA-P2; AFM 2D morphology and size distribution of HA-P2; HeLa cancer cell viability curves after 24 h incubation for HA-M1, HA-M2, HA-P1, and HA-P2 using the microwave-assisted and furnace-assisted methods; CLSM images of HeLa cells using the  $z$ -stacking mode after 1 h treatment with HA-P2; and comparison of QY values of HA-based CDs (PDF)

## ■ AUTHOR INFORMATION

### Corresponding Author

Mochamad Z. Fahmi – Department of Chemistry and Supra Modification Nano-Micro Engineering Group, Universitas Airlangga, Surabaya 60115, Indonesia; [orcid.org/0000-0001-5430-9992](https://orcid.org/0000-0001-5430-9992); Email: [m.zakki.fahmi@fst.unair.ac.id](mailto:m.zakki.fahmi@fst.unair.ac.id)

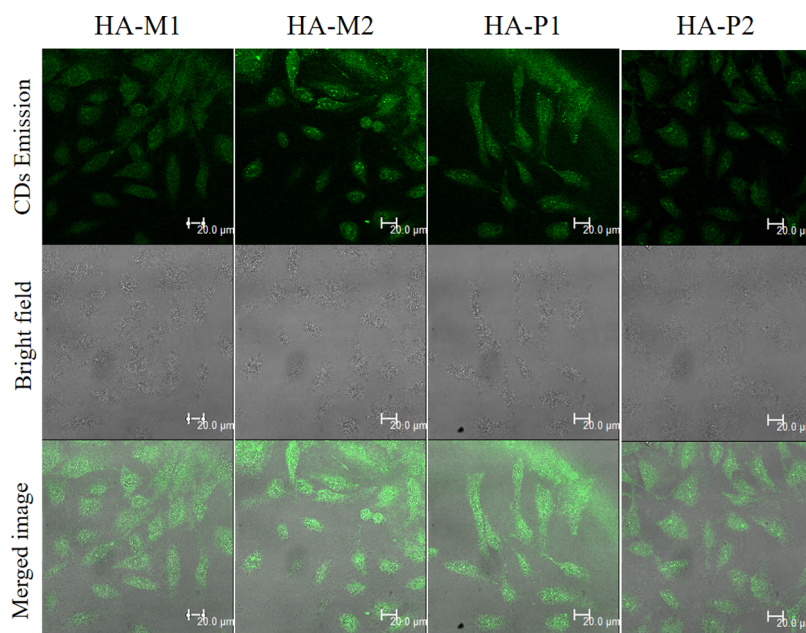

**Figure 7.** Photograph CLSM images of HeLa cells after 1 h incubation with HA-based CDs by excitation at 488 nm. The scale bars represent 20  $\mu\text{m}$ .



## Authors

Yu-Yu Aung – Department of Chemistry, Universitas Airlangga, Surabaya 60115, Indonesia; [orcid.org/0000-0002-2169-4983](https://orcid.org/0000-0002-2169-4983)

Aswandi Wibrianto – Department of Chemistry, Universitas Airlangga, Surabaya 60115, Indonesia; [orcid.org/0000-0002-7746-7405](https://orcid.org/0000-0002-7746-7405)

Jefry S. Sianturi – Department of Chemistry, Universitas Airlangga, Surabaya 60115, Indonesia

Desita K. Ulfa – Department of Chemistry, Universitas Airlangga, Surabaya 60115, Indonesia

Satya. C. W. Sakti – Department of Chemistry and Supra Modification Nano-Micro Engineering Group, Universitas Airlangga, Surabaya 60115, Indonesia

Irzaman Irzaman – Department of Physics, IPB University, Bogor 16680, Indonesia

Brian Yuliarto – Department of Engineering Physics, Faculty of Industrial Technology, Institut Teknologi Bandung, Bandung 40116, Indonesia; [orcid.org/0000-0003-0662-7923](https://orcid.org/0000-0003-0662-7923)

Jia-yaw Chang – Department of Chemical Engineering, National Taiwan University of Science and Technology, Taipei, Taiwan 10607, Republic of China; [orcid.org/0000-0002-4172-6612](https://orcid.org/0000-0002-4172-6612)

Yaung Kwee – Department of Chemistry, Universitas Airlangga, Surabaya 60115, Indonesia

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acsomega.1c01287>

## Notes

The authors declare no competing financial interest.

## ACKNOWLEDGMENTS

The authors thank the Ministry of Research and Technology of the Republic of Indonesia for their research support under contract no. 808/UN3.14/LT/2020 and Universitas Airlangga for research facilities.

## ABBREVIATIONS

CDs, carbon dots; QY, quantum yield; HA-P1, furnace-assisted carbon dots, 2 min; HA-P2, furnace-assisted carbon dots, 2 h; HA-M1, microwave-assisted carbon dots, 2 min; HA-M2, microwave-assisted carbon dots, 2 h; UV–vis, ultraviolet–visible light; PL, photoluminescence; FTIR, Fourier transform infrared; AFM, atomic force microscopy; CCK-8, cell counting kit 8; CLSM, confocal laser scanning microscopy; HA, hyaluronic acid; DMSO, dimethyl sulfoxide; NaOH, sodium hydroxide; C<sub>2</sub>H<sub>5</sub>OH, ethanol; DMEM, Dulbecco's modified Eagle medium; PBS, phosphate-buffered saline; CC<sub>50</sub>, 50% cytotoxic concentration; R6G, rhodamine 6G

## REFERENCES

- (1) Bray, F.; Ferlay, J.; Soerjomataram, I.; Siegel, R. L.; Torre, L. A.; Jemal, A. Global cancer statistics 2018: GLOBOCAN estimates of incidence and mortality worldwide for 36 cancers in 185 countries. *CA A Cancer J. Clin.* **2018**, *68*, 394–424.
- (2) IARC. *Latest global cancer data: Cancer burden rises to 18.1 million new cases and 9.6 million cancer deaths in 2018*; International Agency for Research on Cancer: Lyon, France, 2018.
- (3) Perumal, V.; Sivakumar, P. M.; Zarrabi, A.; Muthupandian, S.; Vijayaraghavalu, S.; Sahoo, K.; Das, A.; Das, S.; Payyappilly, S. S.; Das, S. Near infra-red polymeric nanoparticle based optical imaging in Cancer diagnosis. *J. Photochem. Photobiol., B* **2019**, *199*, 111630.
- (4) Papadimitriou, S. A.; Salinas, Y.; Resmini, M. Smart polymeric nanoparticles as emerging tools for imaging—the parallel evolution of materials. *Chem.—Eur. J.* **2016**, *22*, 3612–3620.
- (5) Fahmi, M. Z.; Chang, J.-Y. A facile strategy to enable nanoparticles for simultaneous phase transfer, folate receptor targeting, and cisplatin delivery. *RSC Adv.* **2014**, *4*, 56713–56721.
- (6) Xu, X.; Lü, S.; Gao, C.; Wang, X.; Bai, X.; Gao, N.; Liu, M. Facile preparation of pH-sensitive and self-fluorescent mesoporous silica nanoparticles modified with PAMAM dendrimers for label-free imaging and drug delivery. *Chem. Eng. J.* **2015**, *266*, 171–178.
- (7) Ghosh, D.; Bagley, A. F.; Na, Y. J.; Birrer, M. J.; Bhatia, S. N.; Belcher, A. M. Deep, noninvasive imaging and surgical guidance of submillimeter tumors using targeted M13-stabilized single-walled carbon nanotubes. *Proc. Natl. Acad. Sci. U.S.A.* **2014**, *111*, 13948–13953.
- (8) Man, H. B.; Kim, H.; Kim, H.-J.; Robinson, E.; Liu, W. K.; Chow, E. K.-H.; Ho, D. Synthesis of nanodiamond–daunorubicin conjugates to overcome multidrug chemoresistance in leukemia. *Nanomed. Nanotechnol. Biol. Med.* **2014**, *10*, 359–369.
- (9) Wegner, K. D.; Hildebrandt, N. Quantum dots: bright and versatile in vitro and in vivo fluorescence imaging biosensors. *Chem. Soc. Rev.* **2015**, *44*, 4792–4834.
- (10) Saeed, A. A.; Sánchez, J. L. A.; O'Sullivan, C. K.; Abbas, M. N. DNA biosensors based on gold nanoparticles-modified graphene oxide for the detection of breast cancer biomarkers for early diagnosis. *Bioelectrochemistry* **2017**, *118*, 91–99.
- (11) More, M. P.; Lohar, P. H.; Patil, A. G.; Patil, P. O.; Deshmukh, P. K. Controlled synthesis of blue luminescent graphene quantum dots from carbonized citric acid: Assessment of methodology, stability, and fluorescence in an aqueous environment. *Mater. Chem. Phys.* **2018**, *220*, 11–22.
- (12) de Medeiros, T. V.; Manioudakis, J.; Noun, F.; Macairan, J.-R.; Victoria, F.; Naccache, R. Microwave-assisted synthesis of carbon dots and their applications. *J. Mater. Chem. C* **2019**, *7*, 7175–7195.
- (13) Molaei, M. J. Carbon quantum dots and their biomedical and therapeutic applications: a review. *RSC Adv.* **2019**, *9*, 6460–6481.
- (14) Wang, X.; Gao, T.; Yang, M.; Zhao, J.; Jiang, F.-L.; Liu, Y. Microwave-assisted synthesis, characterization, cell imaging of fluorescent carbon dots using L-asparagine as precursor. *New J. Chem.* **2019**, *43*, 3323–3331.
- (15) Hill, S.; Galan, M. C. Fluorescent carbon dots from mono- and polysaccharides: synthesis, properties and applications. *Beilstein J. Org. Chem.* **2017**, *13*, 675–693.
- (16) Shang, W.; Cai, T.; Zhang, Y.; Liu, D.; Liu, S. Facile one pot pyrolysis synthesis of carbon quantum dots and graphene oxide nanomaterials: all carbon hybrids as eco-environmental lubricants for low friction and remarkable wear-resistance. *Tribol. Int.* **2018**, *118*, 373–380.
- (17) Choi, E. J.; Lee, J. M.; Youn, Y. S.; Na, K.; Lee, E. S. Hyaluronate dots for highly efficient photodynamic therapy. *Carbohydr. Polym.* **2018**, *181*, 10–18.
- (18) Bukhari, S. N. A.; Roswandi, N. L.; Waqas, M.; Habib, H.; Hussain, F.; Khan, S.; Sohail, M.; Ramli, N. A.; Thu, H. E.; Hussain, Z. Hyaluronic acid, a promising skin rejuvenating biomedicine: A review of recent updates and pre-clinical and clinical investigations on cosmetic and nutraceutical effects. *Int. J. Biol. Macromol.* **2018**, *120*, 1682–1695.
- (19) Su, H.; Wang, J.; Yan, L. Homogeneously Synchronous Degradation of Chitin into Carbon Dots and Organic Acids in Aqueous Solution. *ACS Sustainable Chem. Eng.* **2019**, *7*, 18476–18482.
- (20) Demir, B.; Lemberger, M. M.; Panagiotopoulou, M.; Medina Rangel, P. X.; Timur, S.; Hirsch, T.; Tse Sum Bui, B.; Wegener, J.; Haupt, K. Tracking hyaluronan: molecularly imprinted polymer coated carbon dots for cancer cell targeting and imaging. *ACS Appl. Mater. Interfaces* **2018**, *10*, 3305–3313.
- (21) Tripodo, G.; Trapani, A.; Torre, M. L.; Giammona, G.; Trapani, G.; Mandracchia, D. Hyaluronic acid and its derivatives in

- drug delivery and imaging: recent advances and challenges. *Eur. J. Pharm. Biopharm.* **2015**, *97*, 400–416.
- (22) Wickens, J. M.; Alsaab, H. O.; Kesharwani, P.; Bhise, K.; Amin, M. C. I. M.; Tekade, R. K.; Gupta, U.; Iyer, A. K. Recent advances in hyaluronic acid-decorated nanocarriers for targeted cancer therapy. *Drug Discov. Today* **2017**, *22*, 665–680.
- (23) Xu, X.; Ray, R.; Gu, Y.; Ploehn, H. J.; Gearheart, L.; Raker, K.; Scrivens, W. A. Electrophoretic analysis and purification of fluorescent single-walled carbon nanotube fragments. *J. Agron. Crop Sci.* **2004**, *126*, 12736–12737.
- (24) Bottini, M.; Balasubramanian, C.; Dawson, M. I.; Bergamaschi, A.; Bellucci, S.; Mustelin, T. Isolation and characterization of fluorescent nanoparticles from pristine and oxidized electric arc-produced single-walled carbon nanotubes. *J. Phys. Chem. B* **2006**, *110*, 831–836.
- (25) Sun, Y.-P.; Zhou, B.; Lin, Y.; Wang, W.; Fernando, K. A. S.; Pathak, P.; Meziani, M. J.; Harruff, B. A.; Wang, X.; Wang, H.; Luo, P. G.; Yang, H.; Kose, M. E.; Chen, B.; Veca, L. M.; Xie, S.-Y. Quantum-sized carbon dots for bright and colorful photoluminescence. *J. Agron. Crop Sci.* **2006**, *128*, 7756–7757.
- (26) Zhao, Q.-L.; Zhang, Z.-L.; Huang, B.-H.; Peng, J.; Zhang, M.; Pang, D.-W. Facile preparation of low cytotoxicity fluorescent carbon nanocrystals by electrooxidation of graphite. *Chem. Commun.* **2008**, *41*, 5116–5118.
- (27) Zheng, L.; Chi, Y.; Dong, Y.; Lin, J.; Wang, B. Electrochemiluminescence of water-soluble carbon nanocrystals released electrochemically from graphite. *J. Agron. Crop Sci.* **2009**, *131*, 4564–4565.
- (28) Wei, K.; Li, J.; Ge, Z.; You, Y.; Xu, H. Sonochemical synthesis of highly photoluminescent carbon nanodots. *RSC Adv.* **2014**, *4*, 52230–52234.
- (29) Krysmann, M. J.; Kelarakis, A.; Dallas, P.; Giannelis, E. P. Formation mechanism of carbogenic nanoparticles with dual photoluminescence emission. *J. Agron. Crop Sci.* **2012**, *134*, 747–750.
- (30) Sahu, S.; Behera, B.; Maiti, T. K.; Mohapatra, S. Simple one-step synthesis of highly luminescent carbon dots from orange juice: application as excellent bio-imaging agents. *Chem. Commun.* **2012**, *48*, 8835–8837.
- (31) Gallo-Cordova, Á.; Espinosa, A.; Serrano, A.; Gutiérrez, L.; Menéndez, N.; del Puerto Morales, M.; Mazarío, E. New insights into the structural analysis of maghemite and (MFe<sub>2</sub>O<sub>4</sub>, M = Co, Zn) ferrite nanoparticles synthesized by a microwave-assisted polyol process. *Mater. Chem. Front.* **2020**, *4*, 3063–3073.
- (32) Li, J.; Li, M.; Tian, L.; Qiu, Y.; Yu, Q.; Wang, X.; Guo, R.; He, Q. Facile strategy by hyaluronic acid functional carbon dot-doxorubicin nanoparticles for CD44 targeted drug delivery and enhanced breast cancer therapy. *Int. J. Pharm.* **2020**, *578*, 119122.
- (33) Wang, H.-J.; Zhang, J.; Liu, Y.-H.; Luo, T.-Y.; He, X.; Yu, X.-Q. Hyaluronic acid-based carbon dots for efficient gene delivery and cell imaging. *RSC Adv.* **2017**, *7*, 15613–15624.
- (34) Zhang, L.; Lin, Z.; Yu, Y.-X.; Jiang, B.-P.; Shen, X.-C. Multifunctional hyaluronic acid-derived carbon dots for self-targeted imaging-guided photodynamic therapy. *J. Mater. Chem. B* **2018**, *6*, 6534–6543.
- (35) Qu, D.; Zheng, M.; Zhang, L.; Zhao, H.; Xie, Z.; Jing, X.; Haddad, R. E.; Fan, H.; Sun, Z. Formation mechanism and optimization of highly luminescent N-doped graphene quantum dots. *Sci. Rep.* **2014**, *4*, 1–11.
- (36) Wibrianto, A.; Khairunisa, S. Q.; Sakti, S. C. W.; Ni'mah, Y. L.; Purwanto, B.; Fahmi, M. Z. Comparison of the effects of synthesis methods of B, N, S, and P-doped carbon dots with high photoluminescence properties on HeLa tumor cells. *RSC Adv.* **2021**, *11*, 1098–1108.
- (37) Wang, B.-B.; Jin, J.-C.; Xu, Z.-Q.; Jiang, Z.-W.; Li, X.; Jiang, F.-L.; Liu, Y. Single-step synthesis of highly photoluminescent carbon dots for rapid detection of Hg<sup>2+</sup> with excellent sensitivity. *J. Colloid Interface Sci.* **2019**, *551*, 101–110.
- (38) Wu, Z. L.; Liu, Z. X.; Yuan, Y. H. Carbon dots: materials, synthesis, properties and approaches to long-wavelength and multi-color emission. *J. Mater. Chem. B* **2017**, *5*, 3794–3809.
- (39) Bhartiya, P.; Singh, A.; Kumar, H.; Jain, T.; Singh, B. K.; Dutta, P. Carbon dots: Chemistry, properties and applications. *J. Indian Chem. Soc.* **2016**, *93*, 759–766.
- (40) Lawson-wood, K.; Upstone, S.; Evans, K. Determination of Relative Fluorescence Quantum Yields using the FL6500 Fluorescence Spectrometer. *Fluorescence Spectroscopy*; PerkinElmer Inc.: Seer Green, U.K., 2018.
- (41) Fang, Q.; Dong, Y.; Chen, Y.; Lu, C.-H.; Chi, Y.; Yang, H.-H.; Yu, T. Luminescence origin of carbon based dots obtained from citric acid and amino group-containing molecules. *Carbon* **2017**, *118*, 319–326.
- (42) Pudza, M. Y.; Abidin, Z. Z.; Abdul-Rashid, S.; Yassin, F. M.; Noor, A. S. M.; Abdullah, M. Synthesis and Characterization of Fluorescent Carbon Dots from Tapioca. *ChemistrySelect* **2019**, *4*, 4140–4146.
- (43) Huang, J. J.; Zhong, Z. F.; Rong, M. Z.; Zhou, X.; Chen, X. D.; Zhang, M. Q. An easy approach of preparing strongly luminescent carbon dots and their polymer based composites for enhancing solar cell efficiency. *Carbon* **2014**, *70*, 190–198.
- (44) Thakur, M.; Mewada, A.; Pandey, S.; Bhoori, M.; Singh, K.; Sharon, M.; Sharon, M. Milk-derived multi-fluorescent graphene quantum dot-based cancer theranostic system. *Mater. Sci. Eng. C* **2016**, *67*, 468–477.
- (45) Xu, D.; Lei, F.; Chen, H.; Yin, L.; Shi, Y.; Xie, J. One-step hydrothermal synthesis and optical properties of self-quenching-resistant carbon dots towards fluorescent ink and as nanosensors for Fe<sup>3+</sup> detection. *RSC Adv.* **2019**, *9*, 8290–8299.
- (46) Fahmi, M. Z.; Haris, A.; Permana, A. J.; Nor Wibowo, D. L.; Purwanto, B.; Nikmah, Y. L.; Idris, A. Bamboo leaf-based carbon dots for efficient tumor imaging and therapy. *RSC Adv.* **2018**, *8*, 38376–38383.
- (47) Prasannan, A.; Imae, T. One-pot synthesis of fluorescent carbon dots from orange waste peels. *Ind. Eng. Chem. Res.* **2013**, *52*, 15673–15678.
- (48) Aung, Y. Y.; Kristanti, A. N.; Khairunisa, S. Q.; Nasronudin, N.; Fahmi, M. Z. Inactivation of HIV-1 Infection through Integrative Blocking with Amino Phenylboronic Acid Attributed Carbon Dots. *ACS Biomater. Sci. Eng.* **2020**, *6*, 4490–4501.
- (49) Mathew, S. A.; Praveena, P.; Dhanavel, S.; Manikandan, R.; Senthilkumar, S.; Stephen, A. Luminescent chitosan/carbon dots as an effective nano-drug carrier for neurodegenerative diseases. *RSC Adv.* **2020**, *10*, 24386–24396.
- (50) Stepanidenko, E. A.; Arefina, I. A.; Khavlyuk, P. D.; Dubavik, A.; Bogdanov, K. V.; Bondarenko, D. P.; Cherevko, S. A.; Kundelev, E. V.; Fedorov, A. V.; Baranov, A. V.; Maslov, V. G.; Ushakova, E. V.; Rogach, A. L. Influence of the solvent environment on luminescent centers within carbon dots. *Nanoscale* **2020**, *12*, 602–609.
- (51) Zafar, Z.; Ni, Z. H.; Wu, X.; Shi, Z. X.; Nan, H. Y.; Bai, J.; Sun, L. T. Evolution of Raman spectra in nitrogen doped graphene. *Carbon* **2013**, *61*, 57–62.
- (52) Kütahya, C.; Wang, P.; Li, S.; Liu, S.; Li, J.; Chen, Z.; Strehmel, B. Carbon dots as a promising green photocatalyst for free radical and ATRP-based radical photopolymerization with blue LEDs. *Angew. Chem., Int. Ed.* **2020**, *59*, 3166–3171.
- (53) Zhang, Z.; Yi, G.; Li, P.; Zhang, X.; Fan, H.; Zhang, Y.; Wang, X.; Zhang, C. A minireview on doped carbon dots for photocatalytic and electrocatalytic applications. *Nanoscale* **2020**, *12*, 13899–13906.
- (54) Wang, H.; Cao, J.; Zhou, Y.; Wang, Z.; Zhao, Y.; Liu, Y.; Huang, H.; Shao, M.; Liu, Y.; Kang, Z. Carbon dot-modified mesoporous carbon as a supercapacitor with enhanced light-assisted capacitance. *Nanoscale* **2020**, *12*, 17925–17930.
- (55) Ansari, M. A.; Pedergnana, V.; Pedergnana, V.; L C Ip, C.; Magri, A.; Von Delft, A.; Bonsall, D.; Chaturvedi, N.; Bartha, I.; Smith, D.; Nicholson, G.; McVean, G.; Trebes, A.; Piazza, P.; Fellay, J.; Cooke, G.; Foster, G. R.; Hudson, E.; McLauchlan, J.; Simmonds, P.; Bowden, R.; Klenerman, P.; Barnes, E.; Spencer, C. C. A. Genome-

to-genome analysis highlights the effect of the human innate and adaptive immune systems on the hepatitis C virus. *Nat. Genet.* **2017**, *49*, 666.

(56) Capáková, Z.; Radaszkiewicz, K. A.; Acharya, U.; Truong, T. H.; Pacherník, J.; Bober, P.; Kašpárková, V.; Stejskal, J.; Pflieger, J.; Lehocký, M.; Humpolíček, P. The biocompatibility of polyaniline and polypyrrole 2: Doping with organic phosphonates. *Mater. Sci. Eng. C* **2020**, *113*, 110986.

(57) Kanagasubbakshmi, S.; Lakshmi, K.; Kadirvelu, K. Carbon quantum dots-embedded electrospun antimicrobial and fluorescent scaffold for reepithelialization in albino wistar rats. *J. Biomed. Mater. Res.* **2020**, *109*, 637.

(58) Shen, J.; Zhu, Y.; Yang, X.; Li, C. Graphene quantum dots: emergent nanolights for bioimaging, sensors, catalysis and photo-voltaic devices. *Chem. Commun.* **2012**, *48*, 3686–3699.

(59) Wang, Z.; Tian, Y.; Zhang, H.; Qin, Y.; Li, D.; Gan, L.; Wu, F. Using hyaluronic acid-functionalized pH stimuli-responsive mesoporous silica nanoparticles for targeted delivery to CD44-over-expressing cancer cells. *Int. J. Nanomed.* **2016**, *11*, 6485.

(60) Yu, M.; Jambhrunkar, S.; Thorn, P.; Chen, J.; Gu, W.; Yu, C. Hyaluronic acid modified mesoporous silica nanoparticles for targeted drug delivery to CD44-overexpressing cancer cells. *Nanoscale* **2013**, *5*, 178–183.

**COVID-19 Remote Access Support:** [Learn More](#) about expanded access to ACS Publications research.



[Open Access](#)  
[Submission & Review](#)  
[About the Journal](#)

## Editors & Editorial Board

### Editors-in-Chief

#### **Krishna N. Ganesh**

Indian Institute of Science Education & Research

India

E-mail: [ganesh-office@omega.acs.org](mailto:ganesh-office@omega.acs.org)

#### **Deqing Zhang**

Institute of Chemistry, Chinese Academy of Sciences

China

E-mail: [zhang-office@omega.acs.org](mailto:zhang-office@omega.acs.org)

### Current Issue Editorial Masthead

[View the Masthead in Current Issue](#)

### Senior Editors

#### **Sarbajit Banerjee**

Texas A&M University  
United States

E-mail: [Banerjee-office@omega.acs.org](mailto:Banerjee-office@omega.acs.org)

#### **Frank H. Quina**

Universidade de São Paulo  
Brazil

E-mail: [quina-office@omega.acs.org](mailto:quina-office@omega.acs.org)

### Associate Editors

#### **Esra Çapanoğlu Güven**

Istanbul Technical University  
Turkey

E-mail: [Capanoglu-office@omega.acs.org](mailto:Capanoglu-office@omega.acs.org)

#### **Shaojun Guo**

Peking University, China  
China

E-mail: [guo-office@omega.acs.org](mailto:guo-office@omega.acs.org)

Email: [tokens-office@omega.acs.org](mailto:tokens-office@omega.acs.org)

**Jesús Jiménez-Barbero**

CIC bioGUNE  
Spain  
E-mail: [jimenez-barbero-office@omega.acs.org](mailto:jimenez-barbero-office@omega.acs.org)

**Jeehiun K. Lee**

Rutgers University  
United States  
E-mail: [lee-office@omega.acs.org](mailto:lee-office@omega.acs.org)

**Mohamed Mahmoud**

King Fahd University of Petroleum & Minerals  
Saudi Arabia  
E-mail: [mahmoud-office@omega.acs.org](mailto:mahmoud-office@omega.acs.org)

Email: [ogoshi-office@omega.acs.org](mailto:ogoshi-office@omega.acs.org)

**Luisa Torsi**

Università Degli Studi Di Bari  
Italy  
E-mail: [torsi-office@omega.acs.org](mailto:torsi-office@omega.acs.org)

**Adelina Voutchkova-Kostal**

George Washington University  
United States  
E-mail: [voutchkova-kostal-office@omega.acs.org](mailto:voutchkova-kostal-office@omega.acs.org)

**Jing-Lin Zuo**

Nanjing University  
China  
E-mail: [zuo-office@omega.acs.org](mailto:zuo-office@omega.acs.org)

## Senior Managing Editor

**Dinesh Soares**

E-mail: [managing.editor@omega.acs.org](mailto:managing.editor@omega.acs.org)

## Editorial Advisory Board

**Ayyappanpillai Ajayaghosh**

CSIR–National Institute for Interdisciplinary  
Science and Technology  
India

**Nageh Allam**

The American University in Cairo  
Egypt

**Markus Antonietti**

Max Planck Institute of Colloids and  
Interfaces  
Germany

**Jürgen Bajorath**

University of Bonn  
Germany

**Damià Barceló**

Catalan Institute for Water Research (ICRA)  
Spain

**Suddhasatwa Basu**

Indian Institute of Technology Delhi  
India

**Heloisa Beraldo**

Universidade Federal de Minas Gerais  
Brazil

**Parbati Biswas**

University of Delhi  
India

**Maria Valnice Boldrin Zanoni**

Universidade Estadual Paulista  
Brazil

**Luis M. Campos**

Columbia University  
United States

**Nagasuma Chandra**

Indian Institute of Science  
India

**Vadapalli Chandrasekhar**

Indian Institute of Technology Kanpur  
India

**Dipankar Chatterji**

Indian Institute of Science  
India

**Yu-Ju Chen**

Academia Sinica  
Taiwan

**Cathleen Crudden**

Queen's University  
Canada

**Swagata Dasgupta**

Indian Institute of Technology Kharagpur  
India

**Jyotirmayee Dash**

Indian Association for the Cultivation of  
Science  
India

**Beatriz Garcia de la Torre**

University of KwaZulu-Natal  
South Africa

**Nicoletta Ditaranto**

Università degli Studi di Bari Aldo Moro  
Italy

**Takayuki Doi**

Tohoku University  
Japan

**Qing-Hua Fan**

Institute of Chemistry, Chinese Academy of  
Sciences  
China

**Rute A. S. Ferreira**

University of Aveiro  
Portugal

**Mary Garson**

University of Queensland  
Australia

**Mónica C. Gonzalez**

Universidad Nacional de La Plata  
Argentina

**Concepción González-Bello**

Universidade de Santiago de Compostela  
Spain

**Murray R. Gray**

University of Alberta  
Canada

**Xuefeng Guo**

Peking University  
China

**Jennifer M. Heemstra**

Emory University  
United States

**Thomas Hellweg**

Bielefeld University  
Germany

**Qingrong Huang**

Rutgers University  
United States

**Albena Ivanisevic**

North Carolina State University  
United States

**Katrina A. Jolliffe**

The University of Sydney  
Australia

**Beatriz H. Juárez**

Universidad Autónoma de Madrid  
Spain

**Tanja Junkers**

Monash University  
Australia

**Lynn Kamerlin**

Uppsala University  
Sweden

**Niveen Khashab**

King Abdullah University of Science and  
Technology (KAUST)  
Saudi Arabia

**Katalin E. Kövér**

University of Debrecen  
Hungary

**Elizabeth Krenske**

The University of Queensland  
Australia

**Yamuna Krishnan**

University of Chicago  
United States

**Nitin K. Labhsetwar**

CSIR–National Environmental Engineering  
Research Institute  
India

**Hye Jin Lee**

Kyungpook National University  
Republic of Korea

**Angel Leiva Campusano**

Pontificia Universidad Católica de Chile  
Chile

**Zhen Li**

Wuhan University  
China

**Darren Lipomi**

University of California, San Diego  
United States

**Lei Liu**

Tsinghua University  
China

**Watson Loh**

UNICAMP Universidade Estadual de  
Campinas  
Brazil

**Katja Loos**

University of Groningen  
Netherlands

**Norberto Peporine Lopes**

University of São Paulo  
Brazil

**Lanqun Mao**

Institute of Chemistry, Chinese Academy of  
Sciences  
China

**José Luis Mascareñas**

Universidad de Santiago  
Spain

**Manjusri Misra**

University of Guelph  
Canada

**Maria Cruz Moreno Bondi**

Complutense University of Madrid  
Spain

**Claudio J.A. Mota**

Federal University of Rio de Janeiro  
Brazil

**Daniel H. Murgida**

University of Buenos Aires and CONICET  
Argentina

**Maria Nowakowska**

Jagiellonian University  
Poland

**Cátia Ornelas**

UNICAMP Universidade Estadual de  
Campinas  
Brazil

**Takeaki Ozawa**

The University of Tokyo  
Japan

**Sofia I. Pascu**

University of Bath  
United Kingdom

**Suprakas Sinha Ray**

Council for Scientific and Industrial Research  
South Africa

**Coralía Osorio Roa**

Universidad Nacional de Colombia  
Colombia

**Carme Rovira-Virgili**

Universitat de Barcelona  
Spain

**Paolo Samori**

University of Strasbourg & The National  
Center for Scientific Research  
France

**Clément Sanchez**

Collège de France  
France

**Anubhav Saxena**

Pidilite Industries Limited  
India

**Tamar Seideman**

Northwestern University  
United States

**Alba Silipo**

Università degli Studi di Napoli "Federico II"  
Italy

**Svetlana Simova**

Bulgarian Academy of Sciences  
Bulgaria

**Jayant Singh**

Indian Institute of Technology Kanpur  
India

**Ekaterina V. Skorb**

ITMO University  
Russian Federation

**Miquel Solà**

Universitat de Girona  
Spain

**Christopher Southan**

TW2Informatics Ltd  
United Kingdom

**Eleni Stavrinidou**

Linköping University  
Sweden

**Sabine Szunerits**

Université de Lille  
France

**Kazuo Takimiya**

RIKEN  
Japan

**Keiichi Tomishige**

Tohoku University  
Japan

**Ilja K. Voets**

Eindhoven University of Technology  
Netherlands



Germany

**Li-Jun Wan**

Institute of Chemistry Chinese Academy of Sciences  
China

**Yilin Wang**

Institute of Chemistry Chinese Academy of Sciences  
China

**Shu Wang**

Institute of Chemistry Chinese Academy of Sciences  
China

**Davita L. Watkins**

University of Mississippi  
United States

**Robert S. Weber**

Pacific Northwest National Laboratory  
United States

**Tanja Weil**

Max Planck Institute for Polymer Research  
Germany

**Emily A. Weiss**

Northwestern University  
United States

**Luisa Whittaker-Brooks**

University of Utah  
United States

**Jishan Wu**

National University of Singapore  
Singapore

**Li-Zhu Wu**

Chinese Academy of Sciences  
China

**Matthias Wüst**

University of Bonn  
Germany

**Zhenfeng Xi**

Peking University  
China

**Vivian W. W. Yam**

The University of Hong Kong  
China

**Juyoung Yoon**

Ewha Womans University  
Republic of Korea

**Hua Zhang**

City University of Hong Kong  
China

**Xi Zhang**

Tsinghua University  
China



1155 Sixteenth Street N.W.  
Washington, DC 20036  
Copyright © 2021  
American Chemical Society

## About

About ACS Publications  
ACS & Open Access  
ACS Membership

## Resources and Information


Journals A-Z  
Books and Reference  
Advertising Media Kit  
Institutional Sales  
ACS Publishing Center  
Privacy Policy  
Terms of Use

## Support & Contact

Help  
Live Chat  
FAQ

Connect with ACS Publications



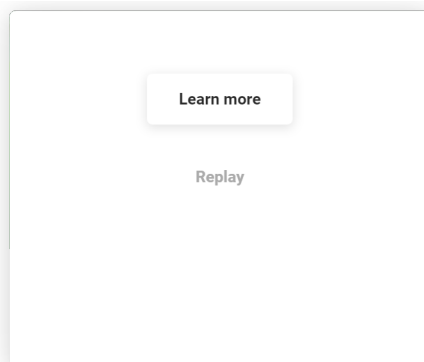


## ACS Omega

### COUNTRY

United States

 Universities and research institutions in United States

### SUBJECT AREA AND CATEGORY

Chemical Engineering  
Chemical Engineering (miscellaneous)  
Chemistry  
Chemistry (miscellaneous)

### PUBLISHER

American Chemical Society

 American Chemical Society in Scimago Institutions Rankings

### H-INDEX

40

### PUBLICATION TYPE

Journals

### ISSN

24701343

### COVERAGE

2016-2020

### INFORMATION

[Homepage](#)  
[How to publish in this journal](#)  
[Ganesh-office@omega.acs.org](mailto:Ganesh-office@omega.acs.org)

 PESAN SEBELUM 30 :  
**DISKON 33**  
+ KEBEBASAN UNTUK ME  
TANGGAL MENGINAP /  
Jika Anda memesan dengan Maste  
Anggota Accor Plus mendapatkan diskon t  
Berlaku untuk menginap sampai 31 Des  
[PESAN SEKARANG](#)  
 ACCOR  
LIVE  
LIMITLESS  
\*Syarat

## SCOPE

ACS Omega is an open-access global publication for scientific articles that describe new findings in chemistry and interfacing areas of science, without any perceived evaluation of immediate impact. ACS Omega is a global open-access journal for the publication of scientific articles that describe new findings in chemistry and interfacing areas of science, without any perceived evaluation of immediate impact. Articles in ACS Omega should advance the frontiers of science through original ideas, even if the full significance is not known. ACS Omega disseminates this knowledge globally and quickly by immediately making all accepted articles open access in perpetuity. Papers published in ACS Omega are therefore available to a much wider readership that includes industry, policy institutions, the media and the general public, in addition to the traditional academic sector.

Join the conversation about this journal

Quartiles

## FIND SIMILAR JOURNALS ?

1  
**Frontiers in Chemistry**

CHE

**94%**  
similarity

2  
**RSC Advances**

GBR

**88%**  
similarity

3  
**Progress in Chemistry**

CHN


**81%**  
similarity

4  
**New Journa**

GBR


**7**  
s

SJR

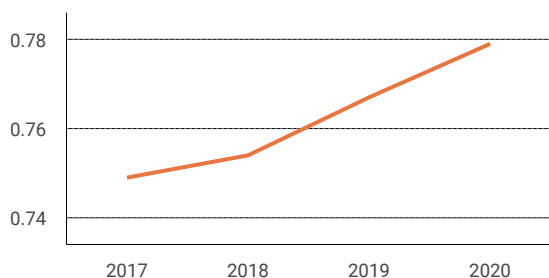


Citations per document


Total Cites    Self-Cites

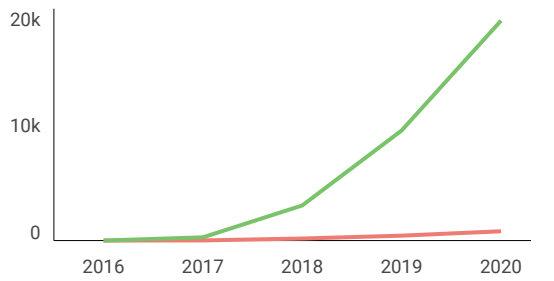


External Cites per Doc Cites per Doc

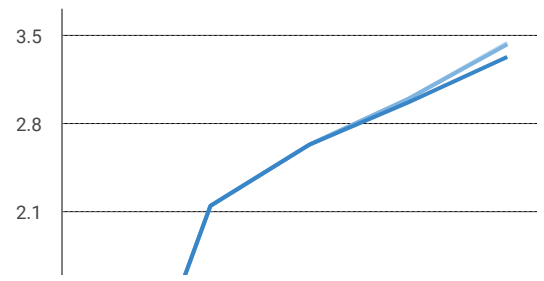



% International Collaboration

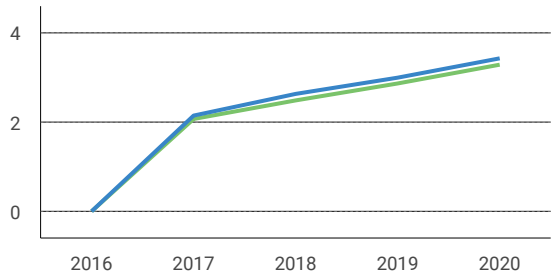

Citable documents Non-citable documents

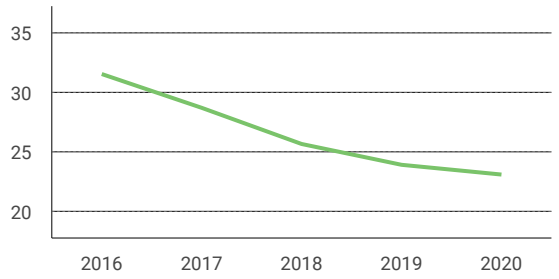

Cited documents Uncited documents

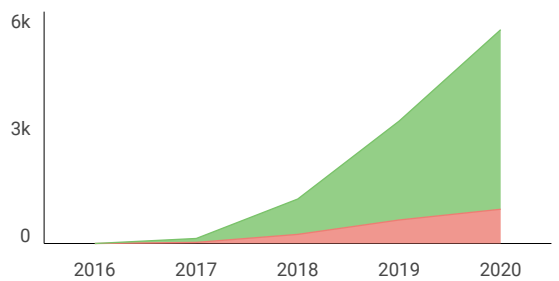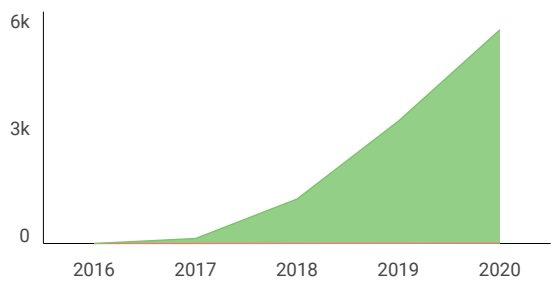

**ACS Omega**

**Q1** Chemical Engineering (miscellaneous) best quartile

**SJR 2020** 0.78

powered by scimagojr.com

← Show this widget in your own website

Just copy the code below and paste within your html code:

```
<a href="https://www.scimaç"
```

---

## Fahmi, Mochamad ao-2021-012873 - Manuscript Submission to ACS Omega 10-Mar-2021

1 message

---

ACS Omega <onbehalf@manuscriptcentral.com>

Wed, Mar 10, 2021 at 5:02 PM

Reply-To: support@services.acs.org

To: m.zakki.fahmi@fst.unair.ac.id, zakkifahmi@gmail.com

Cc: aswandi.wibrianto-2016@fst.unair.ac.id, jefpry.sianturi@gmail.com, desita.kamila.ulfa-2019@fst.unair.ac.id, yu.yu.aung-2018@fst.unair.ac.id, yaung.kwae-2018@fst.unair.ac.id, satya.sakti@fst.unair.ac.id, irzaman@ipb.ac.id, brian@tf.itb.ac.id, m.zakki.fahmi@fst.unair.ac.id, zakkifahmi@gmail.com

10-Mar-2021

Journal: ACS Omega

Manuscript ID: ao-2021-012873

Title: "Comparison Direct synthesis hyaluronic acid-based carbon nanodots as dual active targeting and imaging of HeLa tumor cells"

Authors: Wibrianto, Aswandi; Sianturi, Jefpry ; Ulfa, Desita; Aung, Yu Yu; Kwee, Yaung; Sakti, Satya; Irzaman, Irzaman; Yuliarto, Brian; Fahmi, Mochamad

Manuscript Status: Submitted

Dear Dr. Fahmi:

Your manuscript has been successfully transferred to ACS Omega.

Please reference the above manuscript ID in all future correspondence. If there are any changes in your contact information, please log in to ACS Paragon Plus with your ACS ID at <http://paragonplus.acs.org/login> and select "Edit Your Profile" to update that information.

You can view the status of your manuscript by selecting the tab labeled "My Authoring Activity" in ACS Paragon Plus after logging in to <http://paragonplus.acs.org/login>.

Journal Publishing Agreement and Copyright

Upon acceptance, ACS Publications will require the corresponding author to sign and submit a Journal Publishing Agreement. This agreement gives authors a number of rights regarding the use of their manuscripts. At acceptance, the corresponding author will receive an email linking through to the Journal Publishing Agreement Wizard, which helps you select the most appropriate license for your manuscript.

For more information please see: [https://pubs.acs.org/page/copyright/journals/jpa\\_faqs.html](https://pubs.acs.org/page/copyright/journals/jpa_faqs.html)

ACS Authoring Services

Did you know that ACS provides authoring services to help scientists prepare their manuscripts and communicate their research more effectively? Trained chemists with field-specific expertise are available to edit your manuscript for grammar, spelling, and other language errors, and our figure services can help you increase the visual impact of your research.

Visit <https://authoringservices.acs.org> to see how we can help you! Please note that the use of these services does not guarantee that your manuscript will be accepted for publication.

Thank you for submitting your manuscript to ACS Omega.

Sincerely,

Dr. Krishna Ganesh and Dr. Deqing Zhang  
ACS Omega

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior

written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [Pubupdates@acs.org](mailto:Pubupdates@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.

---

## Fahmi, Mochamad ao-2021-012873 - Manuscript Submission to ACS Omega 10-Mar-2021

1 message

---

ACS Omega <onbehalf@manuscriptcentral.com>

Wed, Mar 10, 2021 at 5:02 PM

Reply-To: support@services.acs.org

To: m.zakki.fahmi@fst.unair.ac.id, zakkifahmi@gmail.com

Cc: aswandi.wibrianto-2016@fst.unair.ac.id, jefpry.sianturi@gmail.com, desita.kamila.ulfa-2019@fst.unair.ac.id, yu.yu.aung-2018@fst.unair.ac.id, yaung.kwae-2018@fst.unair.ac.id, satya.sakti@fst.unair.ac.id, irzaman@ipb.ac.id, brian@tf.itb.ac.id, m.zakki.fahmi@fst.unair.ac.id, zakkifahmi@gmail.com

10-Mar-2021

Journal: ACS Omega

Manuscript ID: ao-2021-012873

Title: "Comparison Direct synthesis hyaluronic acid-based carbon nanodots as dual active targeting and imaging of HeLa tumor cells"

Authors: Wibrianto, Aswandi; Sianturi, Jefpry ; Ulfa, Desita; Aung, Yu Yu; Kwee, Yaung; Sakti, Satya; Irzaman, Irzaman; Yuliarto, Brian; Fahmi, Mochamad

Manuscript Status: Submitted

Dear Dr. Fahmi:

Your manuscript has been successfully transferred to ACS Omega.

Please reference the above manuscript ID in all future correspondence. If there are any changes in your contact information, please log in to ACS Paragon Plus with your ACS ID at <http://paragonplus.acs.org/login> and select "Edit Your Profile" to update that information.

You can view the status of your manuscript by selecting the tab labeled "My Authoring Activity" in ACS Paragon Plus after logging in to <http://paragonplus.acs.org/login>.

Journal Publishing Agreement and Copyright

Upon acceptance, ACS Publications will require the corresponding author to sign and submit a Journal Publishing Agreement. This agreement gives authors a number of rights regarding the use of their manuscripts. At acceptance, the corresponding author will receive an email linking through to the Journal Publishing Agreement Wizard, which helps you select the most appropriate license for your manuscript.

For more information please see: [https://pubs.acs.org/page/copyright/journals/jpa\\_faqs.html](https://pubs.acs.org/page/copyright/journals/jpa_faqs.html)

ACS Authoring Services

Did you know that ACS provides authoring services to help scientists prepare their manuscripts and communicate their research more effectively? Trained chemists with field-specific expertise are available to edit your manuscript for grammar, spelling, and other language errors, and our figure services can help you increase the visual impact of your research.

Visit <https://authoringservices.acs.org> to see how we can help you! Please note that the use of these services does not guarantee that your manuscript will be accepted for publication.

Thank you for submitting your manuscript to ACS Omega.

Sincerely,

Dr. Krishna Ganesh and Dr. Deqing Zhang  
ACS Omega

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior



written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [Pubupdates@acs.org](mailto:Pubupdates@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.

---

## Fahmi, Mochamad ao-2021-012873.R2 - Manuscript Accepted 29-Apr-2021

2 messages

---

**ACS Omega** <onbehalf@manuscriptcentral.com>  
Reply-To: hofkens-office@omega.acs.org  
To: m.zakki.fahmi@fst.unair.ac.id, zakkifahmi@gmail.com

Thu, Apr 29, 2021 at 6:25 PM

29-Apr-2021

Journal: ACS Omega  
Manuscript ID: ao-2021-012873.R2  
Title: "Comparison Direct synthesis hyaluronic acid-based carbon nanodots as dual active targeting and imaging of HeLa Cancer cells"  
Author(s): Aung, Yu-Yu; Wibrianto, Aswandi; Sianturi, Jefry; Ulfa, Desita; Sakti, Satya; Irzaman, Irzaman; Yulianto, Brian; Chang, Jia-Yaw; Kwee, Yaung; Fahmi, Mochamad  
Manuscript Status: Accept

Dear Dr. Fahmi:

We are pleased to inform you that your manuscript has been accepted for publication in ACS Omega.

You will soon receive an email invitation from the ACS Journal Publishing Staff that contains a link to the online Journal Publishing Agreement. Please sign and submit the journal publishing agreement within 48 hours.

You will be contacted in approximately a week by the ACS Journal Publishing Staff regarding the proofs for your manuscript. Although production of your manuscript will start immediately, your manuscript will not be published until you pay the Article Publishing Charges, <https://acsopencience.org/open-access/pricing/>. You may qualify for discounts. You will also be contacted shortly with information on how to pay your publishing charges. Article Publishing Charges are waived for invited Editorials and Perspectives.

After you submit corrections for your proofs and pay the article publishing charges, your manuscript will be published on the Web in approximately 48 hours. In view of this fast publication time, it is important to review your proofs carefully. Once a manuscript appears on the Web, it is considered published. Any change to the manuscript once it appears on the Web will need to be submitted to the journal office as a separate Addition & Correction manuscript via the ACS Paragon Plus environment.

Once your paper is published, you can track downloads and citations of your work by logging into the ACS Publishing Center (<https://pubs.acs.org/publish/dashboard>) and selecting "Published."

Sincerely,

Prof. Johan Hofkens  
Associate Editor  
ACS Omega  
Phone: +3216327804  
Email: [hofkens-office@omega.acs.org](mailto:hofkens-office@omega.acs.org)

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [Pubupdates@acs.org](mailto:Pubupdates@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.

---

**Mochamad Zakki Fahmi** <m.zakki.fahmi@fst.unair.ac.id>  
To: yu yu <yu.yu.aung-2018@fst.unair.ac.id>

Mon, May 3, 2021 at 4:59 PM

**Best Regards,**

-----

**Mochamad Zakki Fahmi, Ph.D (張家其)**  
**Associate Professor, Department of Chemistry**  
**Universitas Airlangga**  
**Phone : +62-838-32901697**  
**Email : [m.zakki.fahmi@fst.unair.ac.id](mailto:m.zakki.fahmi@fst.unair.ac.id)**



[Quoted text hidden]



---

Is the technical quality of the research reported within valid and appropriate?: Yes

Please evaluate the degree of novelty and originality of the research reported: Good

Are the conclusions adequately supported by the data presented?: Yes

Are the literature references appropriate and up to date?: Yes

Reviewer: 2

Recommendation: Publish after major revisions.

Comments:

In this paper, the author synthesized carbon dots from hyaluronic acid by microwave-assisted and fu indicating possible application as bioimaging agents. Carbon dots is an important material. However Ok and its innovation is fair. It can be published in ACS OMDGA after some problems addressed.

The detailed comments are listed below:

1. HA-M1 is obvious different with others in XRD Diffractogram. So, HRTEM is recommended to c
2. Only AFM of HA-P2 was determined, other three kinds of carbon dots should be required to ob
3. The caption of Fig 6 is confused. For example, what does the description of "furnace-assisted" 100; 200; and 400  $\mu\text{g/mL}$  were used, however seven concentration of 1, 2, 3, 5, 25, 100, 400  $\mu\text{g/mL}$
4. Fig 7 were not clearly enough.
5. The optical properties such as absorption spectra and quantum yields should be compared to c

---

Additional Questions:

Is the technical quality of the research reported within valid and appropriate?: Yes

Please evaluate the degree of novelty and originality of the research reported: Fair

Are the conclusions adequately supported by the data presented?: Yes

## Fahmi, Mochamad ao-2021-012873 - Manuscript Formatting Request - Non-scientific changes

3 messages

ACS Omega <onbehalf@manuscriptcentral.com>  
Reply-To: journalsupport@omega.acs.org  
To: m.zakki.fahmi@fst.unair.ac.id, zakkifahmi@gmail.com

Tue, Apr 6, 2021 at 3:32 PM

06-Apr-2021

Manuscript ID: ao-2021-012873

Manuscript Type: Article

Title: "Comparison Direct synthesis hyaluronic acid-based carbon nanodots as dual active targeting and imaging of HeLa tumor cells"

Author(s): Wibrianto, Aswandi; Sianturi, Jefry; Ulfa, Desita; Aung, Yu-Yu; Kwee, Yaung; Sakti, Satya; Irzaman, Irzaman; Yulianto, Brian; Fahmi, Mochamad

Dear Dr. Fahmi:

You recently received a Revision Request from Johan Hofkens. In addition to addressing the Editor's concerns and the requests of the reviewers, please complete the following before submitting your revision:

- \* In case your current addresses differ from the research affiliations they should be included as footnotes. (affiliations in the system and manuscript must match)
- \* Please update Abstract in the system upon submission of your revision if applicable.

- We ask for complete affiliations for all authors: Institution, Department, Postal Address, Postal code, City, Country. In case your current addresses differ from the research affiliations they should be included as footnotes. (affiliations in the system and manuscript must match)

- The names of the authors listed in the manuscript file must match what is listed in ACS Paragon Plus. Please make sure to correct this: from "Irzaman" to "Irzaman Irzaman" in your manuscript and Supporting Information files.

- Please note that E-mail address are required in manuscript for all authors as well. Please include email addresses for all authors in a separate Author information paragraph in the manuscript file (after Acknowledgment and before References)

- Please note that each page of the manuscript should be numbered starting from title page

- Please note that names of journals need to be abbreviated according to Chemical Abstracts Service Source Index (CASSI)

- Kindly confirm whether the photos in Figure 2 were taken by one of the authors. In case they were not, please add a credit line to the caption (e.g., "Photograph courtesy of 'Author's Name'. Copyright 2020.") and clarify if the image [in figure or TOC graphic] is free domain or if permission is required. If permission is required, provide a document that shows a granted permission, and add a credit line accordingly.

More information is available at [http://pubs.acs.org/page/copyright/permissions\\_otherpub.html](http://pubs.acs.org/page/copyright/permissions_otherpub.html).

- Please include a Table of Contents graphic. The graphic should capture the reader's attention and, in conjunction with the manuscript title, give the reader a quick visual impression of the essence of the paper. Examples include structures, graphs, drawings, SEM/TEM/AFM images, or reaction schemes. The author should submit a graphic in the actual size to be used for the TOC, fitting in an area no larger than 3.25 in. × 1.375 in. (8.3cm × 3.5cm). Type size of labels, formulas, or numbers within the graphic must be legible. The page should be labeled "for Table of Contents use only" and this item should be appended as the last page of the manuscript.

Guidelines for preparation of effective TOC graphics can be obtained at the following link: [http://pubsapp.acs.org/paragonplus/submission/toc\\_abstract\\_graphics\\_guidelines.pdf](http://pubsapp.acs.org/paragonplus/submission/toc_abstract_graphics_guidelines.pdf)

- All pages of the Supporting Information file should be numbered consecutively starting from title page with S1, S2,...

- Caption for Figure must contain all elements (a,b,c...). Please make sure to mention all elements (i,ii,iii...) in captions of Figure S4

Please use highlighting, bolding, italics, or marking of any type within the manuscript to indicate changes made in response to the reviews of your manuscript, and upload the marked-up copy as "Supporting Information For Review Only".

We look forward to receiving your revised manuscript, so that processing of your manuscript may proceed without further delay. Thank you for considering ACS Omega as a forum for the publication of your work.

Sincerely,

Danko Ukropina  
Peer Review Analyst  
ACS Omega

-----  
FOR ASSISTANCE WITH YOUR MANUSCRIPT SUBMISSION PLEASE CONTACT:

ACS Publications Customer Services & Information (CSI)  
Email: [support@services.acs.org](mailto:support@services.acs.org)  
Phone: 202-872-4357  
Toll-Free Phone: 800-227-9919 (USA/Canada only)

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [Pubupdates@acs.org](mailto:Pubupdates@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.

---

**Mochamad Zakki Fahmi** <[m.zakki.fahmi@fst.unair.ac.id](mailto:m.zakki.fahmi@fst.unair.ac.id)>  
To: aswandi wibrianto <[aswandi.wibrianto-2016@fst.unair.ac.id](mailto:aswandi.wibrianto-2016@fst.unair.ac.id)>

Tue, Apr 6, 2021 at 5:09 PM

Aswandi diatas merupakan tambahan komentar dari reviewer paper jefry, sepertinya mesalh teknis di tempaltenya saja

**Best Regards,**

-----  
**Mochamad Zakki Fahmi, Ph.D (張家其)**  
Associate Professor, Department of Chemistry  
Universitas Airlangga  
Phone : +62-838-32901697  
Email : [m.zakki.fahmi@fst.unair.ac.id](mailto:m.zakki.fahmi@fst.unair.ac.id)



[Quoted text hidden]

---

**aswandi wibrianto** <[aswandi.wibrianto-2016@fst.unair.ac.id](mailto:aswandi.wibrianto-2016@fst.unair.ac.id)>  
To: Mochamad Zakki Fahmi <[m.zakki.fahmi@fst.unair.ac.id](mailto:m.zakki.fahmi@fst.unair.ac.id)>

Tue, Apr 6, 2021 at 5:17 PM

Baik pak. Segera saya revisi.

Kind regards,

Aswandi Wibrianto

[Quoted text hidden]