

VOLUME 49
ISSUE 6, 2014



ISSN 1314-7471 (print)
ISSN 1314-7978 (on line)
www.uctm.edu

JOURNAL

**OF CHEMICAL TECHNOLOGY
AND METALLURGY**



SOFIA 2014

PARTIAL OXIDATIVE SYNTHESIS OF FLUORESCENT CARBON DERIVED FROM LOCAL BAMBOO LEAVES

Ahmadi Jaya Permana, Abdul Haris, Harsasi Setyawati, Mochamad Zakki Fahmi

*Department of Chemistry, Faculty of Science and Technology
Universitas Airlangga
Kampus C Mulyorejo Universitas Airlangga
Surabaya, Indonesia
E-mail: ahmadi-j-permana@fst.unair.ac.id*

*Received 05 January 2017
Accepted 20 July 2017*

ABSTRACT

The fluorescent carbon based materials have wide medical applications due to their less toxicity, and other attractive properties. Bamboo leaves are an interesting alternative precursor for fluorescent carbon synthesis. They have a good prospect as sustainable raw materials. The synthesis of fluorescent carbon from bamboo leaves by partial oxidation is performed at an optimum temperature of 300°C. Its photoluminescent property is measured by a spectrofluorometer. It shows a wavelength emission at 425 nm - 475 nm. The fluorescent carbon obtained has nanoparticles of the size about 4 nm based on the analysis using atomic force microscopy. It shows a peak at 22,7° by X-Ray diffractometer powder analysis.

Keywords: partial oxidation, bamboo leaves, fluorescent carbon.

INTRODUCTION

The bamboo leaves are abundant, underutilized and low economic value materials in East Java. They contain mostly hydrocarbon compounds such as cellulose that can be a potential source of synthesizing carbon. The latter can be used as a biomedical material because of its less toxicity, good solubility in water, good chemical inertness, high biocompatibility and easy functionalization processes [1].

Carbon nanoparticles have good fluorescence and magnetic properties [2]. Fluorescent carbon is widely used as a biomaterial, pattern coding, sensors fabrication and optoelectronics. Its biomedical applications refer to bioimaging, drug transport and viral inhibitor formulations [3]. Fluorescent carbon generally consists of graphene quantum dots, carbon nanodots, and polymer dots [4].

Top-down and bottom-up synthesis methods of fluorescent carbon nanoparticles are used. The partial oxidation is a favorable bottom-up method of synthesizing fluorescent carbon because it provides a good tem-

perature control and optimum photoluminescence [5]. Fluorescent carbon is synthesized using finely structured organics precursors like graphene and carbon nanotubes or citric acid monohydrate, carboxylate [6], and carbohydrates [7]. However, an improvement of the synthesis method and the choice of the raw material source is needed to provide eco-friendly carbon materials.

Application of bamboo leaves to synthesis carbon dots has been previously proposed by Liu et al. [4]. They show that these leave can be used as a raw material to make precisely carbon dots via a hydrothermal process. A different method of synthesizing carbon dots from bamboo leaves, especially from scrap leaves, is required in view of the effort to develop eco-friendly process of nanomaterials synthesis. The present communication reports a synthesis of fluorescent carbon on the ground of bamboo leaves via partial oxidation. Partial oxidative synthesis of fluorescent carbon is an alternative to pyrolysis. It enhances the product solubility and fluorescent properties preserving carbon functional groups. This refers especially to carbon carboxylic group increases the solubility and the fluorescence of the material obtained.

It can also affect the modification to carbon dots, which in turn leads to wider application [7].

EXPERIMENTAL

Bamboo leaves of the rope type (*Asparagus cochinchinensis*) were collected from Surabaya, Indonesia. Prior to processing they were washed with water. Then they were heated for 2 h at 150°C. The extraction of cellulose was conducted in 2 % (w/v) aqueous solution of NaOH and refluxed for 4 h at 60°C. The extract was rinsed and centrifuged at 2000 rpm for 15 min. The precipitate of the bamboo leaf extract was burned to synthesize fluorescent carbons by partial oxidation for 2 h at 200°C, 250°C, 300°C, 350°C, and 400°C. The product obtained was dissolved in 2 % (w/v) aqueous NaOH solution. This step was followed by filtration with using 0.22 μm syringe to separate particles by size. The filtrates were dialyzed for 24 h with a membrane MWCO 1000 Da for 24 hours.

Sodium hydroxide (NaOH, 98 %) was purchased from Showa Kako Corp., Japan. It was used without further purification.

The solubility percentage of the resulting carbon dots was determined by measuring the weight of the insoluble bamboo leaves after the partial oxidation process and referring to the weight of the initial bamboo leaves. The fluorescence of carbon solutions was observed by using a portable UV-lamp (365 nm) and analyzed on a JASCO FP-6500 luminescence spectrometer. The fluorescent carbon particles size was measured using an atomic force microscope (AFM) BRUKER. Their powder crystallinity was analyzed by a X-ray diffractometer (XRD) X'PERT-PRO PA using CuK α radiation ($\lambda = 1,5418 \text{ \AA}$). The functional groups present were identified by a Fourier transform infrared spectroscopy (FTIR) SHIMADZU-8400S.

RESULTS AND DISCUSSION

The fluorescent carbon obtained at different temperature values shows different solubility in NaOH solution. This is illustrated in Fig. 1. It is evident that the solubility increases going from FC 200 to FC 300 and then decreases – the solubility of FC 400 is less than that of FC 300. Obviously the latter is the optimum one. The product obtained at lower temperatures is not as good

as that produced at higher temperature values in terms of the area and the fluorescent ability [8].

The absorbance spectrum of FC 300 is presented in Fig. 2a. It shows a clear shoulder peak at 350 nm.


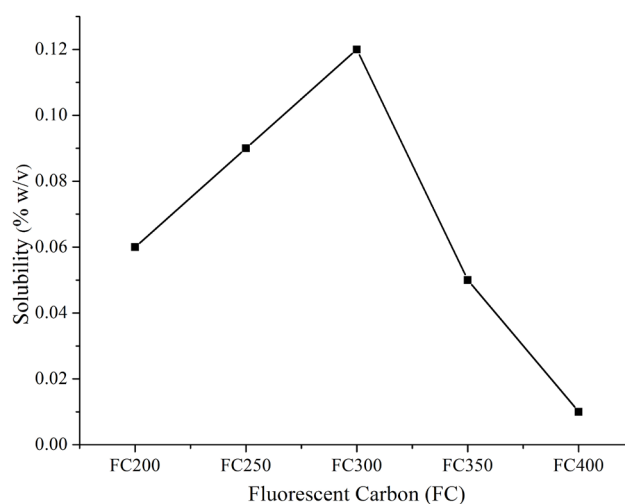


Fig. 1. Solubility of fluorescent carbons (FC).



a)

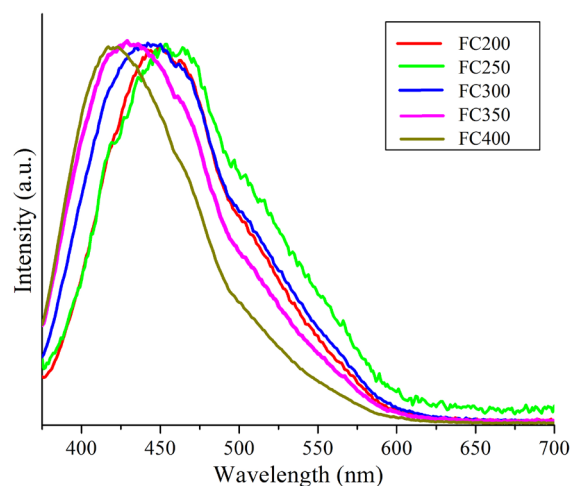


b)

Fig. 2. (a) Emission Spectra of FC; (b) photograph images of water (left) and FC 300 (right) under 254 nm UV light.

The peak is mainly addressed to a three-dimensional confinement of electrons on nano-sized carbon. The photoluminescence (PL) emission spectra of fluorescent carbon are recorded in the wavelength range from 355 nm to 700 nm as shown in Fig. 2b. The difference in emission wavelength is attributed to the different carbon macromolecular structure of bamboo leaves. The pattern of the PL emission spectra is quite similar - the difference is not greater than about 5 nm. The UV-Vis and PL spectra verify the phenomenon of circular absorption and photon emission occurring at the carbon dots. FC 300 has a PL emission around 460 nm and produces a pale blue fluorescence under the portable UV lamp. This finding is in full correspondence with the data reported in ref. [9]

The particle size distribution of fluorescent carbon FC 300 is confirmed by AFM. The corresponding image and particle size distribution histogram is showed in Fig. 3. Based on the AFM image in Fig. 3a, fluorescent carbon

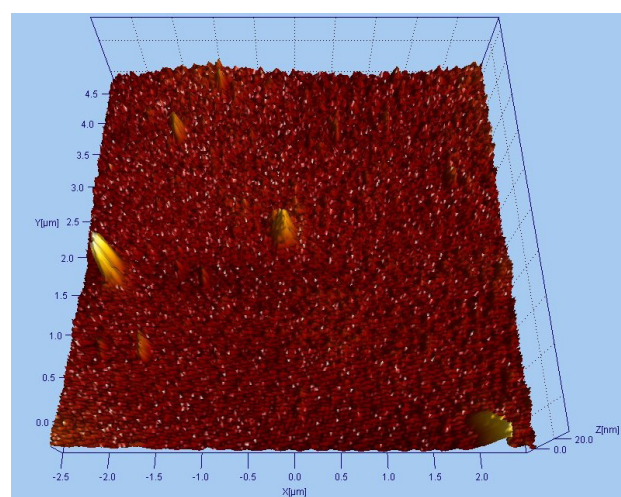

a)

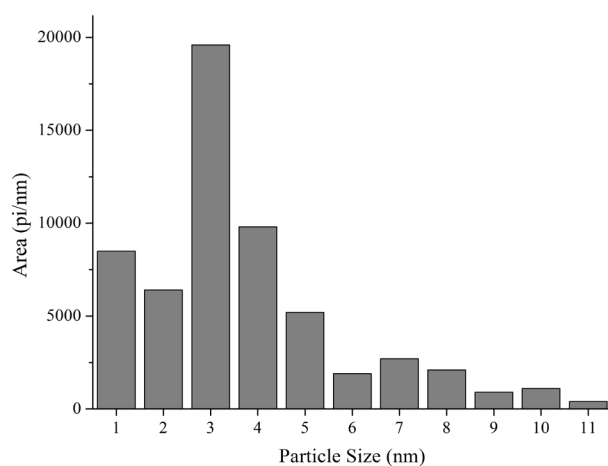


Fig. 3. (a) AFM Image of FC 300 (b) Particle size distribution of FC 300 histogram.

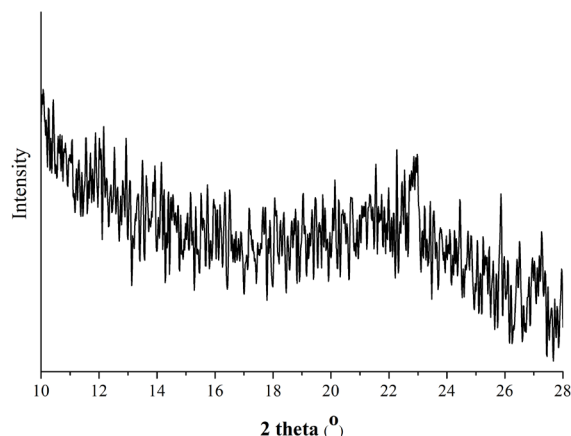


Fig. 4. XRD pattern of FC300.

FC 300 has quite homogenously dispersed particles. Fig. 3b shows a limited particle size distribution of 1nm -11 nm. The dominant distribution is observed at 3 nm.

The XRD pattern of FC300 is shown in Fig. 4. FC 300 is amorphous and a broad peak is observed in the 2θ range of $18^\circ - 26^\circ$. The FC 300 structure is quite similar to that of the graphitic structure based on JCPDS26-1076. The FC 300 particle size is determined in the broad amorphous peak region by the Scherer equation and is found equal to 0,244 nm.

The functional groups of FC 300 are analyzed by FTIR spectroscopy. The FTIR spectrum of FC 300 is shown in Fig. 5. Peaks are outlined at 3431.38 cm^{-1} , 2852.81 cm^{-1} and 1415.8 cm^{-1} . They are assigned to O-H, C-H, and C=O. The hydroxyl and carbonyl groups in FC300 indicate that the fluorescent carbon contains graphene quantum dots [10] and graphene oxide [11]

b)

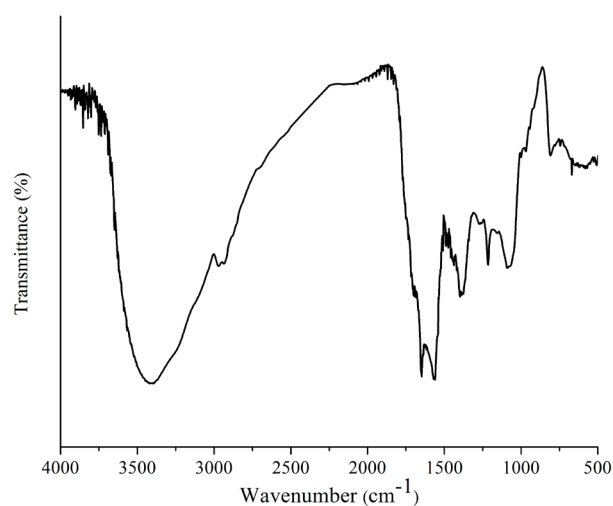


Fig. 5. FTIR Spectrum of FC300.

CONCLUSIONS

Fluorescent carbon is successfully synthesized by partial oxidation of local bamboo leaves. The sample obtained at 300°C has the optimum solubility. It shows PL emission at 460 nm and has blue fluorescence. Its particles show a dominant distribution at 3 nm. The presence of carboxylic and hydroxyl groups is verified. This fluorescent carbon has the potential of a bio-imaging agent due to its optical properties. It can be also used as a drug transport material because of the size of the resulting carbon dots.

Acknowledgements

We thank to Faculty of Science and Technology for the financial support by Hibah Dosen Muda Dana RKAT Fakultas Sains dan Teknologi Universitas Airlangga Tahun 2016 Nomor SP POPA 18148/UN3/KU/2016.

REFERENCES

1. H. Li, X. He, Y. Liu, H. Huang, S. Lian, S.-T. Lee, Z. Kang, One-step ultrasonic synthesis of water-soluble carbon nanoparticles with excellent photoluminescent properties, *Carbon*, 49, 2011, 605-609.
2. H. Liu, T. Ye, C. Mao, Fluorescent Carbon Nanoparticles Derived from Candle Soot, *Angewandte Chemie International Edition* 46, 2007, 6473-6475.
3. H. Li, Z. Kang, Y. Liu, S.-T. Lee, Carbon nanodots: synthesis, properties and applications, *Journal of materials chemistry*, 22, 2012, 24230-24253.
4. Liu, Yingshuai, Yanan Zhao, Yuanyuan Zhang. One-step green synthesized fluorescent carbon nanodots from bamboo leaves for copper (II) ion detection, *Sensors and Actuators B: Chemical*, 196, 2014, 647-652.
5. D. Pan, J. Zhang, Z. Li, C. Wu, X. Yan, M. Wu, Observation of pH-, solvent-, spin-, and excitation-dependent blue photoluminescence from carbon nanoparticles, *Chemical Communications*, 46, 2010, 3681-3683.
6. H. Peng, J. Travas-Sejdic, Simple aqueous solution route to luminescent carbogenic dots from carbohydrates, *Chemistry of Materials*, 21, 2009, 5563-5565.
7. J. Shen, Y. Zhu, X. Yang, C. Li, Graphene quantum dots: emergent nanolights for bioimaging, sensors, catalysis and photovoltaic devices, *Chemical Communications*, 48, 2012, 3686-3699.
8. Y. Yang, J. Cui, M. Zheng, C. Hu, S. Tan, Y. Xiao, Q. Yang, Y. Liu, One-step synthesis of amino-functionalized fluorescent carbon nanoparticles by hydrothermal carbonization of chitosan, *Chemical Communications*, 48, 2012, 380-382.
9. S. Zhu, Y. Song, X. Zhao, J. Shao, J. Zhang, B. Yang, The photoluminescence mechanism in carbon dots (graphene quantum dots, carbon nanodots and polymer dots): current state and future perspective, 2014.
10. M.Z. Fahmi, W. Sukmayani, S.Q. Khairunisa, A.M. Witaningrum, D.W. Indriati, M.Q.Y. Matondang, J.-Y. Chang, T. Kotaki, M. Kameoka, Design of boronic acid-attributed carbon dots on inhibits HIV-1 entry, *RSC Adv.*, 2016.
11. Y. Dong, J. Shao, C. Chen, H. Li, R. Wang, Y. Chi, X. Lin, G. Chen, Blue luminescent graphene quantum dots and graphene oxide prepared by tuning the carbonization degree of citric acid, *Carbon*, 50, 2012, 4738-4743.

Editorial Board

Submitted by admin on Fri, 09/28/2018 - 15:59

EDITOR-IN-CHIEF

Prof. Dr. Bogdana Koumanova

University of Chemical Technology and Metallurgy, Bulgaria

S. J. Allen

Queens University of Belfast, UK

N.Yu. Bashkirceva

National Research Technological University, Kazan, Russia

M. Bojinov

University of Chemical Technology and Metallurgy, Bulgaria

V. Bojinov

University of Chemical Technology and Metallurgy, Bulgaria

J. Carda

University Jaume I, Castellon, Spain

D. Danalev

University of Chemical Technology and Metallurgy, Bulgaria

V. Dimitrov

Bulgarian Academy of Sciences

N. Dishovsky

University of Chemical Technology and Metallurgy, Bulgaria

S.J.C. Feyo de Azevedo

Universidade do Porto, Portugal

N. Georgieva

University of Chemical Technology and Metallurgy, Bulgaria

S. Heinrich

Hamburg University of Technology, Germany

S. Kalcheva

A. Mavrova

University of Chemical Technology and Metallurgy, Bulgaria

I.P. Mazur

Lipetsk State Technical University, Russia

D. Mehandjiev

Bulgarian Academy of Sciences

E. Mihailov

University of Chemical Technology and Metallurgy, Bulgaria

L. Mörl

University "Otto-von-Guericke", Magdeburg, Germany

E. Naydenova

University of Chemical Technology and Metallurgy, Bulgaria

A.B. Nayzabekov

Rudny Industrial Institute, Rudny, Kazakhstan

L. Petrov

Bulgarian Academy of Sciences

S. Piskin

Yildiz Technical University, Istanbul, Turkey

A.K. Pogodaev

Lipetsk State Technical University, Russia

A. Popova

University of Chemical Technology and Metallurgy, Bulgaria

A. Di Schino

University of Chemical Technology and Metallurgy, Bulgaria

F. Keil

Hamburg University of Technology, Germany

T. Komatsu

Nagaoka University of Technology, Japan

J.M. Le Lann

Institut National Polytechnique, Ecole Nationale Supérieure des Ingénieurs en
Arts Chimiques et Technologiques, Toulouse, France

S.N. Lezhnev

Rudny Industrial Institute, Rudny, Kazakhstan

University of Perugia, Italy

V. Stefanova

University of Chemical Technology and Metallurgy, Bulgaria

D. Stoilova

Bulgarian Academy of Sciences

N. Tsarevsky

Southern Methodist University, Dallas, Texas, USA

I. Turunen

Lappeenranta University of Technology, Finland



Ads by Google

Journal of Chemical Technology and Metallurgy

COUNTRY

Bulgaria

Universities and research institutions in Bulgaria

SUBJECT AREA AND CATEGORY

 Chemical Engineering
 Chemical Engineering (miscellaneous)

 Engineering
 Industrial and Manufacturing Engineering

PUBLISHER

 University of Chemical
 Technology and Metallurgy

 University of Chemical
 Technology and Metallurgy
 in Scimago Institutions
 Rankings

H-INDEX

17

PUBLICATION TYPE

Journals


ISSN

13147978, 13147471

COVERAGE

2013-2020

INFORMATION

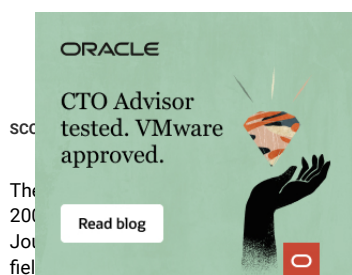[Homepage](#)
[How to publish in this journal](#)
journal@uctm.edu


sc

The

200

Jo

fiel

in Journal of Chemical Technology and Metallurgy. It ran in Bulgarian. In 2013 it was published quarterly in English. Since 2013 it has run bimonthly as the Journal of Chemical Technology and Metallurgy is a specialized scientific edition presenting original research results in the fields of: Inorganic Chemistry; Organic Chemistry; Analytical Chemistry; Physical Chemistry; Organic Synthesis and Fuels; Polymer Engineering; Textile and Leather; Cellulose; Paper and Polygraphy; Inorganic and Electrochemical Productions; Chemical Engineering; Industrial Automation; Information Technology; Biotechnology; Economics and Management of Chemical and Metallurgical Industry; Sustainable Development and Environmental Protection; Physical Metallurgy; Metallurgy of Iron and Casting; Metallurgy of Non-ferrous and Semiconducting Materials; Technology of Silicates; Nanomaterials.

y started originally in 1954 as Annual Journal of the former Higher Institute of Chemical Technology. It ran in Bulgarian. In 2013 it was published quarterly in English. Since 2013 it has run bimonthly as the Journal of Chemical Technology and Metallurgy. It was published quarterly in English. Since 2013 it has run bimonthly as the Journal of Chemical Technology and Metallurgy is a specialized scientific edition presenting original research results in the fields of: Inorganic Chemistry; Organic Chemistry; Analytical Chemistry; Physical Chemistry; Organic Synthesis and Fuels; Polymer Engineering; Textile and Leather; Cellulose; Paper and Polygraphy; Inorganic and Electrochemical Productions; Chemical Engineering; Industrial Automation; Information Technology; Biotechnology; Economics and Management of Chemical and Metallurgical Industry; Sustainable Development and Environmental Protection; Physical Metallurgy; Metallurgy of Iron and Casting; Metallurgy of Non-ferrous and Semiconducting Materials; Technology of Silicates; Nanomaterials.

Join the conversation about this journal

FIND SIMILAR JOURNALS ?

1
Indian Journal of Chemical
Technology
IND

52%
similarity

2
Mediterranean Journal of
Chemistry
MAR

52%
similarity

3
Research Journal of
Chemistry and Environment
IND








51%
similarity

4
Journal of Chemistry
EGY

50%
similarity

5
Moroccan Journal of
Chemistry
MAR

50%
similarity

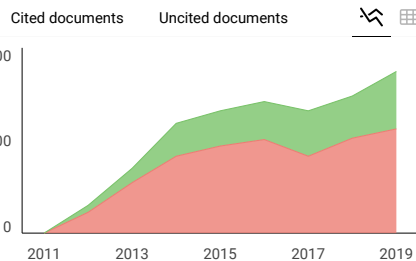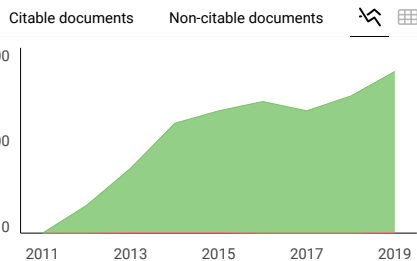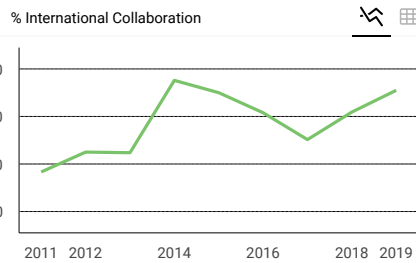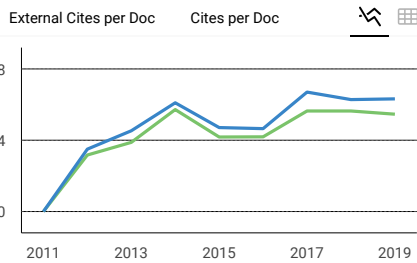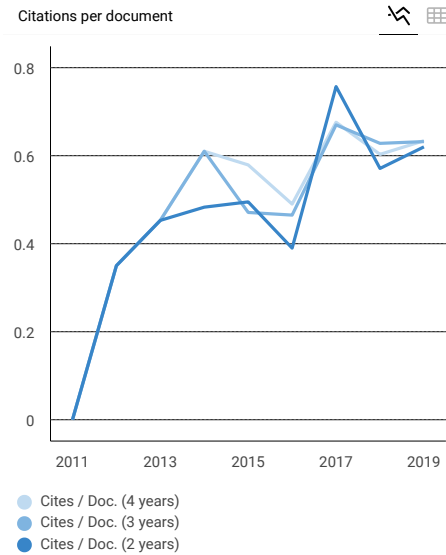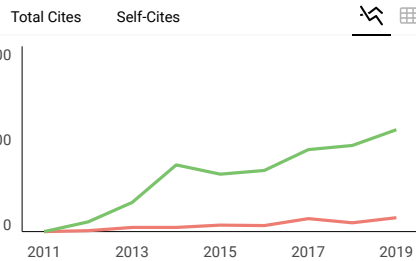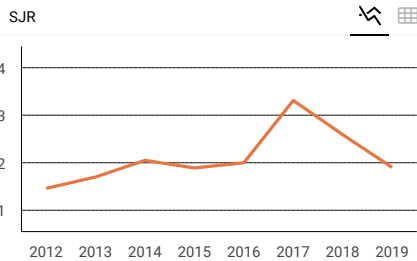

Journal of Chemical Technology and Metallurgy

Q3 Chemical Engineering (miscellaneous) best quartile

SJR 2019 0.19

powered by scimagojr.com

← Show this widget in your own website

Just copy the code below and paste within your html code:

```
<a href="https://www.scimagojr.com" style="border: 1px solid black; padding: 2px; display: inline-block;">https://www.scimagojr.com
```

Metrics based on Scopus® data as of April 2020

M **Mohsen afrouzeh** 2 weeks ago

Hi
could you please let us to know about the ranking of this journal on 2020?
best wishes

reply



Melanie Ortiz 2 weeks ago

Dear Mohsen,
Thank you for contacting us. Our data come from Scopus, they annually send us an update of the data. This update is sent to us around April / May every year. The SJR for 2019 was released on 11 June 2020. Therefore, the indicators for 2020 will be available in

SCImago Team

Volume 52, Iss. 6, 2017

Submitted by admin1 on Sat, 09/29/2018 - 22:14

Journal of Chemical Technology and Metallurgy

52, Iss. 6, 2017
ISSN 1314-7471 (print)
ISSN 1314-7978 (on line)

EDITOR-IN- CHIEF

Prof. Dr. Bogdana Koumanova

Tel: (+ 359 2) 81 63 302

University of Chemical Technology and Metallurgy

8 Kl. Ohridski, 1756 Sofia, Bulgaria

E-mail: journal@uctm.edu

SELECTED ARTICLES

International Conference

**“Collaboration Seminar of Chemistry and
Industry (CoSCI-2016)”**

5-6 October, 2016

Surabaya, Indonesia

Invited Editor

Dr. Purkan Purkan

[Primary study of cellulose acetate hollow fiber as a green membrane applied to hemodialysis](#)

Yanuardi Raharjo, Siti Wafiroh, Mahdya Nayla, Vita Yuliana, Mochamad Zakki Fahmi

[Composite beads of chitosan/bentonite as a matrix for phosphate fertilizer controlled-release](#)

Bambang Piluharto, Veinardi Suendo, Ida Maulida, Asnawati

[Serum acetaldehyde as a potential biomarker for the detection of pathogenic biofilm formation by *Candida albicans*](#)

Masfufatun, Sumayyah Luqman Bayasud, Mei Shirli Yasinta, Ni'matuzahro, Afaf Baktir

[The influence of ascorbic acid, creatine, and creatinine on the uric acid analysis by potentiometry using a carbon paste modified imprinting zeolite electrode](#)

Miratul Khasanah, Muji Harsini, Alfa Akustia Widati, Prihantari Mukti Ibrani

[A novel spectrophotometric method for determination of histamine based on its complex reaction with Cu\(II\) and alizarin red S](#)

Miftakhul Jannatin, Ayu Nabila I.L, Ganden Supriyanto, Pratiwi Pudjiastuti

[Application of ionic liquid dispersive liquid-liquid microextraction for analysis of n-nitrosodipropylamine in salted fish](#)

Aning Purwaningsih, Yanuardi Raharjo, Hendarta Agasi

[Determination of chlorpyrifos pesticide by effervescence liquid phase microextraction HPLC UV-Vis](#)

Usreg Sri Handajani, Yanuardi Raharjo, Bagas Wantoro

[Effect of aliphatic and aromatic hydrocarbons on the oxygenase production from hydrocarbonoclastic bacteria](#)

Sri Sumarsih, Ni'matuzahroh, Fatimah, Miranti Puspitasari, Meilisa Rusdiana

[Identification of *Candida* species by assimilation and Multiplex-PCR methods](#)

Hermansyah, Nurmalina Adhiyanti, Julinar, Kemas Yakub Rahadiyanto, Susilawati

[Xylanase enzyme from a local strain of *Pseudomonas stutzeri*](#)

Purkan Purkan, Emma Huruniawati, Sri Sumarsih

[Study of a catalyst of citric acid crosslinking on locust bean gum](#)

Wuryanto Hadinugroho, Suwaldi Martodihardjo, Achmad Fudholi, Sugeng Riyanto

[Production and characterization of sulfonated chitosan-calcium oxide composite membrane as a proton exchange fuel cell membrane](#)

Siti Wafiroh, Abdulloh, Winda Kusuma Wardani

[An excellent way to prepare conductive glass using a simple glass plate aiming a promising solar cell](#)

Harsasi Setyawati, Handoko Darmokoesoemo, Hamami, Faidur Rochman, Ahmadi Jaya Permana

[Partial oxidative synthesis of fluorescent carbon derived from local bamboo leaves](#)

Ahmadi Jaya Permana, Abdul Haris, Harsasi Setyawati, Mochamad Zakki Fahmi

[Stability of coordination compounds obtained by reduction of copper\(II\) halide and 1,3-bis\(diphenylphosphino\)propane \(DPPP\)](#)

Nike Prilil Puspita Sari, Lis Siaturohmah, Effendy, Fariati

[Phenolic compounds from *Aquilaria microcarpa* stem bark](#)

Alfinda Novi Kristanti, Mulyadi Tanjung, Okky P. Rahayu, Erika Herdiana

[Electrochemical degradation of naphthol AS-BO batik dyes](#)

Muji Harsini, Suyanto, Yhosep Gita Y. Y., Lilik Rhodifasari, Handoko Darmokoesomo

[Silica-methyltrimethoxysilane based hydrophobic coatings on a glass substrate](#)

Alfa A. Widati, Nuryono Nuryono, Indriana Kartini, Noah D. Martino

[Chitosan-based neem seed extract nanocapsules: a new approach on enhancing its effectiveness as an insecticide delivery agent](#)

Mochamad Zakki Fahmi, Hery Suwito, Achmadi Susilo, Erika Joeniarti, Anninda Mughniy Rahayu Jaswidi, Nindayu Indrasari

[Confusarin and nudol, two phenanthrene group compounds, from *Dioscorea esculenta* L. and their antioxidant activities](#)

Nanik Siti Aminah, Ratih Hidayah, Mulyadi Tanjung

[Drug delivery hard shell capsules from seaweed extracts](#)

Pratiwi Pudjiastuti, Muhammad Al Rizqi Dharma Fauzi, Handoko Darmokoesoemo

[Organic template free hierarchical ZSM-5 prepared by desilication](#)

Hartati, Alfa Akustia Widati, Aning Purwaningsih, Alfinda Novi Kristanti, Anggarani Nur Oktavia

[Modification of Gresik's dolomite to CaO•MgO nanocomposite as a catalyst for synthesis of biodiesel from tamanu oil](#)

Abdulloh Abdulloh, Alfa Akustia Widati, Oditio Arizal

[Guide for Authors](#)

