

PARTIAL OXIDATIVE SYNTHESIS OF FLUORESCENT CARBON DERIVED FROM LOCAL BAMBOO LEAVES

by Harsasi Setyawati

Submission date: 03-Jan-2023 03:12PM (UTC+0800)

Submission ID: 1988144517

File name: 2_Partial_oxidative_synthesis_of_fluorescent_carbon_derived.pdf (929.28K)

Word count: 1764

Character count: 9420

PARTIAL OXIDATIVE SYNTHESIS OF FLUORESCENT CARBON DERIVED FROM LOCAL BAMBOO LEAVES

Ahmadi Jaya Permana, Abdul Haris, Harsasi Setyawati, Mochamad Zakki Fahmi

¹ Department of Chemistry, Faculty of Science and Technology
Universitas Airlangga
Kampus C Mulyorejo Universitas Airlangga
Surabaya, Indonesia
E-mail: ahmadi-j-permana@fst.unair.ac.id

³ Received 05 January 2017
Accepted 20 July 2017

ABSTRACT

The fluorescent carbon based materials have wide medical applications due to their less toxicity, and other attractive properties. Bamboo leaves are an interesting alternative precursor for fluorescent carbon synthesis. They have a good prospect as sustainable raw materials. The synthesis of fluorescent carbon from bamboo leaves by partial oxidation is performed at an optimum temperature of 300°C. Its photoluminescent property is measured by a spectrofluorometer. It shows a wavelength emission at 425 nm - 475 nm. The fluorescent carbon obtained has nanoparticles of the size about 4 nm based on the analysis using atomic force microscopy. It shows a peak at 22,7° by X-Ray diffractometer powder analysis.

Keywords: partial oxidation, bamboo leaves, fluorescent carbon.

INTRODUCTION

The bamboo leaves are abundant, underutilized and low economic value materials in East Java. They contain mostly hydrocarbon compounds such as cellulose that can be a potential source of synthesizing carbon. The latter can be used as a biomedical material because of its less toxicity, good solubility in water, good chemical inertness, high biocompatibility and easy functionalization processes [1].

Carbon nanoparticles have good fluorescence and magnetic properties [2]. Fluorescent carbon is widely used as a biomaterial, pattern coding, sensors fabrication and optoelectronics. Its biomedical applications refer to bioimaging, drug transport and viral inhibitor formulations [3]. Fluorescent carbon generally consists of graphene quantum dots, carbon nanodots, and polymer dots [4].

Top-down and bottom-up synthesis methods of fluorescent carbon nanoparticles are used. The partial oxidation is a favorable bottom-up method of synthesizing fluorescent carbon because it provides a good tem-

perature control and optimum photoluminescence [5]. Fluorescent carbon is synthesized using finely structured organics precursors like graphene and carbon nanotubes or citric acid monohydrate, carboxylate [6], and carbohydrates [7]. However, an improvement of the synthesis method and the choice of the raw material source is needed to provide eco-friendly carbon materials.

Application of bamboo leaves to synthesis carbon dots has been previously proposed by Liu et al. [4]. They show that these leave can be used as a raw material to make precisely carbon dots via a hydrothermal process. A different method of synthesizing carbon dots from bamboo leaves, especially from scrap leaves, is required in view of the effort to develop eco-friendly process of nanomaterials synthesis. The present communication reports a synthesis of fluorescent carbon on the ground of bamboo leaves via partial oxidation. Partial oxidative synthesis of fluorescent carbon is an alternative to pyrolysis. It enhances the product solubility and fluorescent properties preserving carbon functional groups. This refers especially to carbon carboxylic group increases the solubility and the fluorescence of the material obtained.

It can also affect the modification to carbon dots, which in turn leads to wider application [7].

EXPERIMENTAL

Bamboo leaves of the rope type (*Asparagus cochinchinensis*) were collected from Surabaya, Indonesia. Prior to processing they were washed with water. Then they were heated for 2 h at 150°C. The extraction of cellulose was conducted in 2 % (w/v) aqueous solution of NaOH and refluxed for 4 h at 60°C. The extract was rinsed and centrifuged at 2000 rpm for 15 min. The precipitate of the bamboo leaf extract was burned to synthesize fluorescent carbons by partial oxidation for 2 h at 200°C, 250°C, 300°C, 350°C, and 400°C. The product obtained was dissolved in 2 % (w/v) aqueous NaOH solution. This step was followed by filtration with using 0.22 µm syringe to separate particles by size. The filtrates were dialyzed for 24 h with a membrane MWCO 1000 Da for 24 hours.

Sodium hydroxide (NaOH, 98 %) was purchased from Showa Kako Corp., Japan. It was used without further purification.

The solubility percentage of the resulting carbon dots was determined by measuring the weight of the insoluble bamboo leaves after the partial oxidation process and referring to the weight of the initial bamboo leaves. The fluorescence of carbon solutions was observed by using a portable UV-lamp (365 nm) and analyzed on a JASCO FP-6500 luminescence spectrometer. The fluorescent carbon particles size was measured using an atomic force microscope (AFM) BRUKER. Their powder crystallinity was analyzed by a X-ray diffractometer (XRD) X'PERT-PRO PA using CuK α radiation ($\lambda = 1,5418 \text{ \AA}$). The functional groups present were identified by a Fourier transform infrared spectroscopy (FTIR) SHIMADZU-8400S.

RESULTS AND DISCUSSION

The fluorescent carbon obtained at different temperature values shows different solubility in NaOH solution. This is illustrated in Fig. 1. It is evident that the solubility increases going from FC 200 to FC 300 and then decreases – the solubility of FC 400 is less than that of FC 300. Obviously the latter is the optimum one. The product obtained at lower temperatures is not as good

as that produced at higher temperature values in terms of the area and the fluorescent ability [8].

The absorbance spectrum of FC 300 is presented in Fig. 2a. It shows a clear shoulder peak at 350 nm.

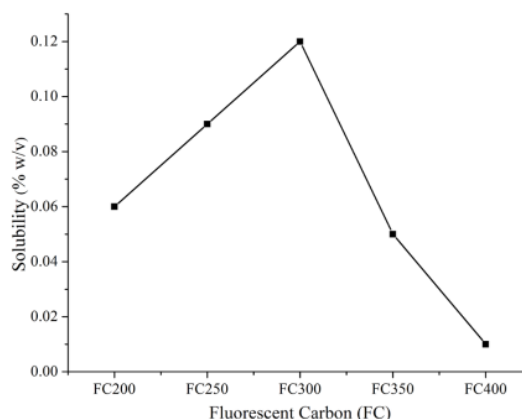


Fig. 1. Solubility of fluorescent carbons (FC).

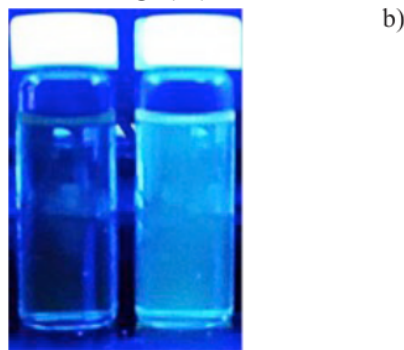
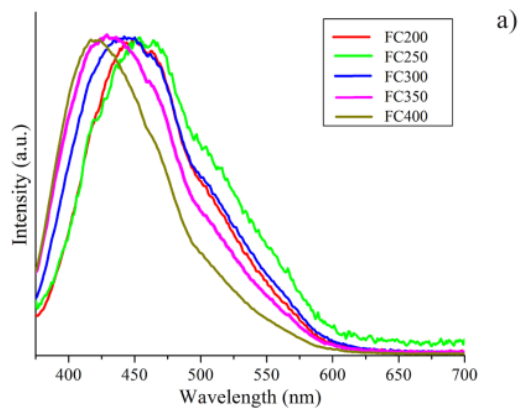


Fig. 2. (a) Emission Spectra of FC; (b) photograph images of water (left) and FC 300 (right) under 254 nm UV light.

The peak is mainly addressed to a three-dimensional confinement of electrons on nano-sized carbon. The photoluminescence (PL) emission spectra of fluorescent carbon are recorded in the wavelength range from 355 nm to 700 nm as shown in Fig. 2b. The difference in emission wavelength is attributed to the different carbon macromolecular structure of bamboo leaves. The pattern of the PL emission spectra is quite similar - the difference is not greater than about 5 nm. The UV-Vis and PL spectra verify the phenomenon of circular absorption and photon emission occurring at the carbon dots. FC 300 has a PL emission around 460 nm and produces a pale blue fluorescence under the portable UV lamp. This finding is in full correspondence with the data reported in ref. [9]

The particle size distribution of fluorescent carbon FC 300 is confirmed by AFM. The corresponding image and particle size distribution histogram is showed in Fig. 3. Based on the AFM image in Fig. 3a, fluorescent carbon

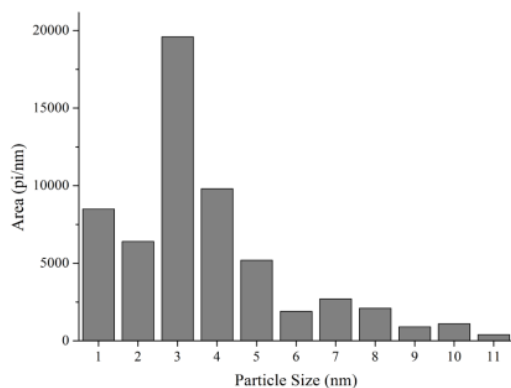
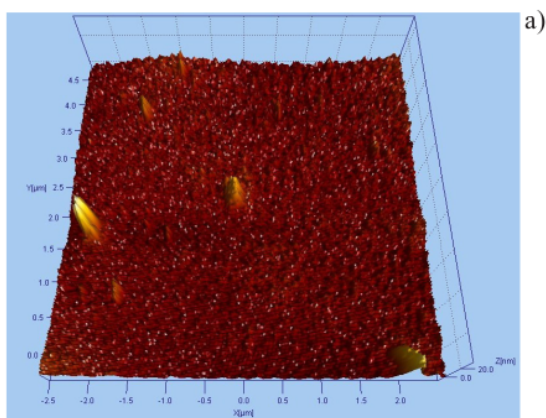


Fig. 3. (a) AFM Image of FC 300 (b) Particle size distribution of FC 300 histogram.

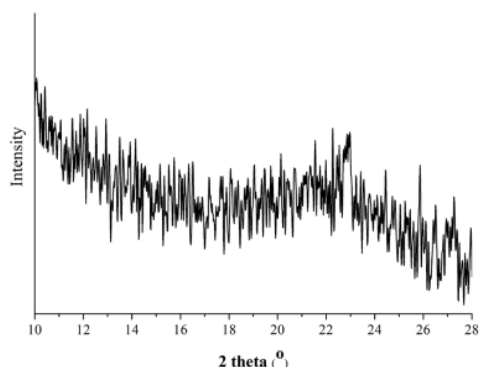


Fig. 4. XRD pattern of FC300.

FC 300 has quite homogeneously dispersed particles. Fig. 3b shows a limited particle size distribution of 1 nm -11 nm. The dominant distribution is observed at 3 nm.

The XRD pattern of FC300 is shown in Fig. 4. FC 300 is amorphous and a broad peak is observed in the 2θ range of $18^\circ - 26^\circ$. The FC 300 structure is quite similar to that of the graphitic structure based on JCPDS26-1076. The FC 300 particle size is determined in the broad amorphous peak region by the Scherer equation and is found equal to 0,244 nm.

The functional groups of FC 300 are analyzed by FTIR spectroscopy. The FTIR spectrum of FC 300 is shown in Fig. 5. Peaks are outlined at 3431.38 cm^{-1} , 2852.81 cm^{-1} and 1415.8 cm^{-1} . They are assigned to O-H, C-H, and C=O. The hydroxyl and carbonyl groups in FC300 indicate that the fluorescent carbon contains graphene quantum dots [10] and graphene oxide [11]

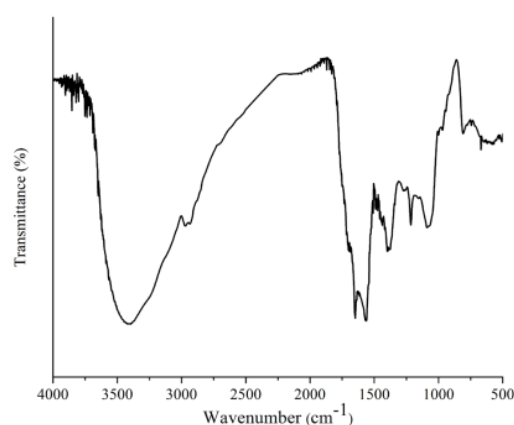


Fig. 5. FTIR Spectrum of FC300.

CONCLUSIONS

Fluorescent carbon is successfully synthesized by partial oxidation of local bamboo leaves. The sample obtained at 300°C has the optimum solubility. It shows PL emission at 460 nm and has blue fluorescence. Its particles show a dominant distribution at 3 nm. The presence of carboxylic and hydroxyl groups is verified. This fluorescent carbon has the potential of a bio-imaging agent due to its optical properties. It can be also used as a drug transport material because of the size of the resulting carbon dots.

Acknowledgements

We thank to Faculty of Science and Technology for the financial support by Hibah Dosen Muda Dana RKAT Fakultas Sains dan Teknologi Universitas Airlangga Tahun 2016 Nomor SP POPA 18148/UN3/KU/2016.

REFERENCES

1. H. Li, X. He, Y. Liu, H. Huang, S. Lian, S.-T. Lee, Z. Kang, One-step ultrasonic synthesis of water-soluble carbon nanoparticles with excellent photoluminescent properties, *Carbon*, 49, 2011, 605-609.
2. H. Liu, T. Ye, C. Mao, Fluorescent Carbon Nanoparticles Derived from Candle Soot, *Angewandte Chemie International Edition* 46, 2007, 6473-6475.
3. H. Li, Z. Kang, Y. Liu, S.-T. Lee, Carbon nanodots: synthesis, properties and applications, *Journal of materials chemistry*, 22, 2012, 24230-24253.
4. Liu, Yingshuai, Yanan Zhao, Yuanyuan Zhang. One-step green synthesized fluorescent carbon nanodots from bamboo leaves for copper (II) ion detection, *Sensors and Actuators B: Chemical*, 196, 2014, 647-652.
5. D. Pan, J. Zhang, Z. Li, C. Wu, X. Yan, M. Wu, Observation of pH-, solvent-, spin-, and excitation-dependent blue photoluminescence from carbon nanoparticles, *Chemical Communications*, 46, 2010, 3681-3683.
6. H. Peng, J. Travas-Sejdic, Simple aqueous solution route to luminescent carbogenic dots from carbohydrates, *Chemistry of Materials*, 21, 2009, 5563-5565.
7. J. Shen, Y. Zhu, X. Yang, C. Li, Graphene quantum dots: emergent nanolights for bioimaging, sensors, catalysis and photovoltaic devices, *Chemical Communications*, 48, 2012, 3686-3699.
8. Y. Yang, J. Cui, M. Zheng, C. Hu, S. Tan, Y. Xiao, Q. Yang, Y. Liu, One-step synthesis of amino-functionalized fluorescent carbon nanoparticles by hydrothermal carbonization of chitosan, *Chemical Communications*, 48, 2012, 380-382.
9. S. Zhu, Y. Song, X. Zhao, J. Shao, J. Zhang, B. Yang, The photoluminescence mechanism in carbon dots (graphene quantum dots, carbon nanodots and polymer dots): current state and future perspective, 2014.
10. M.Z. Fahmi, W. Sukmayani, S.Q. Khairunisa, A.M. Witaningrum, D.W. Indriati, M.Q.Y. Matondang, J.-Y. Chang, T. Kotaki, M. Kameoka, Design of boronic acid-attributed carbon dots on inhibits HIV-1 entry, *RSC Adv.*, 2016.
11. Y. Dong, J. Shao, C. Chen, H. Li, R. Wang, Y. Chi, X. Lin, G. Chen, Blue luminescent graphene quantum dots and graphene oxide prepared by tuning the carbonization degree of citric acid, *Carbon*, 50, 2012, 4738-4743.

PARTIAL OXIDATIVE SYNTHESIS OF FLUORESCENT CARBON DERIVED FROM LOCAL BAMBOO LEAVES

ORIGINALITY REPORT

16%

SIMILARITY INDEX

12%

INTERNET SOURCES

10%

PUBLICATIONS

1%

STUDENT PAPERS

PRIMARY SOURCES

- 1 A J Permana, A T Utami, U S Handajani, H Setyawati. "Facile Sol-Gel Synthesis of Calcium Phosphates: Influence of Ca/P Ratio and Calcination Temperature", IOP Conference Series: Earth and Environmental Science, 2019
Publication 2%
- 2 mmu2.uctm.edu
Internet Source 2%
- 3 repository.ukwms.ac.id
Internet Source 2%
- 4 core.ac.uk
Internet Source 1%
- 5 Fahmi, Mochamad Zakki, Jem-Kun Chen, Chih-Ching Huang, Yong-Chien Ling, and Jia-Yaw Chang. "Phenylboronic acid-modified magnetic nanoparticles as a platform for carbon dot conjugation and doxorubicin delivery", Journal of Materials Chemistry B, 2015.
Publication 1%

6	gyan.iitg.ernet.in Internet Source	1 %
7	journals.plos.org Internet Source	1 %
8	A. Mitra, A. Shaw, Jean-Marc Greneche, P.K. Chakrabarti. "Structural, magnetic, electric and hyperfine behavior of a new multiferroic nanocomposite (Ni _{0.5} Zn _{0.5} Fe ₂ O ₄) _{0.5} (TiO ₂) _{0.5} ", Materials Science and Engineering: B, 2021 Publication	1 %
9	lbmd.coe.pku.edu.cn Internet Source	1 %
10	www.ncbi.nlm.nih.gov Internet Source	1 %
11	www.researchgate.net Internet Source	1 %
12	Lei Cao, Minghui Zan, Fangman Chen, Xinyue Kou, Yulu Liu, Panyong Wang, Qian Mei, Zheng Hou, Wen-Fei Dong, Li Li. "Formation mechanism of carbon dots: From chemical structures to fluorescent behaviors", Carbon, 2022 Publication	1 %
13	Youxing Fang, Shaojun Guo, Dan Li, Chengzhou Zhu, Wen Ren, Shaojun Dong,	1 %

Erkang Wang. "Easy Synthesis and Imaging Applications of Cross-Linked Green Fluorescent Hollow Carbon Nanoparticles", ACS Nano, 2012

Publication

14

Zhao, Andong, Zhaowei Chen, Chuanqi Zhao, Nan Gao, Jinsong Ren, and Xiaogang Qu. "Recent advances in bioapplications of C-dots", Carbon, 2015.

Publication

1 %

15

coek.info

Internet Source

1 %

16

Carbon Nanostructures, 2016.

Publication

<1 %

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

PARTIAL OXIDATIVE SYNTHESIS OF FLUORESCENT CARBON DERIVED FROM LOCAL BAMBOO LEAVES

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4
