

Experimental Design Approach in Erythropoietin-alginate Microsphere Preparation with Different Concentrations of Drug and Polymer

by Tristiana Erawati

Submission date: 13-May-2019 02:10PM (UTC+0800)

Submission ID: 1129544411

File name: reparation_with_Different_Concentrations_of_Drug_and_Polymer.pdf (1.44M)

Word count: 5106

Character count: 27442

Experimental Design Approach in Erythropoietin-alginate Microsphere Preparation with Different Concentrations of Drug and Polymer

Abstract

Background: Microspheres as drug delivery system has been selected to increase stability of Erythropoietin (EPO) to achieve efficacy. **Aim:** Aim of this research was to determine effect of polymer and EPO concentrations on the characteristics. **Materials and Method:** Microspheres involved sodium alginate as polymer and CaCl_2 as a crosslinker. The concentrations of sodium alginate used were 2% and 3%, and EPO were 5000 IU and 10000 IU. Formula of microspheres which consist of 2% and 3% of alginate and 5000 IU EPO were called F1 and F2 respectively, whereas microspheres using 2 and 3% alginate and 10000 IU EPO was named F3 and F4 respectively. Characterization including morphology, particle size, swelling index, and yield of microspheres prepared by ionotropic gelation on aerosolization technique. Design of Experiment (DoE) was used to analyze the formula. **Results:** Results showed that particle sizes of EPO-alginate microspheres were $3.36 \pm 0.26 \mu\text{m}$, $3.42 \pm 0.098 \mu\text{m}$, $3.88 \pm 0.131 \mu\text{m}$ and $3.95 \pm 0.151 \mu\text{m}$ for F1, F2, F3 and F4 respectively. The swelling index measurement based on mass and particle size of microspheres of all formulas showed an index of less than 10. Respectively, yield was $74 \pm 0.290\%$, $86.65 \pm 0.191\%$, $91.89 \pm 0.210\%$, and $94.65 \pm 0.252\%$ for F1 to F4. Using the ANOVA factorial design, it was found that increasing sodium alginate concentration significantly increased yield, while increasing EPO concentration significantly increased particle size and yield of microspheres. Both sodium alginate and EPO concentrations did not affect swelling index of microspheres. Range concentrations of sodium alginate and EPO that produced optimal characteristics of microspheres can be observed in the feasible area of design space overlaid contour plot generated from DoE study. **Conclusion:** EPO-alginate microspheres demonstrated the prospective as carrier and DoE is potential for further optimized formulations.

Keywords: Aerosolization, Ca-alginate microspheres, characteristics, design of experiment, erythropoietin

Introduction

Erythropoietin (EPO) is a glycoprotein that can penetrate the blood-brain barrier and interact with neural receptors to produce neuroprotective functions, which can be used for prophylaxis and Parkinson's therapy.^[1,2] EPO is a protein that has a weakness, namely its risk to be denatured at high temperatures and under extreme pH conditions of <3 and >9 , and its necessity for frequent invasive administration to produce neuroprotective function.^[3,4] Therefore, it is necessary to select an appropriate drug delivery system in order to achieve efficacy and safety.

Microspheres are microparticles composed of homogeneous mixtures or dispersions of active ingredients and entrapment materials.^[5] The recommended dry

microsphere size for the subcutaneous route is $3.5\text{--}5 \mu\text{m}$ to reduce the potential for inflammation in the tissues.^[6] The desired microspheres are in the form of a dry suspension to maintain the stability of the active ingredient, which can then be reconstituted before use. Another advantage of microspheres is that it can reduce side effects due to precipitous drug release.^[7]

The manufacture of microspheres by ionotropic gelation method with aerosolization technique is performed by spraying a polymer solution in a crosslinked solution with the advantages that the drug is encapsulated to become stable, has a uniform particle size of $<8 \mu\text{m}$, has a spherical shape, is produced easily and through quick process, has safety in manufacture, and ensures low cost due to not using organic solvents.^[8]

In the process of making microspheres, a polymer and a crosslinker are required.

Dewi Melani Hariyadi,
Tristiana Erawati,
Vita Fitria
Ramadhani

Department of Pharmaceutics,
Faculty of Pharmacy,
Universitas Airlangga,
Surabaya, Indonesia

Address for correspondence:
Dr. Dewi Melani Hariyadi,
Department of Pharmaceutics,
Faculty of Pharmacy,
Universitas Airlangga,
Jl. Dharmawangsa Dalam,
Surabaya, Indonesia.
E-mail: dewi-m-h@ff.unair.ac.id

Access this article online

Website:
www.jrpsjournal.com

DOI: 10.4103/jrpts.jrpts_4_18

Quick Response Code:



How to cite this article: Hariyadi DM, Erawati T, Ramadhani VF. Experimental design approach in erythropoietin-alginate microsphere preparation with different concentrations of drug and polymer. J Rep Pharma Sci 2019;8:78-84.

This is an open access journal, and articles are distributed under the terms of the Creative Commons Attribution-NonCommercial-ShareAlike 4.0 license, which allows others to remix, tweak, and build upon the work non-commercially, as long as appropriate credit is given and the new creations are licensed under the identical terms.

For reprints contact: reprints@medknow.com

The most commonly used polymer is sodium alginate. This polymer in the form of hydrophilic polysaccharides isolated from the brown algal cell wall. The benefits of sodium alginate are that it is biocompatible, biodegradable, safe, and cheap.^[9] The most frequently used crosslinkers are Ba²⁺ and Ca²⁺ divalent cations. At the selected level of 1 M, calcium chloride (Ca²⁺) crosslinker is safer and affects the rate of drug release (ovalbumin model), causing it to be slower and more controlled than barium chloride (Ba²⁺) crosslinker.^[10,11] Then, the selected drying technique was freeze-drying using 5% maltodextrin lyoprotectant to ensure stability and produce a smooth and spherical microsphere and make the release of the active ingredient more controllable, constant, and predictable.^[8,12]

From the above process, EPO-alginate microspheres would be formed, which can be reconstituted and injected subcutaneously in the patient. The alginate microspheres will release EPO without subsequent microsphere movement from the subcutaneous tissue. In general, the release of the active ingredient from the microsphere includes two stages. The first stage is the stage when the dissolution medium diffuses and stabilizes the hydrodynamic pressure in the microsphere. The second stage is the process of drug release from the microsphere.^[13] EPO is released from alginate microspheres and diffuses from the subcutaneous tissue to blood circulation, going into the brain, penetrating the blood-brain barrier, interacting with neural receptors, and then, producing indirect neuroprotective effects.^[11]

The characteristics of the microsphere are influenced by formula variables such as active ingredient content, polymer type, polymer content, crosslinker solution content, crosslinking time, and pH.^[12] Levels of polymer and active ingredient content used greatly affect microsphere characteristics. With increasing polymer levels in the microspheres, there is an increase in microsphere mean diameter, swelling index, and yield, as long as the quantities of polymer and crosslinker are sufficient.^[11,12] According to Hariyadi *et al.*, an increase of 1%, 1.5%, and 2.5% in sodium alginate polymer content in the ovalbumin-alginate microsphere leads to increased microsphere particle sizes.^[11] In another study, a content increase of 2% and 3% in sodium alginate polymers in the albumin-alginate bovine serum microsphere results in increased microsphere particle size with a spherical shape and smoother surface.^[14] On the other ^[24] d, increased content of antigen model active ingredient leads to an increase in microsphere particle size and yield as long as levels of polymer and crosslinker are sufficient to form microspheres.^[15]

This study was conducted to determine the effect of polymer content of sodium alginate and EPO on several characteristics, namely morphology (shape and surface), size, swelling index, and yield of EPO-alginate microspheres. The preparation of EPO-alginate microspheres was carried out through ionotropic gelation method with aerosolization technique using 2% and 3% sodium alginate polymer and 5000 IU and 10,000 IU of EPO crosslinked with CaCl₂ 1 M solution.

Materials and Methods

Materials

Pharmaceutical grade recombinant human EPO (Daewoong Pharmaceutical Co., Ltd, Gyeonggi, Republic of Korea); pharmaceutical grade sodium alginate (Sigma-Aldrich Inc., St. Louis, MO, USA); pharmaceutical grade CaCl₂·2H₂O (Solvay Chemicals International); Na₂HPO₄ pro analysis (Merck, Darmstadt, Germany); KH₂PO₄ pro analysis (Merck, Darmstadt, Germany); NaCl pro analysis (Sigma-Aldrich Inc., St. Louis, MO, USA); pharmaceutical grade Maltodextrin (Brataco Chemicals, Jakarta, Indonesia); HCl pro analysis (Merck, Darmstadt, Germany); NaOH pro analysis (Merck, Darmstadt, Germany); and demineralized water are used.

Research method

Erythropoietin-alginate microsphere formula design

The formula design of EPO-alginate microspheres of F1 to F4 were presented in Table 1.

Erythropoietin-alginate microspheres production

Sodium alginate (2 g) was dissolved into 100-ml demineralized water; EPO was dispersed into alginate solution and was stirred until it became homogeneous. The resulting Erythropoietin-alginate solution was sprayed using aerosol spray with a hole size of 35 μm, a constant pressure of 40 psi, and a spraying distance of 8 cm into 200 ml of CaCl₂ and was stirred constantly for 30 min at the speed of 1000 rpm. The formed microspheres were centrifuged at a speed of 4000 rpm for 6 min and then washed using distilled water 2–3 times. The washed microspheres were suspended in a 5% maltodextrin solution and then dried using freeze-dryer (Eyela FD-81, Tokyo, Japan) at -45°C for 30 h.

Erythropoietin-alginate microsphere evaluation

Particle size distribution examination

The evaluation of EPO-alginate microsphere size distribution was performed using 400 × optical microscope magnification (Axioscope 40-Zeiss, LLC, USA). This evaluation was performed by placing wet microspheres on the glass object and observing as many as 300 particles.

Table 1: Erythropoietin-alginate microspheres formulas with different sodium alginate and erythropoietin content

Materials	Function	Formula			
		F1	F2	F3	F4
Erythropoietin	Active ingredient	5000 IU	5000 IU	10000 IU	10000 IU
Sodium alginate	Polymer	2%	3%	2%	3%
CaCl ₂ solution	Crosslinker	15 M	1 M	1 M	1 M
Crosslinking time	-	30 min	30 min	30 min	30 min
Maltodextrin	Lyoprotectant	5%	5%	5%	5%

Then, the average diameter was determined, and a microsphere size distribution curve was created. The average diameter was calculated using the formula:

$$d_{vs} = \frac{nd^3}{nd^2}$$

Microsphere shape and surface morphology

The evaluation of EPO-alginate microsphere shape and surface evaluation was performed using a scanning electron microscope (SEM) (Fei Inspect S50, Japan). This evaluation was performed by placing a sample on the handle of the preparation with an adhesive material containing metal grains, such as the metal Pt. The gold in the chamber was evaporated so that the gold steam coated the entire surface of the microparticles. The surface of the gold-coated microparticle was observed with SEM to observe the shape and surface morphology of its microspheres.

Infrared spectra examination

The spectrophotometric evaluation using Fourier-transform infrared (FTIR) spectrophotometer (Perkin Elmer Instrument), India, was performed to determine which microspheres were formed. This evaluation can be done by weighing 1 mg of the microsphere formula with dried KBr powder. Afterward, the microspheres were compressed with hydrophilic presses equipped with a steam puller so that the result obtained is a light-penetrating, light-permeable plate. The resulting infrared spectra were compared with EPO, alginate, and maltodextrin spectra.

Thermal analysis results using differential thermal analysis

A melting point evaluation was conducted to determine whether microspheres have been formed. This evaluation can be done by weighing 3–5 mg samples, then putting it into a sample pan with a crucible aluminum type that has a maximum temperature of 350°C, and then closed. Then, the sample pan was inserted into the sample holder. A heating with a heating rate of 5°C/min, and the equilibrium time was obtained after the initial melting temperature was reached. The peak results of the melting point obtained were compared with the peak of the alginate melting point and CaCl₂.

Moisture content determination

The moisture content (MC) determination on EPO-alginate microspheres can be performed using the moisture analyzer (Mettler Toledo HB43-S Greifensee, Switzerland). This evaluation can be performed by weighing 0.5 g of microspheres and inserting them into the moisture measurement tool. The tool would work for 10 min. The MC was calculated by the formula:

$$MC = \frac{\text{initial weight} - \text{resulting weight}}{\text{resulting weight}} \times 100\%$$

Determination of swelling index

About 100 mg of dry microspheres was laid in 10 ml of phosphate-buffered saline pH 7.4. Swelling index observations were performed at 24- and 30-h intervals. The expanding microspheres were then filtered, and the microsphere surface is wiped with filter paper until the filter paper did not become wet anymore. Samples were laid in a 37°C oven for 2 h, which were then carefully weighed to obtain constant final sample weight.^[16]

Swelling Index Mass

$$= \frac{\text{sample weight at time } t - \text{initial sample weight (mg)}}{\text{initial sample weight (mg)}}$$

Yield determination

The yield value was determined by the ratio of the total weight of the dry microspheres obtained to the amount of weight of EPO, sodium alginate, and maltodextrin. The yield value can be calculated using the formula:

$$\text{Yield (\%)} = \frac{\text{total microsphere weight (mg)}}{\text{alginate weight} + \text{erythropoietin weight} + \text{maltodextrin weight (mg)}} \times 100\%$$

A factorial design ANOVA statistical analysis using the SPSS 21 program (International Business Machines Corporation, IBM, New York, USA) with 95% confidence degree ($\alpha = 0.05$) was performed on particle sizes, swelling indices, and yield data. A free sample *t*-test was performed to determine the compatibility of the swelling index mass and size at the same time. A paired *t*-test was performed to determine the difference of swelling indices at different observation times. In addition, data processing was also performed using Factorial Design 2² design of experiment (DOE) in Minitab 17 software to determine the main effect plot, contour plot, and overlaid contour plot, as well as the range of polymer content of sodium alginate and EPO content to produce the optimal microsphere characteristics, including microsphere size of 3.15–3.85 μm, swelling index of 1–2, and yield of 85%–100%.

Results

Physical characteristics of erythropoietin-alginate microspheres

Organoleptic observations were performed on dried EPO-alginate microspheres of F1, F2, F3, and F4 with maltodextrin lyoprotectant. There was a uniform result,

namely white and odorless powder. Furthermore, the MC of EPO-alginate microspheres F1, F2, F3, and F4 was examined using a moisture analyzer. The examination obtained the results in Table 2 of 9.23% ±0.243%, 9.36% ±0.212%, 9.79% ±0.204%, and 9.53% ±0.200% for each formula according to the requirement that the microsphere MC is <10%.^[17]

DTA thermogram of EPO-alginate microspheres of F1, F2, F3 and F4 showed the melting points and melting heats for each respective formula of 163.5°C and 77.8 J/g, 172.3°C and 58.9 J/g, 163.9°C and 167 J/g, and 204.9°C and 211.9°C. These data indicated that melting points of EPO-alginate microspheres of F1, F2, and F3 were in the range of the melting points of sodium alginate (143°C) and CaCl₂ (176°C), thus it can be inferred that interaction was occurred between sodium alginate and CaCl₂ to form microspheres.^[18] The endothermic peaks of the EPO-alginate F4 microspheres showed melting at 204.9°C; 211.9°C is probably the polymorphic result of the microsphere after the freeze-drying process. The intensity of the endothermic peak and the enthalpy of the EPO-alginate microspheres is higher than that of the polymer and the crosslinker materials because a stable system of Ca-alginate has been formed, requiring higher energy to melt the EPO-alginate microspheres.^[19]

From the results of FTIR spectral examination of the four formulas in Figure 1, the uptake of the amide-specific group of EPO amide (C = O) is present in all formulas, indicating that EPO is stable during the encapsulation process.^[18] From the results of the examination, the peak of amide uptake was found in all four formulas with F1

Table 2: Moisture content examination

Formula	Replication	MC (%)	Average±SD (%)
F1	R1	8.95	9.23±0.243
	R2	9.38	
	R3	9.36	
F2	R1	9.17	9.36±0.212
	R2	9.59	
	R3	9.33	
F3	R1	9.56	9.79±0.204
	R2	9.95	
	R3	9.86	
F4	R1	9.33	9.53±0.200
	R2	9.73	
	R3	9.54	

SD: Standard deviation, MC: Moisture content

Table 3: Swelling index of microspheres based on mass and particle size

Formula	Based on mass		Based on particle size	
	t=24 h	t=30 h	t=24 h	t=30 h
	Swelling Index±SD	Swelling Index±SD	Swelling Index±SD	Swelling Index±SD
F1	1.25±0.188	1.78±0.230	1.15±0.258	1.80±0.168
F2	1.43±0.240	2.16±0.167	1.32±0.231	1.98±0.179
F3	1.29±0.163	1.89±0.106	1.22±0.214	1.92±0.203
F4	1.49±0.224	2.21±0.299	1.36±0.115	2.13±0.200

SD: Standard deviation

wavenumbers (1641.31/cm), F2 (1646.27/cm), F3 (1639.54/cm), and F4 (1633.39/cm). However, the absorption of the NH stretching groups of all formulas on the wavenumber is 3267.56/cm is undetected because there is an overlap with a wider OH group uptake. There was also showed that the absorption of specific groups of guluronate fingerprints of Na-alginate, maltodextrin, and asymmetric carboxylate salt groups were occurred due to crosslinking reactions, which indicated by FTIR that Ca-alginate microspheres have been formed. Other research was also studied formation of crosslinked calcium alginate microspheres by using FTIR spectroscopy.^[20]

Morphology and particle size of microspheres

The results showed that the shape of wet microspheres of formula F1, F2, F3, and F4 was spherical and of a smooth surface [Figure 2]. The SEM results in Figure 1 of all microspheres of the formula showed that the microspheres were spherical shaped and had a smooth surface. The addition of lyoprotectant maltodextrin can cause hydrogen bonding between maltodextrin and the polar surface of microspheres, which can cover the microsphere surface cavity and prevent microsphere formation caused by water sublimation from microspheres during the drying process by freeze-drying method.^[21]

In the observation of wet microspheres with optical microscope, the average particle diameter (dvs) of particle sizes of EPO-alginate microspheres F1, F2, F3, and F4 was 3.36 ± 0.126, 3.42 ± 0.098, 3, 88 ± 0.131, and 3.95 ± 0.151 μm, respectively [Figure 3]. These results indicated that the mean diameter of microsphere size increases with increasing content of sodium alginate polymer and the content of EPO used. The increased particle size of the microspheres may be affected by ions in the microsphere system.^[22] Increased levels of partially negatively charged (more active COO group) EPO will el the COO group of alginate, causing chain extension, increasing the viscosity of the polymer solution, and enlarging the droplet, thus increasing the particle size of the microsphere.^[23,24]

Swelling index of microspheres

Examination of swelling index of EPO-alginate microspheres was performed based on mass and particle size of microspheres at 24 and 30 h. The obtained swelling

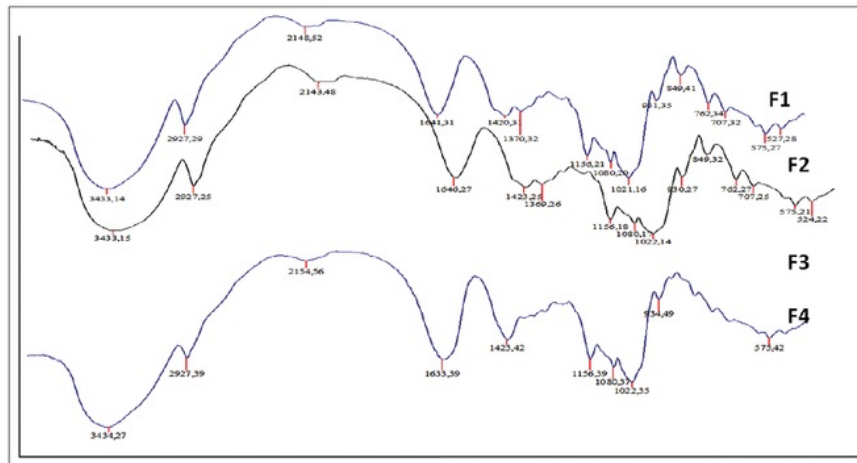


Figure 1: FTIR spectrophotometer of microspheres formula using 5000 IU EPO, alginate 2% and CaCl₂ 1M (F1), 5000 IU EPO, alginate 3% and CaCl₂ 1M (F2), 10000 IU EPO, alginate 2% and CaCl₂ 1M (F3) and 10000 IU EPO, alginate 3% and CaCl₂ 1M (F4)

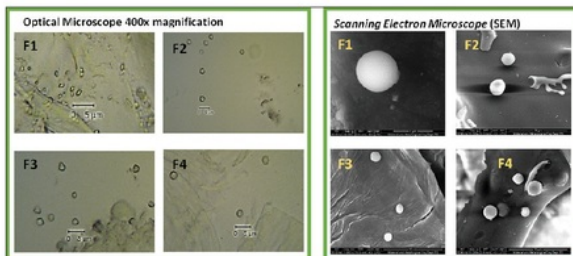


Figure 2: The shape and surface of EPO-alginate microspheres of F1, F2, F3, and F4

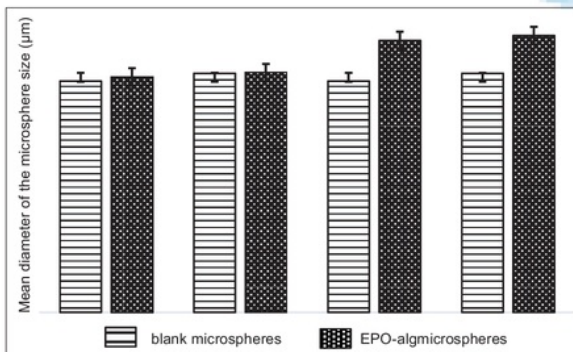


Figure 3: Histogram of blank microspheres and erythropoietin-alginate microspheres

index results are based on mass at 24 and 30 h and based on particle sizes at 24 and 30 h, respectively, on EPO-alginate microspheres as seen in Table 3.

There was no significant difference between the swelling index results based on mass and based on the particle size at the same time of observation. In addition, there was a significant difference between the swelling index results

at 24 and 30 h of observation, both based on mass and particle size. Based on the analysis with ANOVA factorial design, it was found that sodium alginate and EPO polymer content had no significant effect on swelling index based on mass or particle size both at 24 and 30 h of observation on EPO-alginate microspheres.

The swelling index data can be used to predict drug release from the microspheres accompanied with the data of the drug levels released per unit time.^[22] However, due to the limited number of EPO-alginate microspheres in the absence of assay data, this study only observed swelling indices at two observation times, each of which was replicated three times. The swelling index data of EPO-alginate microspheres ranged from 1.25 to 2.13. The values of an equilibrium state swelling index resulting in the controlled release of alginate microspheres in saline phosphate buffer are in the range of 1–2.^[17,20,25-26] It is desirable that EPO-alginate microspheres can expand by a swelling index of 1–2 for 48 h to obtain a controlled release of EPO from alginate microspheres [Figure 4].

For the yield examination of F1, F2, F3, and F4, the yield of 77.84 ± 0.290%, 86.65 ± 0.191%, 91.89 ± 0.210%, and 94.65 ± 0.252% were obtained. Based on ANOVA factorial design analysis, it can be seen that both the sodium alginate polymer and the EPO content significantly influence the yield of EPO-alginate microspheres F1, F2, F3, and F4 [Figure 5].

Design of experiment

The results of data analysis with Minitab 17.0 software (Minitab inc., PA, USA) using main effect plot to observe the effect of polymer content of sodium alginate and EPO content showed that increased sodium alginate polymer did not affect particle size, increased swelling index based on microsphere mass and particle size at 24 and 30 h,

and increased the yield of the EPO-alginate microspheres. On the other hand, an increased concentration of EPO increased the particle size, did not affect swelling index based on microsphere mass and particle size at 24 and 30 h, and increased the yield of EPO-alginate microspheres.

The results of data analysis using Pareto chart found that EPO was the most influential factor on particle size and EPO-alginate microsphere yield as shown in Figure 6. In the result of overlaid contour plot, the range of polymeric sodium alginate and EPO content was obtained, which can be used to produce optimal microsphere characteristics that include wet EPO-alginate microsphere particle sizes

of 3.15–3.85 μm . Swelling index based on mass and size of 1–2^[25,17] and the yield of EPO-alginate microsphere of 85%–100% was found in the feasible area of design space.

The optimal amount of polymer and crosslinking may affect the particle size of the microsphere.^[10] In this study, the amount of sodium alginate polymer is less than that of CaCl_2 crosslinker used, so no alginate polymer can be bonded by Ca^{2+} to thicken the microsphere layer. Ultimately, microsphere particle size did not increase with the addition of 2% and 3% sodium alginate polymers.^[10] Meanwhile, an increase in negative partially charged EPO levels will deny alginates that are also negatively charged, resulting in chain extension and increased viscosity of the solution to form droplets of enlarging microsphere particles.^[23,24,27] Increased levels of sodium alginate polymer and the active ingredient content used may result in higher microsphere yield.^[10]

From the above description, it can be concluded that the sodium alginate polymer significantly affects the yield. Meanwhile, EPO significantly affected the particle size and

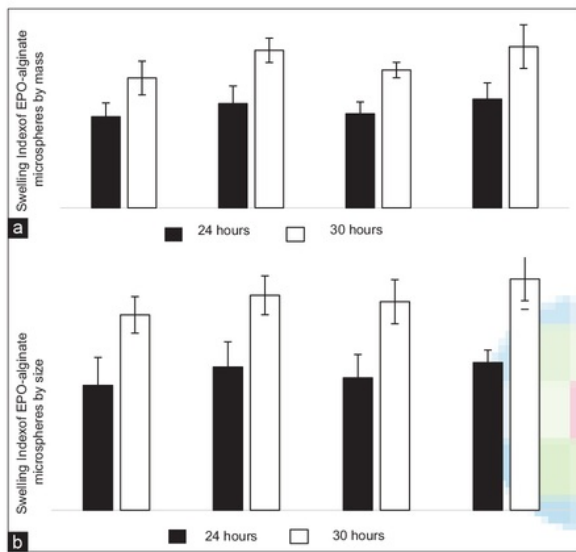


Figure 4: Swelling index of erythropoietin-alginate microspheres (a) based on mass and (b) based on size

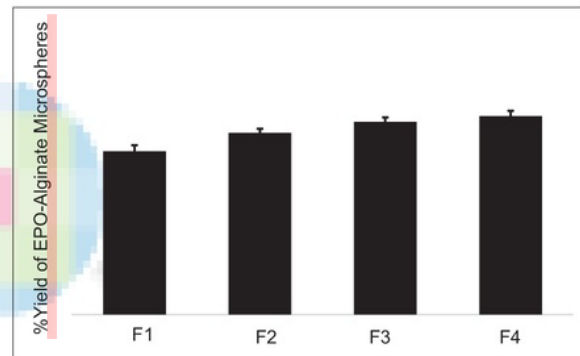


Figure 5: Microspheres yield

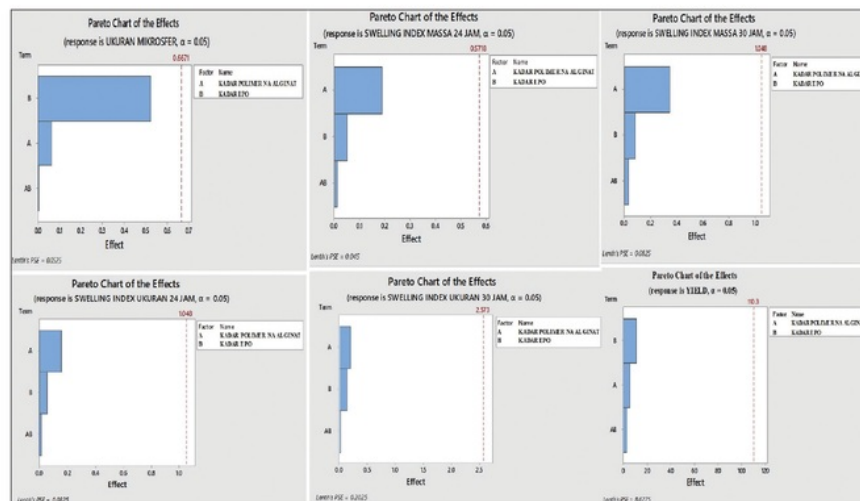


Figure 6: The Pareto chart of sodium alginate and erythropoietin polymer content to the size, swelling index of the mass and size at 24 and 30 h, and the yield of erythropoietin-alginate microspheres

yield of EPO-alginate microspheres. In addition, it is suggested that subsequent research optimizes the assaying method and the release test of EPO from alginate microspheres.

Conclusion

EPO-alginate microspheres prepared using ionotropic gelation method with aerosolization technique using 2% and 3% sodium alginate polymer levels and EPO 5000 IU and 10,000 IU levels have spherical shapes with smooth surfaces. Increased levels of sodium alginate polymer can significantly increase yield, while elevated levels of EPO can increase particle size and yield significantly. The range of sodium alginate polymer and EPO content which contained characteristics including particle size, swelling index based on mass and particle size, and optimum yield is found in the feasible area of design space as a result of overlaid contour plots with a sodium alginate content range of 2%–2.6% and an EPO content range of 7500–9500 IU.

Acknowledgments

The author would like to thank DIKTI and Faculty of Pharmacy Airlangga University who have supported this research.

Financial support and sponsorship

Nil.

Conflicts of interest

There are no conflicts of interest.

References

1. Kooij Van Der MA. Neuroprotection of newborn brain: Therapeutic targets and behavioral outcome. *Neurobiol Dis* 2010;7:65-72.
2. Puskovic V, Wolfe D, Wechuck J, Krisky D, Collins J, Glorioso JC, et al. HSV-mediated delivery of erythropoietin restores dopaminergic function in MPTP-treated mice. *Mol Ther* 2006;14:710-5.
3. Solá RJ, Griebenow K. Effects of glycosylation on the stability of protein pharmaceuticals. *J Pharm Sci* 2009;98:1223-45.
4. Kellert BA, McPherson RJ, Juul SE. A comparison of high-dose recombinant erythropoietin treatment regimens in brain-injured neonatal rats. *Pediatr Res* 2007;61:451-5.
5. Campos E, Branquinho J, Carreira AS, Carvalho A, Coimbra P, Ferreira P, et al. Designing polymeric microparticles for biomedical and industrial applications. *Eur Polym J* 2013;49:2005-21.
6. Fayed BE, Tawfik AF, Yassin AE. Novel erythropoietin-loaded nanoparticles with prolonged *in vivo* response. *J Microencapsul* 2012;29:650-6.
7. Sahil K, Akanksha M, Premjeet S, Bilandi A, Kapoor B. Microsphere: A review. *IJPPS* 2011;1:1184-98.
8. Hariyadi DM, Purwanti T, Kusumawati I, Nirmala RN, Maindra HM. Physical characterization and *in vivo* study of ovalbumin encapsulated in alginate microspheres. *Int J Drug Deliv Technol* 2015;5:48-53.
9. Comaposada J, Gou P, Marcos B, Armau J. Physical properties of sodium alginate solutions and edible wet calcium alginate coatings. *LWT Food Sci Technol* 2015;64:212-9.
10. Patil JS, Kamalapur MV, Marapur SC, Kadam DV. Ionotropic gelation and polyelectrolyte complexation: The novel techniques to design hydrogel particulate sustained, modulated drug delivery system: A review. *Dig J Nanomater Biostruct* 2010;5:241-8.
11. Hariyadi DM, Hendradi E, Purwanti T, Fadil FD, Ramadani CN. Effect of cross linking agent and polymer on the characteristics of ovalbumin loaded alginate microspheres. *Int J Pharm Pharm Sci* 2014;6:469-74.
12. Mao S, Guo C, Shi Y, Li LC. Recent advances in polymeric microspheres for parenteral drug delivery – Part 1. *Expert Opin Drug Deliv* 2012;9:1161-76.
13. Sendé R, Amighi K, Devleeschouwer MJ, Moës AJ. Studies of pectin HM/Eudragit RL/Eudragit NE film-coating formulations intended for colonic drug delivery. *Int J Pharm* 2002;197:181-192.
14. Nochos A, Douroumis D, Bouropoulos N. *In vitro* release of bovine serum albumin from alginate/HPMC hydrogel beads. *Carbohydr Polym* 2008;74:451-7.
15. Inanlou F, Khaki P, Mohammadpour N, Bidhendi SM, Zolfagharian H, Chang YF, et al. Preparation of microspheres containing leptospiral antigen using biodegradable alginate polymers. *Veterinarski Arhiv* 2015;85:395-406.
16. Bajpai SK, Kiran N. Swelling and drug release behavior of calcium alginate/poly (sodium acrylate) hydrogel beads. *Des Monomers Polym* 2016;19:89-98.
17. Shan L, Tao EX, Meng QH, Hou WX, Liu K, Shang HC, et al. Formulation, optimization, and pharmacodynamics evaluation of chitosan/phospholipid/ β -cyclodextrin microspheres. *Drug Des Devel Ther* 2016;10:417-29.
18. Nugrahani I, Asyarie S, Nurmeyna B. Solid Characterization of Crosslinks Metformin HCl / Alginate-Ca²⁺ microspheres. *Acta Pharm Indones* 2013;38:2013-9.
19. de Laia AG, de Souza Costa E Jr., de Souza Costa H. A study of sodium alginate and calcium chloride interaction through films for intervertebral disc regeneration uses. *CBECIMAT: Brazilian congress of engineering and materials science; Cuiaba, MT (Brazil)* 2014;8:p. 21.
20. Daemi H, Barikani M. Synthesis and characterization of calcium alginate nanoparticles, sodium homopolymannuronate salt and its calcium nanoparticles. *Scientia Iranica*, 2012;19:2023-8.
21. Abdelwahed W, Degobert G, Stainmesse S, Fessi H. Freeze-drying of nanoparticles: Formulation, process and storage considerations. *Adv Drug Deliv Rev* 2006;58:1688-713.
22. Eikeland ME. Alginate gels cross-linked with mixture of calcium and chitosan oligomers: Effect on swelling properties and leakage from the gel. Thesis, Trondheim: Norwegian University of Science and Technology; 2016.
23. Chaudari SA, Kar JR, Singhal RS. Immobilization of proteins in alginate: functional properties and applications. *Curr Organic Chem* 2015;19:1732-54.
24. Zhai P. Alginate microspheres for protein delivery in tissue engineering. Canada: University of Saskatchewan; 2012.
25. Chan LW, Ching AL, Liew CV, Heng PWS. Mechanistic study on hydration and drug release behavior of sodium alginate compacts. *Drug Dev Ind Pharm* 2007;33:667-76.
26. Noyes A, Godavarti R, Titchener-Hooker N, Coffman J, Mukhopadhyay T. Quantitative high throughput analytics to support polysaccharide production process development. *Vaccine* 2014;32:2819-28.
27. Theophile T. Infrared Spectroscopy: Anharmonicity of Biomolecules, Crosslinking of Biopolymers, Food Quality and Medical Applications. *Intech Open, United Kingdom*; 2015. DOI: 10.5772/58483.

Experimental Design Approach in Erythropoietin-alginate Microsphere Preparation with Different Concentrations of Drug and Polymer

ORIGINALITY REPORT

13%

SIMILARITY INDEX

10%

INTERNET SOURCES

6%

PUBLICATIONS

1%

STUDENT PAPERS

PRIMARY SOURCES

1	repository.unair.ac.id Internet Source	6%
2	www.shroffeyecentre.com Internet Source	2%
3	M.P. Hantias, L. Magafas, S.G. Stavriniades. "“Reverse Engineering” in Econophysics", International Journal of Productivity Management and Assessment Technologies, 2019 Publication	1%
4	Mao, Yimin, Ming Zhao, Yongbiao Ge, and Jiang Fan. "Novel Alginate-Chitosan Composite Microspheres for implant delivery of vancomycin and in vivo evaluation", Chemical Biology & Drug Design, 2016. Publication	<1%
5	www.ijppsjournal.com Internet Source	<1%

6	link.springer.com Internet Source	<1%
7	Submitted to Universitas Airlangga Student Paper	<1%
8	journals.plos.org Internet Source	<1%
9	www.dovepress.com Internet Source	<1%
10	IFMBE Proceedings, 2015. Publication	<1%
11	Myung-Kul Yum, Nam-Su Kim, Jae-Won Oh, Chang-Ryul Kim et al. "Non-linear cardiac dynamics and morning dip: an unsound circadian rhythm", Clinical Physiology, 2008 Publication	<1%
12	Y Sato, K Oizumi, H Kuno, M Kaji. "RETRACTED: Effect of immobilization upon renal synthesis of 1,25-dihydroxyvitamin D in disabled elderly stroke patients", Bone, 1999 Publication	<1%
13	Nguyen, Tuong Ngoc-Gia, Phuong Ha-Lien Tran, Toi Van Vo, Wei Duan, and Thao Truong-Dinh Tran. "Development of a Sustained Release Solid Dispersion Using Swellable Polymer by Melting Method",	<1%

Pharmaceutical Research, 2015.

Publication

14	www.turkjps.org Internet Source	<1%
15	newdiscoveries.org Internet Source	<1%
16	gala.gre.ac.uk Internet Source	<1%
17	banglajol.info Internet Source	<1%
18	Tahereh Dara, Alireza Vatanara, Mohsen Nabi Meybodi, Molood Alsadat Vakilinezhad et al. "Erythropoietin-loaded solid lipid nanoparticles: Preparation, optimization, and in vivo evaluation", Colloids and Surfaces B: Biointerfaces, 2019 Publication	<1%
19	tel.archives-ouvertes.fr Internet Source	<1%
20	www.ijptjournal.com Internet Source	<1%
21	nsrf.ie Internet Source	<1%
22	Beata A. Zasońska, Helena Hlídková, Eduard Petrovský, Severyn Myronovskij et al.	<1%

"Monodisperse magnetic poly(glycidyl methacrylate) microspheres for isolation of autoantibodies with affinity for the 46 kDa form of unconventional Myo1C present in autoimmune patients", *Microchimica Acta*, 2018

Publication

23

mdpi.com

Internet Source

<1%

24

M. N. V. Ravi Kumar, R. A. A. Muzzarelli, C. Muzzarelli, H. Sashiwa, A. J. Domb. "Chitosan Chemistry and Pharmaceutical Perspectives", *Chemical Reviews*, 2004

Publication

<1%

25

Oxidative Stress in Applied Basic Research and Clinical Practice, 2014.

Publication

<1%

26

Elaheh Kashani-Amin, Amirhossein Sakhteman, Bagher Larijani, Azadeh Ebrahim-Habibi. "Introducing a New Model of Sweet Taste Receptor, a Class C G-protein Coupled Receptor (C GPCR)", *Cell Biochemistry and Biophysics*, 2019

Publication

<1%

Exclude quotes Off

Exclude matches Off

Exclude bibliography On