



ICPPS 2014

Proceeding

The 1st International Conference on Pharmaceutics & Pharmaceutical Sciences

Drug Delivery Systems:
From Drug-Discovery, Pre-formulation, Formulation and Technological Approaches for
Poorly Soluble Drugs and Protein



The 1st International Conference on Pharmaceutics & Pharmaceutical Sciences Proceedings

ISBN : 978-602-72333-0-0

(Letter of National ISBN Agency No. 4127/E.8/p/03.2015 Date 18 March 2015)

1st edition Proceeding

Published by:

Faculty of Pharmacy Universitas Airlangga
Surabaya, Indonesia

Address:

Kampus B Jl. Dharmawangsa Dalam
Surabaya 60286
Phone +62 31 5033710
Fax +62 31 5020514
Website: www.icpps2014.com or www.ff.unair.ac.id
Email: icppinfo@gmail.com

ISBN 978-602-72333-0-0



TABLE of CONTENT

| | |
|-------------------------|-----|
| Preface from Chairman | |
| Committee | ii |
| Table of Contents | iii |
| Author Index | iii |

AUTHOR INDEX

| | |
|--|----|
| COMPARISON OF SODIUM STARCH GLYCOLATE AND CROSSCARMELLOSE SODIUM AS SUPERDISINTEGRANT IN MEFENAMIC ACID FAST DISINTEGRATING TABLET Adeltrudis Adelsa D, Oktavia Eka Puspita, Amalia Ayuningtyas, Marulita Isadora | 1 |
| STUDY EXPRESSION OF HUMAN ERYTHROPOIETIN EXPRESSION IN MAMMALIAN CELL Adi Santoso, Popi Hadiwisnuwardhani, Yana Rubiana, Yulaika Romadhani, Endah Puji Septisetyani, Dyanningtyas D.P. Putri | 4 |
| ANTIOXIDANT STABILITY ASSAY OF ALPHA TOCOPHERYL ACETATE IN SOLID LIPID NANOPARTICLE SYSTEM (LIPID BASE BEESWAX AND MONOSTEARIC GLISERYL 50:50) Anggie Widhi, Noorma Rosita, Widji Soeratri | 8 |
| A BIOACTIVE <i>BOVINE HYDROXYAPATITE</i> -GELATIN IMPLANT FOR IN VITRO GENTAMICIN RELEASE Aniek Setiya Budiatin, M. Zainuddin, Junaidi Khotib, Diah Himawati | 13 |
| EFFECT OF COMPARISON SURFACTANT AND COSURFACTANT IN WATER/OIL MICROEMULSION IN RELEASE OF OVALBUMIN Microemulsion Water/Oil with Surfactant (Span 80-Tween 80) : Cosurfactant (Ethanol) =5:1, 6:1, and 7:1) Anisa Rizki Amalia, Riesta Primaharinastiti, Esti Hendradi | 18 |
| ANALYSIS OF MYCOLIC ACIDS CLEAVAGE PRODUCT OF <i>Mycobacterium tuberculosis</i> BY GAS CHROMATOGRAPHY-FLAME IONIZATION DETECTOR Asri Darmawati, Deby Kusumaningrum, Isnaeni, Muhamad Zainuddin | 21 |
| PERIPLASMIC EXPRESSION OF GENE ENCODING ANTI-EGFRvIII SINGLE-CHAIN VARIABLE FRAGMENT ANTIBODY USING PeIB LEADER SEQUENCE IN <i>ESCHERICHIA COLI</i> Kartika Sari Dewi, Debbie Sofie Retnoningrum, Catur Riani, Asrul Muhamad Fuad | 24 |
| IN VIVO ANTIMALARIAL ACTIVITY OF ETHANOL EXTRACT AND ETHYL ACETATE FRACTION OF <i>Alectryon serratus</i> LEAVES ON <i>Plasmodium berghei</i> INFECTED MICE Aty Widyawaruyanti, Uswatun Khasanah, Lidya Tumewu, Hilkatul Ilmi, Achmad Fuad Hafid, Indah S Tantular | 30 |
| PROFILE OF COMMUNITY PHARMACISTS KNOWLEDGE IN PATIENT ASSESSMENT WITH INFLUENZA SYMPTOMS AND ITS PRODUCTS Azza Faturrohmah, Arie Sulistyarini, Ana Yuda | 33 |

| | |
|--|----|
| SOLUBILITY AND DISSOLUTION STUDY OF KETOPROFEN – HIDROXYPROPYL- β -CYCLODEXTRIN INCLUSION COMPLEX (Prepared by Kneading Method) Bambang Widjaja, Achmad Radjaram, Arafah Zulhana | 37 |
| FORMULATION AND STABILITY TESTING OF MELOXICAM SOLID DISPERSION GEL Budipratiwi Wisudyaningsih, Inka Dewi Nur Anggaraini, Fersiya Wardani | 40 |
| EFFECT OF MENTHOL AS PENETRATION ENHANCER TO DICLOFENAC SODIUM MEMBRANE-TYPED TRANSDERMAL PATCH CHARACTERIZATION Destria Indah Sari, Esti Hendradi, Junaidi Khotib | 43 |
| PHYSICAL CHARACTERISTICS AND RELEASE STUDY OF OVALBUMIN FROM ALGINATE MICROSPHERES PREPARED BY DIFFERENT CONCENTRATION OF ALGINATE AND BaCl ₂ USING AEROSOLIZATION TECHNIQUE Dewi Melani Hariyadi, Tristiana Erawati, Sisilia Ermawahyuningtyas | 46 |
| MUCOADHESIVE TABLET OF ETHANOLIC EXTRACT OF SAMBILOTO (<i>Andrographis paniculata</i>) AS ANTIDIABETIC USING CHITOSAN Dhadhang Wahyu Kurniawan, Hening Pratiwi, and Lingga Ikaditya | 50 |
| PHYSICAL INTERACTION STUDY OF IBUPROFEN-STEARIC ACID BINARY MIXTURE Diajeng Putri Paramita, Dwi Setyawan, Dewi Isadiartuti | 59 |
| MOLECULAR MODELING AND SYNTHESIS OF 1-(3,4-Dichlorobenzoyl)-1,3-dimethylurea Dian Agung Pangaribowo, Siswandono, Bambang Tri Purwanto | 63 |
| EXPRESSION OF RECOMBINANT HUMAN GRANULOCYTE-COLONY STIMULATING FACTOR WITHIN PERIPLASMIC COMPARTMENT OF <i>Escherichia coli</i> USING PeIB LEADER PEPTIDE Dian Fitria Agustiyanti, Asrul Muhamad Fuad | 66 |
| EVALUATION OF ANTIHYPERURICEMIC ACTIVITY FROM BULBS OF BAWANG TIWAI (<i>Eleutherine palmifolia</i> (L.) Merr.) BY IN VITRO AND IN VIVO STUDIES Dian Ratih Laksmiawati, Rininta Firdaus, Yulinda, Mediana Astika | 72 |
| ANTIOXIDANT ACTIVITY OF 96% ETHANOL EXTRACT OF COMBINATION OF STRAWBERRY FRUIT (<i>Fragaria x ananassa</i> Duch.) AND STARFRUIT (<i>Averrhoa carambola</i> L.) USING ABTS FREE RADICAL SCAVENGING METHOD Diana Serlahwaty, Indira Natalia Timang | 76 |
| ENHANCEMENT OF SOLUBILITY AND DISSOLUTION ATORVASTATIN BY MICROCRYSTALLIZATION METHOD Dolih Gozali, Yoga Windu Wardhana, Ronny Tandela | 79 |
| IN VITRO ANTIMALARIAL ACTIVITY OF DICHLOROMETHANE SUB-FRACTION OF <i>Eucalyptus globulus</i> L. Stem AGAINST <i>Plasmodium falciparum</i> Elis Suwarni, Achmad Fuad Hafid, Aty Widyawaruyanti | 86 |
| <i>Arcangelisia flava</i> INCREASES RATS' LEUKOCYTES BUT HAS BIPHASIC EFFECT ON RATS' LYMPHOCYTE Endah Puspitasari, Evi Umayah Ulfa, Vita Ariati, Mohammad SulthonHabibi | 89 |

| | |
|--|-----|
| IN VITRO ANTIMALARIAL ACTIVITY OF CHLOROFORM SUBFRACTION OF SALAM BADAK LEAVES (<i>Acmena acuminatissima</i>) Erna Cahyaningsih, Achmad Fuad Hafid, Aty Widyawaruyanti | 92 |
| CHARACTERIZATION OF DOSAGE FORM AND PENETRATION DICLOFENAC SODIUM WITH MICROEMULSION SYSTEM IN HPMC 4000 GEL BASE (Microemulsion W/O with rasio use of surfactant Span 80 – Tween 80 : Cosurfactan Ethanol 96% = 6:1) Esti Hendradi, Tutiek Purwanti, Karina Wahyu Irawati | 95 |
| CONSTRUCTION AND VALIDATION OF THE STRUCTURE-BASED VIRTUAL SCREENING PROTOCOLS WITH PDB CODE OF 3LN1 TO DISCOVER CYCLOOXYGENASE-2 INHIBITORS Mumpuni E, Nurrochmad A, Pranowo HD, Jenie UA, Istyastono EP | 99 |
| VALIDATED UV SPECTROPHOTOMETRIC METHOD FOR THE DETERMINATION OF ASPIRIN IN RABBIT PLASMA : APLICATION TO BIOAVAILABILITY STUDY OF ASPIRIN MICROCAPSULE IN RABBIT Faizatun, Novi yantih, Teguh Iman Saputra | 102 |
| EFFECT OF COMPARISON OF SURFACTANT AND COSURFACTANT W/O MICROEMULSION OVALBUMIN WITH SOYBEAN OIL TO PHYSICOCHEMICAL CHARACTERIZATION (w/o Microemulsion with Surfactant Span 80- Tween 80 : Cosurfactant Ethanol 96% = 5:1; 6:1 and 7:1) Farida Mutiara Sari, Riesta Primaharinastiti, Esti Hendradi | 105 |
| pH INFLUENCE IN DESALTING PROCESS OF CRUDE PERTUSSIS TOXIN (PT) AND FILAMENTOUS HEMAGGLUTININ (FHA) PURIFICATION FROM <i>Bordetella pertussis</i> BY SEPHADEX G-25 COLUMN CHROMATOGRAPHY Faris Adrianto, Esti Hendradi, Neni Nurainy, Isnaeni | 108 |
| SEPARATION OF COSMETIC PRESERVATIVES USING SILICA-BASED MONOLITHIC COLUMN Febri Annuryanti, Riesta Primaharinastiti, Moch. Yuwono | 111 |
| PREPARATION AND CHARACTERIZATION OF TELMISARTAN-CITRIC ACID CO-CRYSTAL Fikri Alatas, Hestiary Ratih, Sundani Nurono Soewandhie | 114 |
| PATIENTS' AND CAREGIVERS' LIQUID MEDICATION ADMINISTRATION ERRORS Gusti Noorrizka Veronika Achmad, Gesnita Nugraheni | 117 |
| THE POTENCY OF CANARIUM OIL (<i>Canarium indicum</i>) AS A MATERIAL FOR STRUCTURED LIPID PRODUCTION Hamidah Rahman, Johnner P Sitompul, Kusnandar Anggadiredja, Tutus Gusdinar | 121 |
| EFFECT OF TREHALOSE ON THERMAL PROPERTIES OF PHOSPHOLIPID-DDA AND TPGS MIXTURES Helmy Yusuf | 124 |
| PREPARATION AND CHARACTERIZATION OF FLUKONAZOLE- β -CYCLODEXTRIN INCLUSION COMPLEXES Hestiary Ratih, Fikri Alatas, Erin Karlina | 127 |
| ISOLATION AND IDENTIFICATION OF ANTIOXIDANT COMPOUND BY BIOPRODUCTION OF ENDOPHYTIC FUNGI OF TURMERIC (<i>Curcuma longa</i> L.) ISOLATE CL.SMI.RF11 Hindra Rahmawati, Bustanussalam, Partomuan Simanjuntak | 130 |

| | |
|---|------------|
| MODIFICATION PROCESS OF NATURAL CASSAVA STARCH : THE STUDY OF CHARACTERISTICS AND PHYSICAL PROPERTIES Prasetia, Jemmy A, C.I.S. Arisanti, N.P.P.A. Dewi, G.A.R. Astuti, N.W.N Yulianingsih, I M.A.G. Wirasuta | 133 |
| DRUG USE PROFILE OF DIABETIC PATIENTS IN EAST SURABAYA PRIMARY HEALTH CARE I Nyoman Wijaya, Azza Faturrohmah, Ana Yuda, Mufarriha, Tesa Geovani Santoso, Dina Kartika, Hikmah Prasasti N, Whanni Wido Agustin | 136 |
| GLYCINE MAX DETAM II VARIETY AS PREVENTIVE AND CURATIVE ORGAN DAMAGE DUE TO EXPOSURE TO ,LEAD (Pb) Rika Yulia, Sylvan Septian Ressandy, Gusti Ayu Putu Puspikaryani, I Putu Agus Yulyastrawan, Dewa Ayu Kusuma Dewi | 142 |
| AN ACTIVITY TEST OF MATOA LEAVES EXTRACT AS HEART RATE FREQUENCY REDUCTION WITH ADRENALINE INDUCTION Ika Purwidyaningrum, Elin Yulinah Sukandar, Irda Fidrianny | 144 |
| EFFORT TO REDUCE COMPRESSIBILITY OF RAMIPRIL THROUGH CRYSTAL ENGINEERING Indra, Sundani N Soewandhi | 147 |
| IN VITRO ALPHA-GLUCOSIDASE INHIBITORY ACTIVITY OF ETHANOLIC LEAF EXTRACT AND FRACTIONS OF <i>Rauvolfia serpentina</i> (L.) Benth. ex Kurz Julie Anne D. Bolaños, Ivan L. Lawag | 150 |
| PERIPLASMIC EXPRESSION OF GENE ENCODING ANTI-EGFRvIII SINGLE-CHAIN VARIABLE FRAGMENT ANTIBODY USING PeIB LEADER SEQUENCE IN <i>Escherichia coli</i> Kartika Sari Dewi, Debbie Sofie Retnoningrum, Catur Riani, Asrul Muhamad Fuad | 153 |
| CHARACTERIZATION AND LD ₅₀ VALUE DETERMINATION OF 1,5-bis(3'-ethoxy-4'-hydroxyphenyl)-1,4-pentadiene-3-one (EHP) Lestari Rahayu, Septian, Esti Mumpuni | 159 |
| DEVELOPMENT OF MELOXICAM TRANSDERMAL MATRIX TYPE PATCH USING POLYVINYLPYRROLIDONE, HYDROXYPROPYL METHYLCELLULOSE, AND ETHYL CELLULOSE COMBINATION Lidya Ameliana, Monica Iwud, Selly Rio | 162 |
| ANTIHEPATITIS C VIRUS ACTIVITY SCREENING ON <i>Harpullia arborea</i> EXTRACTS AND ISOLATED COMPOUND Lidya Tumewu, Evhy Apryani, Mei Ria Santi, Tutik Sri Wahyuni, Adita Ayu Permanasari, Myrna Adianti, Chie Aoki, Aty Widayawaruyanti, Achmad Fuad Hafid, Maria Inge Lusida, Soetjipto, Hak Hotta..... | 165 |
| HPLC METHOD PRECISION TO ASSAY OF A-MANGOSTIN IN Mangosteen (<i>Garcinia mangostana</i> L.) FRUIT RIND EXTRACT FORMULATED IN ORAL SOLUTION Lilie Nurhidayati, Siti Sofiah, Ros Sumarny, Kevin Caesar | 168 |

| | |
|---|-----|
| PREPARATION AND CHARACTERIZATION OF NARINGENIN-LOADED CHITOSAN NANOPARTICLES FOR CHEMOPREVENTION Lina Winarti, Lusia Oktora Ruma Kumala Sari | 170 |
| RELATIONSHIP OF KNOWLEDGE AND PATIENT BEHAVIOR ON SELF MEDICATION PIROXICAM (Studies of Pharmacy in Sukun District, Malang City) Liza Pristianty, Reshtia Eriana Putri, Hidayah Rachmawati | 173 |
| EFFECT OF CHRONIC USE OF ENERGY DRINK ON KIDNEY Mahardian Rahmadi, Zamrotul Izzah, Mareta Rindang A, Aniek Setya B, Suharjono | 176 |
| SCREENING OF SURFACE MODIFIERS TO PRODUCE STABLE NANOSUSPENSION : A GENERAL GUIDANCE Maria Lucia Ardhani Dwi Lestari | 179 |
| DEVELOPMENT OF SIMPLE POLYPHENOL SENSOR BASED ON SODIUM META PERIODATE AND 3-METHYL-2-BENZOTHAZOLINONE HYDRAZONE FOR COFFEE SAMPLES Moch. Amrun Hidayat, Nindya Puspitaningtyas, Agus Abdul Gani, Bambang Kuswandi | 181 |
| VALIDATION OF AN HPLC ANALYTICAL METHOD FOR DETERMINATION OF LEVOFLOXACIN IN OPHTHALMIC PREPARATIONS Mochamad Yuwono, Riesta Primaharinastiti, Ageng Teguh Wardoyo | 184 |
| VALIDATION OF SPECTROPHOTOMETRIC METHOD FOR ESTIMATION OF EPERISONE HYDROCHLORIDE IN TABLET DOSAGE FORM Nia Kristiningrum, Diah Yuli Pangesti | 187 |
| ANTIOSTEOPOROTIC ACTIVITY OF 96% ETHANOLIC EXTRACTS OF ABELMOSCHUS MANIHOT L.MEDIK LEAVES AND EXERCISE ON INCREASING BONE DENSITY OF FEMALE MICE'S FEMORAL TRABECULAR Niliestria Ayu Faramitha Sholikhah | 190 |
| EFFECT OF -CYCLODEXTRIN ON SPF VALUE AND INHIBITION OF KOJIC ACIDSTYROSINASE ACTIVITY IN VANISHING CREAM BASE FORMULATION (ON SUNSCREEN PRODUCT CONTAINED OXYBENZONE) Noorma Rosita, Diana, Diana Winarita, Tristiana Erawati, Widji Soeratri | 193 |
| ANTIMICROBIAL ACTIVITY OF LACTOBACILLI PROBIOTIC MILK AND GUAVA LEAF ETHANOLIC EXTRACT (Psidium guajava) COMBINATION AGAINST BACTERIAL CAUSE OF DIARRHEA Nur Putri Ranti, Isnaeni, Juniar Moechtar, Febri Annuryanti | 197 |
| THE INFLUENCES OF PARTICLE SIZE AND SHAPE ON ZETA POTENTIAL OF COENZYME Q10 NANOSUSPENSION Nuttakorn Baisaeng | 200 |
| SYNTHESIS, MOLECULAR DOCKING, AND ANTITUMOR ACTIVITY OF N,N'-Dibenzoyl-N,N'-Dimethylurea AGAINST HUMAN BREAST CANCER CELL LINE (MCF-7) Nuzul Wahyuning Diyah | 203 |
| EXPRESSION OF ANTI-EGFRVIII SINGLE CHAIN FRAGMENT ANTIBODY (SCFV) ON THE SURFACE OF PICHIA PASTORIS Pratika Viogenta, Asrul Muhamad Fuad, Suharsono | 206 |

| | |
|--|-----|
| SUBCLONING OF <i>csf3syn</i> (COLONY STIMULATING FACTOR-3) GENE INTO pGAP? AND TRANSFORMATION OF RECOMBINANT VECTOR INTO PICHIA PASTORIS Prety Ihda Arfia, Asrul Muhamad Fuad | 212 |
| THE USE OF PERICARP MANGOSTEEN (<i>Garcinia mangostana</i> L.) EXTRACT IN FORMULATION OF CREAM-TYPE O / W Rahmah Elfiyani, Naniek Setiadi Radjab, Mia Sagita Sofyan | 218 |
| CHITOSAN BASED PARTICULATE CARRIER OF DITERPENE LACTON OF SAMBILOTO PREPARED BY IONIC GELATION-SPRAY DRYING :EFFECT OF STIRRING RATE AND NOZZLE DIAMETER Retno Sari, Titin Suhartanti, Dwi Setyawan, Esti Hendradi, Widji Soeratri | 222 |
| GAS CHROMATOGRAPHY-MASS SPECTROMETRY METHOD VALIDATION FOR PESTICIDES RESIDUES ANALYSIS IN FOOD USING QuEChERS KIT Riesta Primaharinastiti, Setyo Prihatiningtyas, Mochammad Yuwono | 225 |
| CHARACTERIZATION OF PARACETAMOL ORALLY DISINTEGRATING TABLET USING GELATIN 1% AND 2% AS BINDER AND POLYPLASDONE XL-10 10% AS DISINTEGRANT (Prepared by Freeze Drying Method) Roisah Nawatila, Dwi Setyawan. Bambang Widjaja | 230 |
| ANTIOXIDANT STUDY OF COSOLVENT SOLUTION OF MANGOSTEEN (<i>Garcinia mangostana</i> L.) RIND EXTRACT IN RATS BY USING MDA PARAMETER Ros Sumarny, Liliek Nurhidayati, Yati Sumiyati, Fransiska Diana Santi | 233 |
| SCREENING OF SELECTED PHILIPPINE ROOT CROPS FOR β -Glucosidase INHIBITION Sarah Jane S. Almazora, Ivan L. Lawag | 236 |
| NIOSOME EMULGEL FORMULATION AND STABILITY TEST OF CINNAMON (<i>Cinnamomum burmanii</i> Nees & Th. Nees) Bark ETHANOLIC EXTRACT AS ANTIOXIDANT Sasanti Darijanto, Fidriani Irda, Widhita P.A.S | 239 |
| THEOPHYLLINE RELEASE FROM SUSTAINED RELEASE TABLET USING LACTOSA AND PVP K30 AS A CHANELLING AGENT Sugiyartono, Retno Sari, Agus Syamsur Rijal, TriMulyani, Agustina Maharani | 242 |
| EFFORTS TO PRODUCE 1-(BENZOYLOXY)UREA AS ANTICANCER DRUG CANDIDATE Suko Hardjono | 245 |
| DEVELOPMENT OF PEGylated RAPAMYCIN LITHOCHOLIC ACID MICELLE FOR CANCER THERAPY Aran Tapsiri, Kanokwan Jaiprasert, Rungtip Nooma, Awadsada Sukgasem, Supang Khondee | 248 |
| FEASIBILITY OF ORAL IMMUNIZATION AGAINST JAPANESE ENCEPHALITIS VIRUS USING CHITOSAN PARTICLES Supavadee Boontha, Worawan Boonyo, Hans E. Junginger, Tasana Pitaksuteepong, Neti Waranuch, Assadang Polnok, Narong Nitatpattana, Sutee Yoksan | 251 |

| | |
|--|-----|
| THE INFLUENCE OF HYDROXY GROUP AT ORTHO (o) AND PARA (p) POSITIONS ON METILBENZOAT AGAINST SYNTHESIS OF HIDROKSIBENZOAHIDRAZIDA DERIVATIVES Suzana, Adita R, Melanny Ika .S, Juni Ekowati, Marcellino Rudyanto, Hadi Poerwono, Tutuk Budiati | 254 |
| ANTIOXIDANT ACTIVITY TEST OF BEE PROPOLIS EXTRACT (Apis mellifera L.) USING DPPH (1,1-diphenyl-2-picrilhidrazyl) FREE RADICALS SCAVENGING ACTIVITY Titiek Martati, Shahyawidya | 258 |
| CAPSULE FORMULATION and EVALUATION COMBINATION OF AQUEOUS EXTRACT OF Phaleria's (Phaleria macrocarpa (Scheff Boerf)) FRUITS and LEAVES as ANTIHIPERTENSIVE AGENT Titta H Sutarna, Sri Wahyuningsih, Julia Ratnawati, Fahrouk P, Suci Nar Vikasari, Ita Nur Anisa | 260 |
| MANUFACTURE AND CHARACTERIZATION OF SOLID DISPERSION GLIKLAZID- PVP K90 Titta H Sutarna, Fikri Alatas, Cich Ayu Ningsih | 264 |
| ANTI-INFLAMMATORY ACTIVITY OF PARA METHOXY CINNAMIC ACID (PMCA) IN NANOEMULSION USING SOYBEAN OIL Tristiana Erawati M, Anneke Indraswari P, Nanda Ghernasih N.C, Noorma Rosita, Suwaldi Martodihardjo, Widji Soeratri | 266 |
| PHYSICAL CHARACTERISTICS AND PENETRATION OF DICLOFENAC SODIUM NIOSOMAL SYSTEM USING SPAN 20 AND SPAN 60 Tutiek Purwanti, Esti Hendradi, Noverika A. Putri, Nurtya J. Devi | 271 |
| FORMULATION AND CHARACTERIZATION OF JUICE OF LIME GEL USING CMC-Na BASE Uswatun Chasanah, Esti Hendradi, Inayah | 275 |
| HEPATOPROTECTIVE ACTIVITY OF Bidens pilosa L. IN CARBON TETRACHLORIDE INDUCED HEPATOTOXICITY IN RATS Vina Alvionita Soesilo, C.J. Soegihardjo | 278 |
| CYTOTOXIC ACTIVITY ASSAY AGAINST HELA CELL LINES OF NOVEL ANTICANCER DRUG : N-(PHENYLCARBAMOYL)ISOBUTIRAMIDE Wimzy Rizqy Prabhata, Tri Widiandani, Siswandono | 284 |
| SIMPLE STEPS PURIFICATION OF RECOMBINANT HUMAN ERYTHROPOIETIN PRODUCED IN CHINESE HAMSTER OVARY CELL CULTURE Yana Rubiyana, Endah Puji Septisetyani, Adi Santoso | 287 |
| KINETICS STUDY COCRYSTALS KETOCONAZOLE-SUCCINIC ACID PREPARED WITH SLURRY METHOD BASED ON POWDER X-RAY DIFFRACTION (PXRD) Yuli Ainun Najih, Dwi Setyawan, Achmad Radjaram | 290 |
| CONSTRUCTION OF RECOMBINANT IMMUNOTOXIN Anti-EGFRvIII scFv::HPR FUSION PROTEIN AND INDUCIBLE EXPRESSION IN Pichia pastoris AS A TARGETED DRUG CANDIDATE Yuliawati, Asrul Muhamad Fuad | 297 |
| ALTERED PHARMACOKINETIC OF LEVOFLOXACIN BY COADMINISTRATION OF ATTAPULGITE Zamrotul Izzah, Toetik Aryani, Amalia Illiyyin, Budi Suprapti | 303 |



ANTIOXIDANT STABILITY ASSAY OF ALPHA TOCOPHERYL ACETATE IN SOLID LIPID NANOPARTICLE SYSTEM (LIPID BASE BEESWAX AND MONOSTEARIC GLISERYL 50:50)

Anggie Widhi, Pharmaceutics Department Faculty of Pharmacy Universitas Airlangga, anggiewip@gmail.com,
Noorma Rosita, Pharmaceutics Department Faculty of Pharmacy Universitas Airlangga, Widji Soeratri, Pharma-
ceutics Department Faculty of Pharmacy Universitas Airlangga

ABSTRACT

Introduction : As an antioxidant, alpha tocopheryl acetate is easily degraded by light and free radical in air. Solid Lipid Nanoparticle (SLN) is a system that can provide protection of active ingredient because of its drug entrapment ability and physical protective from UV light due to its nano-sized. The aim of this study is for investigated the ability of SLN that could increase stability of antioxidant potency from alpha tocopheryl acetate. SLN is expected to have higher stability of antioxidant potency compared with simple cream.

Methods : SLN and simple cream was made SLN was made using lipid beeswax (BW) and monostearic glyceryl (GMS) as base and Tween 80 as stabilizer. SLN was produced using high shear homogenization method and simple cream was produced using hot plate magnetic stirrer. Antioxidant potency was measured by DPPH method. Sample was radiated by UV C light as free radical initiator.

Result and Discussion : Alpha tocopheryl acetate loaded in SLN system has higher stability of antioxidant potency compared with simple cream that shown with k value as constanta of antioxidant potency degradation between time. This could be due to its physical blocker of UV light and drug entrapment properties.

Conclusion : SLN was selected as antioxidant carrier due to its ability to increase antioxidant stability of alpha tocopheryl acetate.

Keywords : antioxidant, alpha tocopheryl acetate, DPPH, stability, SLN

INTRODUCTION

Solid Lipid Nanoparticle (SLN) is a dispersion system with nano-sized particles in range 40-1000 with spherical shape (Muller, 2009). SLN has widely used in cosmetic formulation because of its advantages due to its nano-sized particle such as UV protective effect and enhance emollient (Souto, 2008; Wissing, 2002).

Alpha tocopheryl acetate is derivate from tocopherol that commonly used as an antioxidant in cosmetic due to its properties of photo protective for skin and could decrease skin's damage of free radical (Nam, 2012; Tsai, 2012). As an antioxidant, alpha tocopheryl acetate is easily degraded by light and free radical in air. SLN is one of the system that could prevent the antioxidant degradation of alpha tocoph-

eryl acetate especially because the presence of light. It is result from SLN ability to scattering light with its nano-sized particles and produce physical UV protective effect (Golmohammadzadeh, 2012). The lipid matrix that contained in SLN also has the protective effect for active ingredient (Souto, 2008).

The aim for this study was for investigated the impact of SLN system with binary lipid beeswax and monostearic glyceryl (50:50) on antioxidant stability of alpha tocopheryl acetate compared with simple cream. Antioxidant activity is measured by DPPH method. Combination 50:50 of lipid component beeswax and monostearic glyceryl was selected due to the combination has higher physical stability and drug entrapment (Jenning, 2000; Rosita, 2013).



MATERIALS AND METHOD

Materials:

Tocopheryl acetate, DPPH (Sigma Aldrich), beeswax, monostearic glyceryl, tween 80, (PT. Bratako). Dapar component: acetic acid and sodium citrate (E. Merck), aquadest (PT. Jawisesa).

Instrument:

Double beam UV Spectrophotometer UV-1800 Shimadzu, One Fourier Transform Infrared (FTIR) Spectrophotometer, pH meter Eutech Instruments pH 700, Differential Thermal Analyzer (DTA), DelsaTMNano C Particle Analyzer, JEOL JEM-1400 Electron Microscope, Ultra Turax IKA® T25 Digital High Shear Homogenizer, Sentrifuge Hettich Rotofix 32, Ultrasonic LC 60h Elma, Hot plate, UV C lamp

Preparation method of SLN

SLN formed by beeswax and monostearic glyceryl (GMS) as lipid core 50: were prepared by high shear homogenization method. 10% of tween 80 was used as surfactant and 20% of propylene glycol was used as co-surfactant. Acetic buffer pH 4.2, $\mu=0,5$ was used as aqueous phase (table 1). They were stirred at 24,000 rpm for 8 minutes, with 30 seconds intervals every two minutes, using an Ultra Turax homogenizer T-25. The hot dispersion were cooled keep in stirring decreased speed gradually.

| Ingredient | Function | Concentration |
|---------------------------------|-------------------|---------------|
| Beeswax | Lipid | 10 % |
| Monostearic glyceryl | Lipid | |
| Alpha tocopheryl acetate | Active ingredient | 10% |
| Tween 80 | surfactant | 10% |
| Propilen glycol | Co-surfactant | 20% |
| Acetic buffer pH 4,2, $\mu=0,5$ | Aqueous phase | Ad 100% |

Table 1. Formula of SLN and simple cream tocopheryl acetate

Characterization of SLN

Measurement of Particle Size

Each sample was diluted with water before measurement. The particle sizes were analyzed by Delsa Nano Particle Size Analyzer at 25°C. Each measurement was performed in triplicates and the particle average diameter and polydispersity index (PI) was determined.

Observation of SLN morphology

The morphology of SLNs was observed by Transmission Electron Microscope (TEM). Either SLN blanks or SLN-PMCA were stained with phosphotungstic acid 2% w/v and placed on copper grids with former film for viewing at 120 kV (JEOL JEM-1400) and operated using software. The shape of SLN observed with Thermal Electron Microscope (TEM) and Drug entrapment of PMCA was measured by centrifugation method.

Measurement IC 50 Value of Alpha Tocopheryl Acetate

IC 50 value of alpha tocopheryl acetate was measured by DPPH method. The series of concentration of alpha tocopheryl acetate was prepared. 2 ml of sample in ethanol solution was centrifuged with 2 ml of DPPH solution. After 30 minutes absorbance of sample was measured by spectrophotometer in 517 nm.

Measurement of Antioxidant stability of Alpha tocopheryl acetate in SLN and simple cream

Each sample of SLN and simple cream alpha tocopheryl acetate was radiated by UV C light as free radical initiator. 1 gram of each sample was taken and diluted in ethanol and then centrifuged at 2500 rpm for 20 minutes. Supernatant was taken 2 ml and then mixed with 2 ml of DPPH. The reduction in DPPH radical was measured by spectrophotometer at 517 nm.

$$\% \text{ reduction} = \left\{ \frac{A_{\text{control}} - A_{\text{sample}}}{A_{\text{control}}} \right\} \times 100\%$$



RESULT AND DISCUSSION

SLN-alpha tocopheryl acetate had most spherical shape (fig 1,). Range of particle size, average of particle size and their Polydispersity Index (PI) can be seen in table 2.

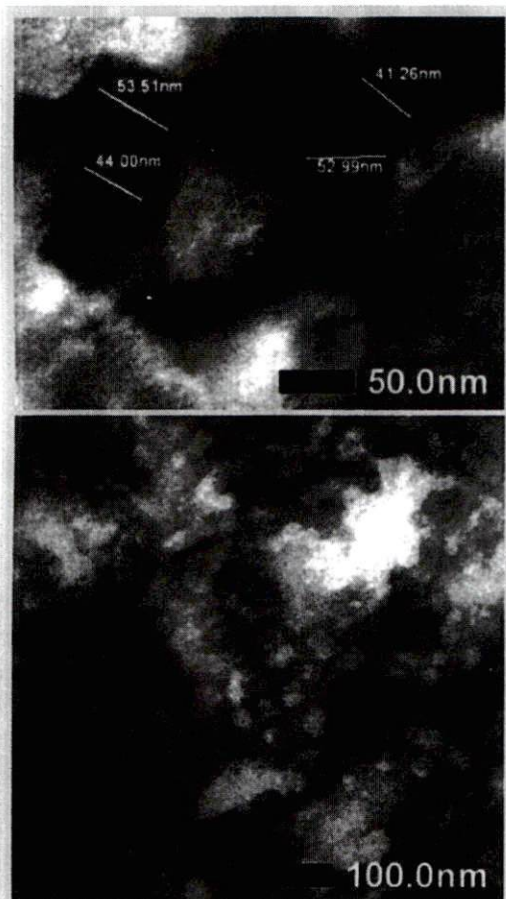


Fig 1. Morfology of SLN-alpha tocopheryl acetate measured by TEM

The existence of the particle size of SLN alpha tocopheryl acetate that are outside the range because the weakness of the manufacturing method of SLN with high shear homogenizer / high speed homogenizer which can result in the size of the microparticles in the SLN (Lason, 2011).

From table 3 it shown the IC 50 value of alpha tocopheryl acetate. The mean value of IC 50 alpha tocopheryl acetate is 2,56% ± 0,0850.

| Replication | IC 50 Value (%) | Mean of IC 50 value ± SD (%) |
|-------------|-----------------|------------------------------|
| 1 | 2,66 | |
| 2 | 2,53 | 2,56±0,0850 |
| 3 | 2,50 | |
| | | |

Table 3. IC 50 value of alpha tocopheryl acetate

The antioxidant stability of SLN and simple cream alpha tocopheryl acetate was shown in table 4 and fig.2.

| System | Replication | Diameter range (nm) | Poly-dispersity Index (PI) | Diameter (nm) | Mean of Particle size ± SD (nm)) |
|---------------------------------------|-------------|---------------------|----------------------------|---------------|----------------------------------|
| SLN alpha tocopheryl acetate | 1 | 252,2 – 2544,9 | 0,345 | 900,7 | 1087,03 ± 256,28 |
| | 2 | 353,5 – 1764,3 | 0,386 | 981,1 | |
| | 3 | 338,4 – 6184,0 | 0,530 | 1379,3 | |
| Simple cream alpha tocopheryl acetate | 1 | 727,6 – 34129,2 | 0,766 | 2302,5 | 1957,9 ± 321,95 |
| | 2 | 414,7 – 213904,4 | 0,623 | 1664,8 | |
| | 3 | 417,9 – 95650,4 | 0,642 | 1906,4 | |

Table 2. Range of particle size, average of particle size and their Polydispersity Index (PI)

Fig



Fr
th
sk
ac
sta
SL
sir
co
da
cre
alp
of
tio
toc
cur
ent
ing

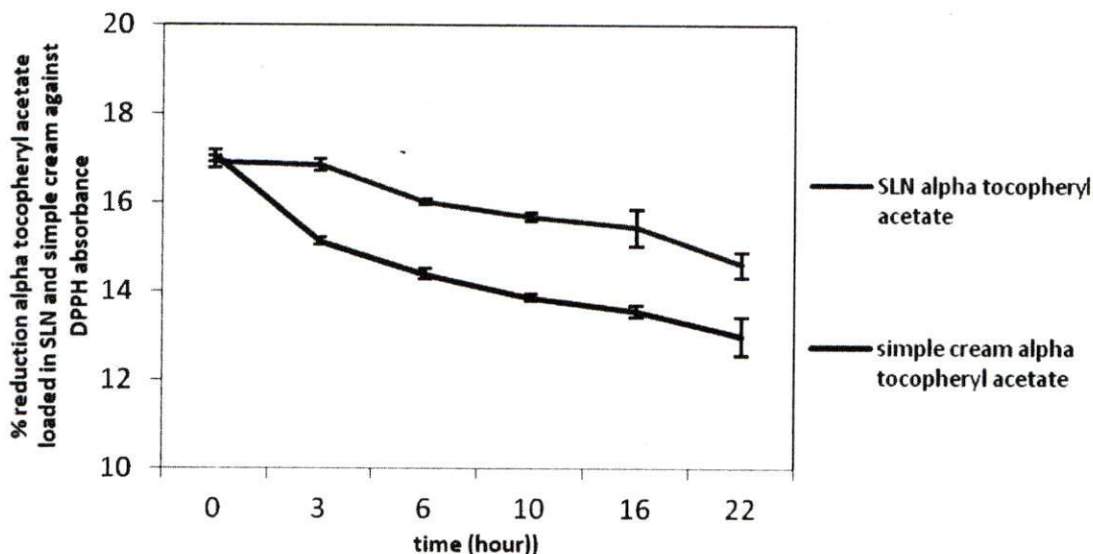


Fig. 2. Graphic % reduction alpha tocopheryl acetate loaded in SLN and simple cream against DPPH absorbance between time

| System | Replication | constanta of antioxidant potency degradation between time (/hour) | Mean of constanta of antioxidant potency degradation between time±SD |
|--|-------------|---|--|
| SLN alpha tocopheryl acetate | 1 | 0,0913 | 0,1030±0,0175 |
| | 2 | 0,0946 | |
| | 3 | 0,1232 | |
| Simple cream konvensional alpha tocopheryl acetate | 1 | 0,1714 | 0,1558±0,0169 |
| | 2 | 0,1379 | |
| | 3 | 0,1580 | |

Table 4. Constanta value of antioxidant potency degradation between time

From graphic in fig.2 it can be determined that SLN alpha tocopheryl acetate shown less sloping than simple cream alpha tocopheryl acetate. It means that decrease of antioxidant stability of alpha tocopheryl acetate loaded in SLN over the time is smaller than loaded in simple cream. This result was confirmed with constanta value of antioxidant potency degradation between time among SLN and simple cream loaded alpha tocopheryl acetate. SLN alpha tocopheryl acetate has smaller value of constanta of antioxidant potency degradation between time than simple cream alpha tocopheryl acetate. This phenomenon may occur as a result of UV blocker by SLN and drug entrapment effect of SLN that could protect active ingredient.

CONCLUSION

SLN was selected as antioxidant carrier due to its ability to increase antioxidant stability of alpha tocopheryl acetate.

REFERENCES

- Golmohammadzadeh, Shiva., Mortezaia, Somaye., Jaafari, M.R. 2012 Improved Photostability, Reduced Skin Permeation And Irritation Of Isotretinoin By Solid Lipid Nanoparticles. *Acta Pharm*, Vol 62, p.547-562
- Jenning, Volkhard., Gohla, Sven. 2000. Comparison of Wax and Glyceride Solid Lipid Nanoparticle (SLN). *International Journal of Pharmaceutics*, Vol 196, p.219-222



ICPPS 2014

Proceeding
The 1st International Conference
on Pharmaceutics & Pharmaceutical Sciences

Lason, Elwira., Ogonowski, Jan. Solid Lipid Nanoparticles – Characteristics, Application And Obtaining. 2011. CHEMIK. Vol 65, p.960-967

Muller, R.H., Hommoss, Aiman., Pardeike, Jana. 2009. Lipid Nanoparticles (SLN, NLC) In Cosmetic And Pharmaceutical Dermal Products. International Journal of Pharmaceutics, Vol 366, p.170-184

Rosita, Noorma., Soeratri, Widji. 2013. Pembuatan Dan Karakterisasi Sistem Solid Lipid Nanopartikel Asam Para Metoksisinamat (SLN-APMS) Dengan Basis: Berbagai Komposisi Beeswax dan Gliseril Monostearat. Surabaya : Universitas Airlangga

Souto, E.B., Muller, R.H. 2008. Cosmetic Features And Applications Of Lipid Nanoparticles (SLN, NLC). International Journal of Cosmetic Science, Vol 30, p.157-165

Nam, Yoong Sun., Kim, Jin-Woong., Han, Hoon Sang. 2012. Tocopheryl Acetate Nanoemulsions Stabilized With Lipid-Polymer Hybrid Emulsifiers For Effective Skin Delivery. Colloids and Surfaces B: Biointerfaces. Vol 94, p.51-57

Tsai, Feng-Jen., Wang, Yuang-Dai., Wu, Yu-Jen. 2012. Evaluation Of The Antioxidative Capability Of Commonly Used Antioxidants In Dermocosmetics By In Vivo Detection Of Protein Carbonylation In Human Stratum Corneum. Journal of Photochemistry and Photobiology B: Biology. Vol 112, p.7-15

Wissing, S.A., Muller, R.H. 2002. Solid Lipid Nanoparticles As Carrier For Sunscreens: In Vitro Release And In Vivo Skin Penetration. Journal of Controlled Release, Vol 8, p. 225-233