

# Modification of Turen's Bentonite with $\text{AlCl}_3$ for Esterification of Palmitic Acid

*by* Nanik Siti Aminah

---

**Submission date:** 17-May-2019 02:49PM (UTC+0800)

**Submission ID:** 1131908168

**File name:** BENTONIT.pdf (711.22K)

**Word count:** 3969

**Character count:** 20400



Research Article

## Modification of Turen's Bentonite with $\text{AlCl}_3$ for Esterification of Palmitic Acid

A. Abdulloh<sup>1,2</sup>, Siti Maryam<sup>2</sup>, Nanik Siti Aminah<sup>2</sup>, T. Triyono<sup>1</sup>,  
Wega Trisunaryanti<sup>1</sup>, M. Mudasir<sup>1</sup>, Didik Prasetyoko<sup>3\*</sup>

<sup>1</sup> Department of Chemistry, Faculty of Mathematics and Natural Science, Universitas Gadjah Mada, Yogyakarta, Indonesia

<sup>2</sup> Department of Chemistry, Faculty of Science and Technology, Universitas Airlangga, Surabaya, 60115, Indonesia

<sup>3</sup> Laboratory of Material Chemistry and Energy, Department of Chemistry, Faculty of Mathematics and Natural Science, Institut Teknologi Sepuluh Nopember, Surabaya, 60111, Indonesia

Received: 24th September 2013; Revised: 31st December 2013; Accepted: 26th January 2014

### Abstract

Natural Turen's bentonite has been purified, modified and applied as catalyst for palmitic acid esterification. Modification of natural Turen's bentonite was conducted by cation exchange method using  $\text{AlCl}_3$  solution. Catalyst characterization was performed on X-ray Fluorescence, X-ray Diffraction, nitrogen adsorption-desorption and infrared spectroscopy techniques. The catalytic activity test in the esterification reaction of palmitic acid with methanol was conducted by bath at 65 °C with a variation of reaction time of 1, 2, 3, 4 and 5 h. Catalytic activity has been observed qualitatively using GC-MS and quantitatively by changes in acid number. The analysis showed the formation of  $\text{Al}^{3+}$ -bentonite. Observation on the elements has shown that the presence of calcium decreased from 10.2 to 4.17 %, with an increase of aluminium content from 9.9 to 13 %. Diffraction line at  $2\theta$  5.7379° became 5.6489°, along with changes in  $d$ -spacing of 15.3895 to 15.6319 Å. The surface area increased from 83.78 to 91.26  $\text{m}^2/\text{g}$ , while Brönsted acid sites increased from 10.2 to 67.5  $\mu\text{mol}/\text{g}$  and Lewis acid sites increased from 94.9 to 132  $\mu\text{mol}/\text{g}$ . Furthermore,  $\text{Al}^{3+}$ -bentonite has showed as active catalyst in the esterification reaction of palmitic acid with palmitic acid with conversion of 78.78 % for 7 h. © 2014 BCREC UNDIP. All rights reserved

**Keywords:** natural Turen's bentonite;  $\text{Al}^{3+}$ -bentonite; esterification; palmitic acid

**How to Cite:** Abdulloh, A., Maryam, S., Aminah, N.S., Triyono, T., Trisunaryanti, W., Mudasir, M., Prasetyoko, D. (2014). Modification of Turen's Bentonite with  $\text{AlCl}_3$  for Esterification of Palmitic Acid. *Bulletin of Chemical Reaction Engineering & Catalysis*, 9 (1): 66-73. (doi:10.9767/bcrec.9.1.5513.66-73)

**Permalink/DOI:** <http://dx.doi.org/10.9767/bcrec.9.1.5513.66-73>

### 1. Introduction

Fuel scarcity is solution current issue which continues to demand the finding of new solutions. Government and the society continue to seek alternative energy sources to substitute

petroleum-based energy. One of the new and renewable energy sources (renewable resources) which could be relied upon is derived from various types of vegetable oils, as raw material for the manufacture of biodiesel. Synthesis of biodiesel from vegetable oils can be made through transesterification reaction using an acid or base catalyst. The profitable use of basic catalysts for the reaction is because of fast reaction [1]. However, the use of basic catalysts can lead

\* Corresponding Author.  
E-mail: didikp@chem.its.ac.id;  
didik.prasetyoko@gmail.com (D. Prasetyoko)

to the formation of soap if FFA content in vegetable oils is greater than 2%, which can complicate the separation of glycerol from biodiesel.

Tiwari et al. [2] reported that in order to avoid the formation of soap, the synthesis of biodiesel from *Jatropha* oil containing 14% free fatty acids can be carried out in two stages, namely esterification catalyst with  $H_2SO_4$  and transesterification with KOH catalyst to generate conversions up to 99%. The results of the conversion are slightly reduced to 90% if the FFA *Jatropha* oil contains 15% KOH in the transesterification process and replaced with NaOH [3]. Although the method is quite effective, the use of catalysts KOH, NaOH and  $H_2SO_4$  are relatively less effective in large-scale production [4]. Therefore, the catalyst used needs to be replaced with heterogeneous catalysts.

One of the heterogeneous catalysts that has been used for the esterification reaction is  $Al^{3+}$ -montmorillonite. The use of  $Al^{3+}$ -montmorillonite in the esterification reaction of succinic acid with 1-butanol can produce dibutyl succinate 94%, penilacetate acid esterification with p-cresol produced 67% p-cresol penilacetate [5], succinic acid esterification with p-cresol generated 75% p-cresol succinate [6], succinic acid esterification with isobutanol producing isobutyl succinate 94% [7], propanoic acid esterification with p-cresol ester with 88% conversion [8].

Montmorillonite is the main constituent of bentonite component. In East Java, bentonite can be found mainly in the area of Pacitan, Trenggalek, Blitar, and Malang with quartz and iron oxide as significant impurities. Based on this background, this study has been done to purify and modify the natural bentonite of Turen-Malang, East Java to  $Al^{3+}$ -bentonite via mechanical separation (purification) and apply for the esterification of palmitic acid. This due to the palmitic acid found in any vegetable oil can be used as the raw material for biodiesel production. A total of 42.47% of palmitic acid is found in red palm oil, 36.77% in palm oil, 12.43% in corn oil, 9.16% coconut oil (9) and 11.30% within *jatropha* oil [2].

17

## 2. Materials and Methods

### 2.1. Materials

Natural bentonite comes from Turen-Malang (East Java). Another materials include palmitic acid, methanol,  $AlCl_3$ ,  $H_2C_2O_4$ ,  $Na_2SO_4$ , anhydrous, KOH, ethanol, phenolphthalein indicator, bromothymol,  $AgNO_3$  and n-hexane.

1

### 2.2. Preparation and Characterization of Catalysts

Natural Turen's bentonite was purified by pouring in water with ratio bentonite:water 1:4 (wt./wt.), stirring for 15 minutes, and letting the mixture stand a day. This process was repeated seven times. Finally, one third of solids at the top was taken and dried at 110 °C for 24 h.

A total of 5 g of purified natural Turen's bentonite (said Turen's bentonite) was placed into a glass beaker containing 200 ml of 0.5 M  $AlCl_3$  and stirred with a magnetic stirrer for 24 h. The mixture was then centrifuged to separate the precipitated  $Al^{3+}$ -bentonite with a solution of  $AlCl_3$ . The  $Al^{3+}$ -bentonite was then washed with distilled water until free of  $Cl^-$  ions. Test of  $Cl^-$  ions were performed by adding 2 drops of  $AgNO_3$  0.1 M into the former washing water until no more white precipitate formed [8].

Characterization to determine the surface area and pore size of the catalyst was performed by  $N_2$  adsorption-desorption method. Concentration of elements in the samples were determined by a XRF spectrophotometer, while the structural analysis were monitored using a XRD spectrophotometer with  $CuK\alpha$  radiation ( $\lambda = 1.5405 \text{ \AA}$ ). The types and amounts of acid sites were determined using pyridine adsorption coupled with infrared spectrophotometer [8].

### 2.3. Catalytic Activity

For catalytic activity determination, a total of 0.25 grams of  $Al^{3+}$ -bentonite, palmitic acid and methanol with a molar ratio of 1:30 to palmitic acid was used in the reaction. Methanol and  $Al^{3+}$ -bentonite was mixed in the reaction flask and then refluxed for 30 minutes [10]. Further esterification reaction achieved at a temperature of 65 °C, by addition of palmitic acid into the reaction flask. To observe how the reaction of palmitic acid esterification by  $Al^{3+}$ -bentonite can take place, the reaction was stopped after 1 h, the mixture of substances in the reaction flask was taken and separated from the catalyst and methanol.

Characterization by GC-MS spectrophotometer was conducted to observe the formation of methyl palmitate. Conversion to methyl palmitate from palmitic acid ( $x(\%)$ ) was determined by changes in acid number according to the equation [11]:

$$x(\%) = \left(1 - \frac{AV_i}{AV_o}\right) \times 100\% \quad (1)$$

in which  $AV_i$  and  $AV_o$  as the number before and after esterification reaction.

### 3. Result and Discussion

#### 3.1. Characterization of $Al^{3+}$ -Bentonite Catalyst

Testing the characteristics of the structure by XRD, and elemental content by XRF samples of Turen's bentonite were done first to prove that the sample was bentonite. Based on the XRD analysis, Turen's bentonite samples have multiple diffraction angle  $2\theta$  (Figure 1):  $5.7380^\circ$ ,  $17.3511^\circ$ ,  $19.8309^\circ$ ,  $20.8906^\circ$ ,  $23.6664^\circ$ ,  $25.0697^\circ$ ,  $26.6773^\circ$ ,  $29.0217^\circ$ ,  $35.1642^\circ$ , and  $41.3079^\circ$ . The peaks have compatibility with XRD pattern of montmorillonite (bentonite constituent minerals) with PDF number 00-029-1498 ( $Na_{0.3}(Al,Mg)_2Si_4O_{10}(OH)_2 \cdot 4H_2O$ ) and clinoptilolite with PDF number 00-039-1383 ( $K,Na_2Ca_2(Si_{29}Al_7)O_{72} \cdot 24H_2O$ ) with cristobalite ( $SiO_2$ ) with PDF number 00-039-1425 and quartz ( $SiO_2$ ) with PDF number 00-046-1045 as an impurities.


The results of the XRF elemental analysis also showed that the bentonite samples contained elements of Si, Al, Ca, Mg and Fe (Table 1). The results of elemental analysis also showed isomorphous substitution of  $Al^{3+}$  in an octahedral field by  $Fe^{2+}$ , as the ratio of the amount of Si and Al in the coating unit was 2:1 (consisting of two sheets of silica tetrahedral and one sheet of alumina octahedral) on montmorillonite, without any element of O and H, was 67.47 % and 32.53 %. Results of XRF analysis of bentonite samples showed contents of Si and Al, at 43.3 % and 9.9 %, respectively. Isomorphous substitution of  $Al^{3+}$  by  $Fe^{2+}$  bentonite

deficiency caused a positive charge so that in general the montmorillonite interlayer cations that serves as a balancing charge, usually Ca or Na. Based on the results of elemental analysis (Table 1), cations balancing the charge in Turen Malang's bentonite samples were  $Ca^{2+}$ , so the bentonite samples including Ca-bentonite occurs isomorphous substitution of  $Fe^{2+}$  in octahedral field.

Characterisation of the structure and content of elements was also performed on samples of Turen's bentonite to observe changes in the structure by shifting the field (change  $2\theta$  and d-spacing) and the percentage change in Al and Ca to prove the exchange of  $Ca^{2+}$  cations in the interlayer region of  $Al^{3+}$  from  $AlCl_3$  solution. Based on the analysis of the elements of Ca and Al, Table 1 shows that the total percentage of elemental Ca decreased from 10.2 to 4.17 % and the Al elements increased from 9.9 to 13%. This suggests that there has been an exchange of cations. The cation exchange of  $Ca^{2+}$  by  $Al^{3+}$  was also observed by a shift in the field, shown by the shift in angle  $2\theta$  from  $5.7379^\circ$  to  $5.6489^\circ$  and d-spacing changes from  $15.3895 \text{ \AA}$  to  $15.6319 \text{ \AA}$  from the XRD structure analysis (Figure 2). Cation exchange processed  $Ca^{2+}$  by  $Al^{3+}$  ions due to differences in the interaction of  $Ca^{2+}$  and  $Al^{3+}$  to the siloxane cavity ( $-SiO_3$ ) on the surface of bentonite.  $Ca^{2+}$  ions interacted with the siloxane cavity in the form of hydrates forming cation outer-sphere surface complex of which bonds are weaker than the  $Al^{3+}$  ions

**Table 1.** Number and percentage of elements from natural Turen bentonite, before and after cation exchange using a solution of  $AlCl_3$

Element	Turen's bentonite (%)	$Al^{3+}$ -Turen's bentonite (%)
Al	9.90	13.00
Si	43.30	48.20
Ca	10.20	4.17
Fe	30.90	30.20
K	1.50	1.40
Cu	0.19	0.19
Ti	1.10	1.10
V	0.05	0.07
Cr	0.08	0.08
Mn	0.10	0.14
Ni	0.27	0.36
Zn	0.14	0.17
Sr	1.10	0.59
Ba	0.49	0.30
Re	0.30	0.10

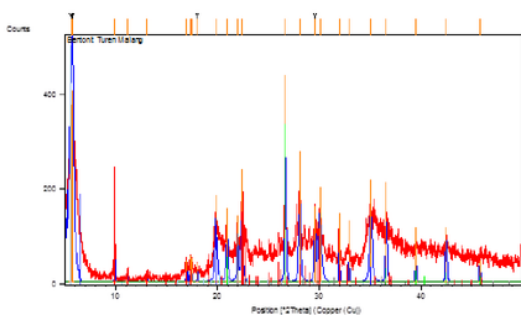


**Figure 1.** XRD pattern of Turen's bentonite

which could interact directly with siloxane cavity, forming an inner-sphere surface complex [12]. Besides, there were no other significant changes of shifting  $2\theta$  and d-spacing. This indicates that after the cation occurs exchange process, bentonite structure did not collapse.

Characterization of the surface area and the amount of acid sites was also done because both are factors that can affect the catalytic activity in heterogeneous catalytic reactions. Pyridine was used to determine of the number of acid sites in the samples. This was done because pyridine could be coordination covalently bonded with the Lewis acid sites and covalently bonded with Brönsted acid sites. Reddy et.al. [8] reported that the interaction of pyridine with Brönsted, both Brönsted and Lewis, and Lewis acid sites were observed at wavenumbers 1545, 1490, and 1450  $\text{cm}^{-1}$ , respectively. In this study, the acidity of Turen's bentonite was indicated by the peak at 1551.81, 1491.25 and 1443.44  $\text{cm}^{-1}$ . For the  $\text{Al}^{3+}$ -bentonite, the peak was indicated at 1549.40, 1489.71, and 1441.32  $\text{cm}^{-1}$  (Figure 3).

Quantitatively, the amount of acid sites was determined by area under the peak [13]. Based on FTIR spectrum curves of Turen's bentonite, peaks area at 1551.81 and 1443.44  $\text{cm}^{-1}$  were 0.3670 and 2.5745, respectively. Therefore, Turen's bentonite had Brönsted acid sites of 10.2  $\mu\text{mol/g}$  and Lewis of 94.9  $\mu\text{mol/g}$ . The peak area of 1549.40 and 1441.32  $\text{cm}^{-1}$  in the infrared spectra of  $\text{Al}^{3+}$ -bentonite were 2.4240 and 3.5825 in which  $\text{Al}^{3+}$ -bentonite having Brönsted acid sites of 67.5  $\mu\text{mol/g}$  and Lewis of 132  $\mu\text{mol/g}$ . Increasing the amount of acidity in  $\text{Al}^{3+}$ -bentonite (Brönsted from 10.2  $\mu\text{mol/g}$  to 67.5  $\mu\text{mol/g}$  and Lewis from 94.9  $\mu\text{mol/g}$  to 132  $\mu\text{mol/g}$ ) due to the ability of ion  $\text{Al}^{3+}$ -dissociated

hydrate water molecules bound to the interlayer region into  $\text{H}^+$  (equation 2) and provided an empty orbital which increased the amount of Lewis acid sites [14].



The BET surface area analysis shows that the cation exchange of  $\text{Ca}^{2+}$  by  $\text{Al}^{3+}$  caused an increased surface area of 83.781 to 91.266  $\text{m}^2/\text{g}$  and pore size increase of 6.32 to 20.09  $\text{\AA}$ . Adsorption-desorption isotherm of  $\text{Al}^{3+}$ -bentonite Turen Malang (Figure 4) showed hysteresis loup starting at  $P/P_0$  of 0.4, which is the type IV isotherm of adsorption-desorption that occurs in mesoporous materials [15].

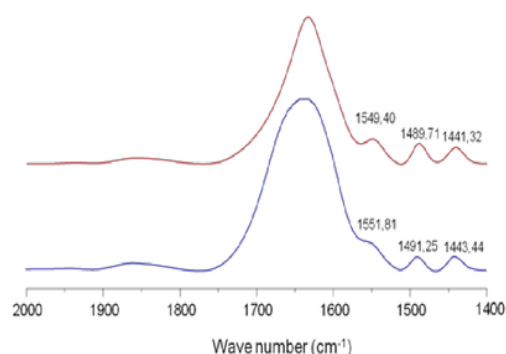


Figure 3. Infrared spectra of Turen's bentonite and  $\text{Al}^{3+}$ -Turen's bentonite after adsorption of pyridine and evacuation at 150 °C

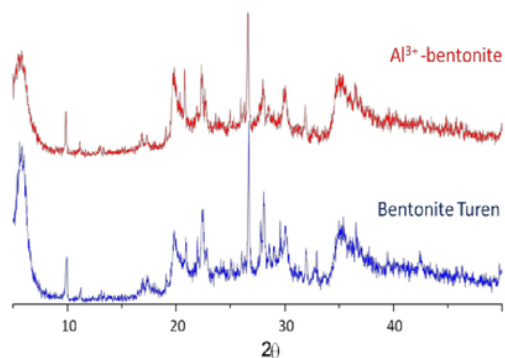


Figure 2. XRD patterns of natural Turen's bentonite and  $\text{Al}^{3+}$ -bentonite (modified from Turen's bentonite)

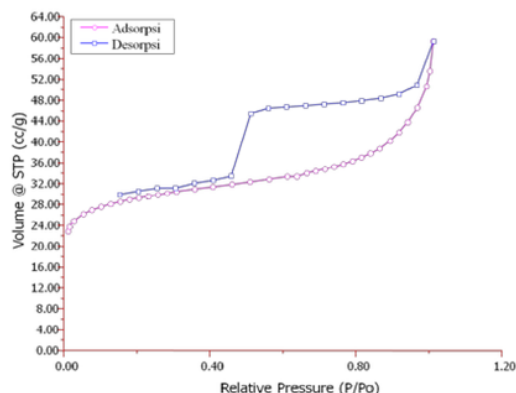


Figure 4. Nitrogen adsorption-desorption isotherm of  $\text{Al}^{3+}$ -Turen's bentonite

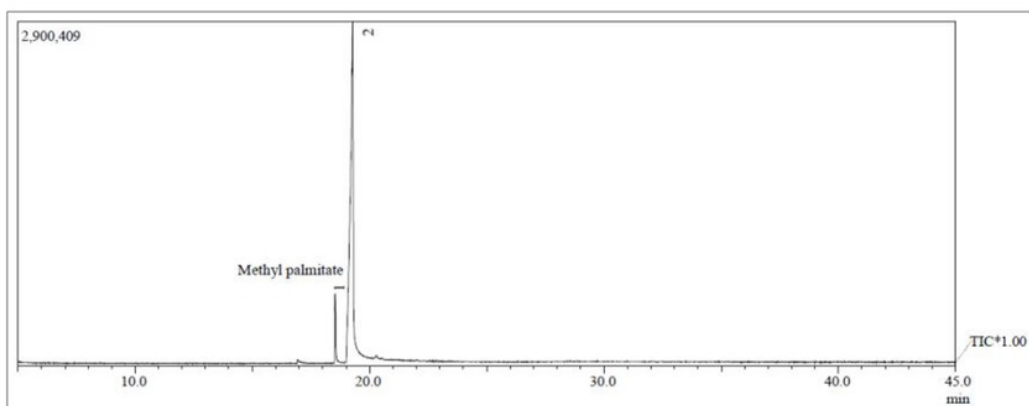


Figure 5. Chromatogram results of palmitic acid esterification

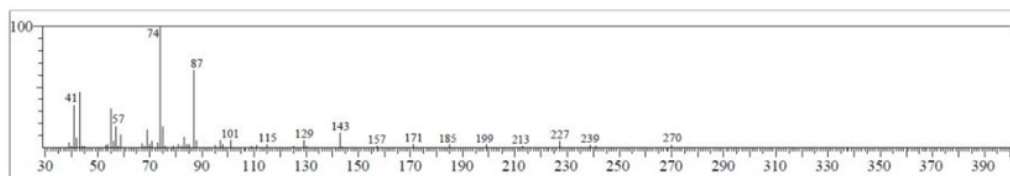


Figure 6. The mass spectra of the product of palmitic acid esterification

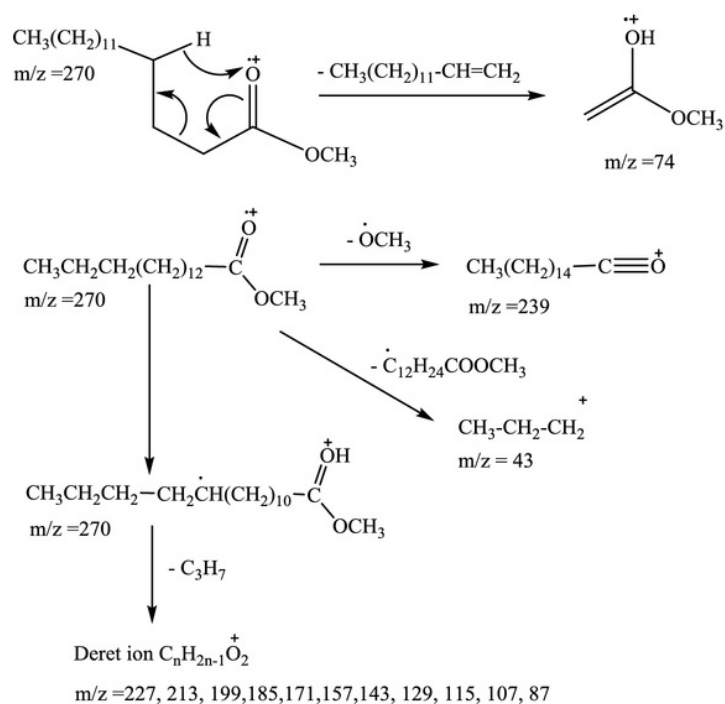


Figure 7. Mechanism of methyl palmitate fragmentation [17]


6

### 3.2 Catalytic Activity

Qualitatively, catalytic activity of  $\text{Al}^{3+}$ -bentonite in the esterification reaction between methanol to palmitic acid is determined by the formation of methyl palmitate. Analysis of methyl palmitate was performed using GC-MS on a non-polar phase, as the methyl ester is classified as a non-polar compound and mixed with fatty acids after esterification reaction. The studies on this, after esterification formed three layers, namely layer deposition of catalyst  $\text{Al}^{3+}$ -bentonite, nonpolar layers and layers of methanol (polar compounds) which have not reacted.

Based on the analysis of the GC chromatogram of the non-polar layer, a second peak was seen with a retention time of 18.536 min and 19.284 min (Figure 5). Based on the mass spectra data library, peaks on the chromatogram 1 is methyl palmitate (or similarity index SI = 95) and the top 2 are palmitic acid (SI = 95) which is a products of the esterification reaction and the reactants which did not react.


In the spectrum of peak No. 1 from the esterification reaction using catalysts  $\text{Al}^{3+}$ -bentonite (Figure 6) appeared molecular ion  $m/z$  270 derived from the  $\text{C}_{17}\text{H}_{34}\text{O}_2^+$  (ion molecule methyl palmitate), while the base peak  $m/z$  74 derived from  $\text{C}_3\text{H}_6\text{O}^+$  was formed by the breakdown of -B through McLafferty rearrangement. A fragments of  $m/z$  239 derived from the  $\text{C}_{16}\text{H}_{31}\text{O}^+$  was produced by the loss of a methoxy group from the molecular ion peak. The fragment with  $m/z$  43 was derived from the release of radical  $\text{C}_{12}\text{H}_{24}\text{COOCH}_3$ . Peaks at  $m/z$  87,

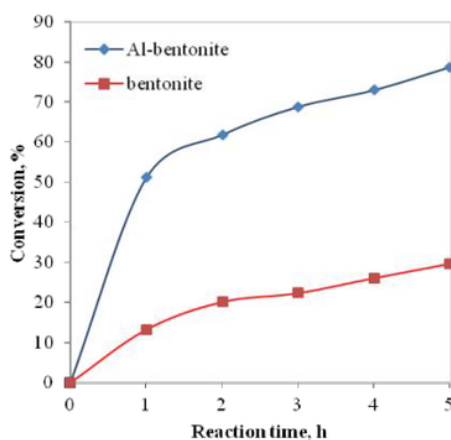

**Figure 8.** Conversion of palmitic acid in the esterification reaction using  $\text{Al}^{3+}$ -bentonite

101, 115, 129, 143, 157, 171, 185, 199, 213 and 227 were due to the fragmentation pattern of the solution at each  $\text{CH}_2\text{CH}_2$  bonds, known as ion fragmentation pattern of the series  $\text{C}_n\text{H}_{2n-1}\text{O}_2^+$  [16]. Mechanism of fragmentation of methyl palmitate is shown in Figure 7 [17].

Determination of acid number indicates that during the reaction time of 1 hour, the amount of palmitic acid converted to methyl palmitate was 51.12 % (Figure 8). Catalytic activity reaction of  $\text{Al}^{3+}$ -bentonite tended to decrease, although the resulting conversion always increased. At the beginning of the reaction, catalytic activity of  $\text{Al}^{3+}$ -bentonite was quite large at 51.12 % per 1 hour (51.12 %/h), but then decreased with increasing reaction time into 61.88 % per 2 hours (30.94 %/h), 68.48 % by the reaction of 3 hours (22.83 %/h), 73.04 % per reaction of 4 hours (18.26 %/h), and 78.78 % with a reaction time of 5 hours (15.76 %/h.) This was because the interaction of the catalyst-reactant,

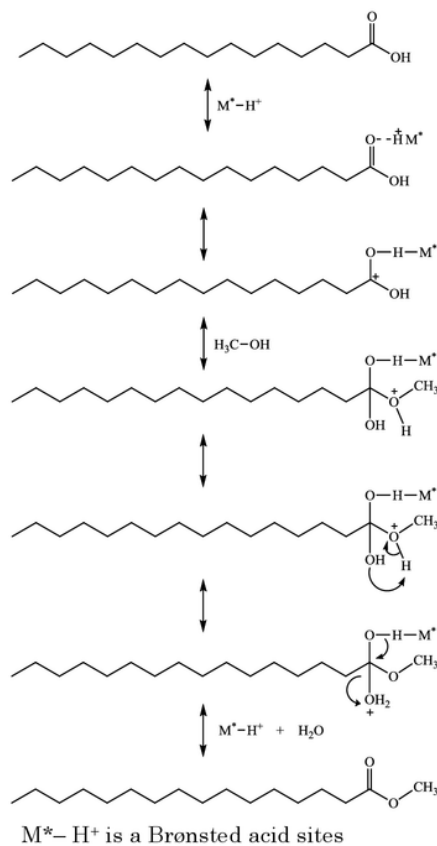

**Figure 9.** Palmitic acid esterification reaction mechanism using  $\text{Al}^{3+}$ -bentonite

catalyst-oxygen intermediates, catalysts and reaction products played a significant role in the esterification reaction with the catalyst  $\text{Al}^{3+}$ -bentonite, although the reaction mechanism of catalyst esterification which occurred in  $\text{Al}^{3+}$ -bentonite (Figure 9) was similar to the mechanism of the esterification reaction in homogeneous acid catalyst ( $\text{H}_2\text{SO}_4$ ).

Based on the principle of Sabatier, interactions of catalyst-reactant, catalyst-oxygen intermediates, catalysts and reaction products in reactions using heterogeneous catalysts must be just right. If the interactions are too weak, the reactants will move away from catalyst, so that reaction will not take place and if it happened too strong, reactants or the reaction will not leave the catalyst which could eventually poison the catalyst, or inhibit the reaction. Hydrophobicity of the surface of the catalyst in the esterification of fatty acids is a crucial factor. If the amount of Brönsted acid sites are too low, then the activity is lower. Otherwise if Brönsted acid sites appeared too much, it will lead to water adsorption and deactivation [18].

There are three types of relationship in which appeared the activity of catalyst surface hydrophobicity. Firstly, if the Brönsted acid sites appeared in an isolated environment

around hydrophobic (neutral siloxane O atoms from the surface of the  $\text{Al}^{3+}$ -bentonite), tail palmitic acid is hydrophobic which will be adsorbed parallel to the surface hydrophobic of catalyst  $\text{Al}^{3+}$ -bentonite (Figure 10a). Secondly, if there are several sites in the vicinity of Brönsted acid, fatty acid molecules can be adsorbed perpendicular to the surface (Figure 10 b). Thirdly, if the catalyst is highly acidic or hydrophilic (lots of acid sites adjacent or group hydroxyl), esterification reaction will produce water, which can be adsorbed on the surface of catalyst and will prevent access of fatty acids towards the catalyst, and thus the catalyst can lose its activity (Figure 10c). These three phenomena caused the catalytic activity of  $\text{Al}^{3+}$ -bentonite in the esterification reaction of palmitic acid changes.

#### 4. Conclusions

Turen's bentonite Malang as Ca-bentonite can be modified to be  $\text{Al}^{3+}$ -bentonite with a characteristic number of Brönsted acid sites of 67.5 mmol/g, Lewis acid sites of 132  $\mu\text{mol/g}$ , a surface area of 91.266  $\text{m}^2/\text{g}$  and also as a mesoporous material (having pores of 20, 0956 Å).  $\text{Al}^{3+}$ -bentonite can be used as a catalyst in the esterification reaction of palmitic acid into methyl palmitate by the number of conversions 78.78 % at a reaction time of 5 hours.


9

#### Acknowledgments

The authors gratefully acknowledge the financial support from Ministry of Education and Culture under "Unggulan" grant, Indonesia.

#### References

- [1] Schuchardt, U., Sercheli, R., Vargas, R.M. (1998). Transesterification of vegetable oils: A review, *J. Braz. Chem. Soc.*, 9: 199 – 210.
- [2] Tiwari, A.K., Kumar, A., Raheman, H. (2007). Biodiesel production from jatropha oil (*Jatropha Curcas*) with high free fatty acid: An optimized process, *Biomass Bioenerg.*, 31: 569 – 575.
- [3] Berchmans, H.J., Hirata, S. (2008). Biodiesel production from crude *Jatropha curcas* L. seed oil with a high content of free fatty acids, *Bioresour. Technol.* 99: 1716 – 1721.
- [4] Jothiramalingam, R., Wang, M.K. (2009). Review of Recent Developments in Solid Acid, Base, and Enzyme Catalysts (Heterogeneous) for Biodiesel Production via Transesterification, *Ind. Eng. Chem. Res.* 48: 6162–6172.

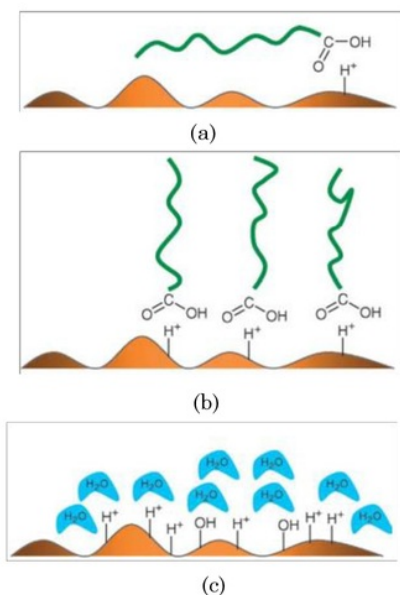

**Figure 10.** Catalyst surface hydrophobicity relations of the catalytic activity of fatty acid esterification: (a) isolated Brönsted acid sites (too little) (b) some Brönsted acid sites (too much) (c) too many Brönsted acid sites [18]



- [5] Reddy, C.R., Iyengar, P, Nagendrappa, G., Prakash, B.S.J. (2005). Esterification of succinic anhydride to di-(p-cresyl) succinate over Mn<sup>+</sup>-Montmorillonite Clay Catalysts, *J. Mol. Catal. A: Chemical*, 229: 31 – 37.
- [6] Reddy, C.R., Iyengar, P, Nagendrappa, G., Prakash, B.S.J. (2005). Esterification of dicarboxylic acid to diester over M<sup>n+</sup>-montmorillonite clay catalysts, *Catal. Lett.*, 101: 87 – 91.
- [7] Reddy, C.R., Nagendrappa, G., Prakash, B.S.J. (2005). Surface acidity of M<sup>n+</sup>-montmorillonite clay catalysts by FTIR spectroscopy: Correlation with esterification activity, *Catal. Commun.*, 8: 241 – 246.
- [8] Reddy, C.R., Bhat, Y.S., Prakash, B.S.J. (2009). Brønsted and Lewis acidity of modified montmorillonite clay catalysts determined by FT-IR spectroscopy, *Catal. Today*, 141: 157 – 160.
- [9] Dauqan, E.M.A, Sani, A.H., Abdullah, A., Kasim, M.Z. (2011). Fatty Acids Composition of Four Different Vegetable Oils (Red Palm Olein, Palm Olein, Corn Oil and Coconut Oil) by Gas Chromatography, *2nd Int. Conf. on Chem. and Chem. Eng.*, IPCBEE Vol.14, p. 31 – 34
- [10] Meunier, J.N.F.C. (2007). Esterification of free fatty acids in sunflower oil over solid acid catalysts, *Appl. Catal. A*, 333: 122 – 130.
- [11] Mengyu, G., Deng, P., Li, M., En, Y., Jianbing, H. (2009). The kinetics of the esterification of free fatty acids in waste cooking oil using Fe<sub>2</sub>(SO<sub>4</sub>)<sub>3</sub>/C catalyst, *Chinese. J. Chem. Eng.*, 17: 83 – 87.
- [12] Kehew, E.A. (2001). *Applied Chemical Hydrogeology*, Prentice Hall, New
- [13] Emeis, C.A. (1993). Determination of integrated molar extinction coefficients for infrared absorption of pyridine adsorbed on solid acid catalysts, *J. Catal.*, 141: 347 – 354.
- [14] Stylish, F., Theng, B.K.G., Lagaly, G. (2006). *Handbook of Clay Science*, 1st ed., Elsevier, Amsterdam.
- [15] Lowel, S., Shields, E.J., Thomas, A.M., Thommes, M. (2006). *Characterization of Porous Solids and Powder: Surface Area, Pore Size and Density*, Kluwer academic Publ., Dordrecht., p. 12 – 14
- [16] Silverstein, R.M., Bassler, G.C., Morrill, T.C., (1991). *Spectrometric identification of organic compounds*, Wiley, New York.
- [17] Soerya, D.M., Desi, S.H. (2003). Analisis Spektrofotometer Infra Merah dan Kromatografi Gas-Spektrometri Massa Kandungan Senyawa Non polar Ekstrak Biji Kakao (*Theobroma cacao* Linn.) Fermentasi. *J. Alchemy*, 2: 57 – 66.
- [18] Rothenberg, G. (2008). *Catalysis: Concept and Green Application*, WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim, p. 64 – 65, 186 – 187

# Modification of Turen's Bentonite with AlCl 3 for Esterification of Palmitic Acid

## ORIGINALITY REPORT

14%

SIMILARITY INDEX

8%

INTERNET SOURCES

13%

PUBLICATIONS

0%

STUDENT PAPERS

## PRIMARY SOURCES

- 1** A Abdulloh, G Supriyanto, O W Ningsih. "Adsorption of Isopropyl Alcohol (IPA) in Water Using Activated Bentonite", IOP Conference Series: Earth and Environmental Science, 2019  
Publication **5%**
- 2** [citeseerx.ist.psu.edu](http://citeseerx.ist.psu.edu)  
Internet Source **2%**
- 3** [e-journal.unair.ac.id](http://e-journal.unair.ac.id)  
Internet Source **1%**
- 4** Holilah, Holilah, Didik Prasetyoko, Titie Prapti Oetami, Eka Budiadi Santosa, Yusuf Muhammad Zein, Hasliza Bahruji, Hamzah Fansuri, Ratna Ediati, and Juwari Juwari. "The potential of Reutealis trisperma seed as a new non-edible source for biodiesel production", Biomass Conversion and Biorefinery, 2015.  
Publication **1%**
- 5** [kimia.fst.unair.ac.id](http://kimia.fst.unair.ac.id)  
Internet Source **1%**

6

Wang, Lingtao, Xiuqin Dong, Haoxi Jiang, Guiming Li, and Minhua Zhang. "Ordered mesoporous carbon supported ferric sulfate: A novel catalyst for the esterification of free fatty acids in waste cooking oil", Fuel Processing Technology, 2014.

Publication

<1%

7

Suwito, Hery, EmptyYN="Y" Jumina, EmptyYN="Y" Mustofa, Pratiwi Pudjiastuti, Much Fanani, Yoko Kimata-Ariga, Ritsuko Katahira, Toru Kawakami, Toshimichi Fujiwara, Toshiharu Hase, Hasnah Sirat, and Ni Puspaningsih. "Design and Synthesis of Chalcone Derivatives as Inhibitors of the Ferredoxin — Ferredoxin-NADP+ Reductase Interaction of Plasmodium falciparum: Pursuing New Antimalarial Agents", Molecules, 2014.

Publication

<1%

8

[uad.portalgaruda.org](http://uad.portalgaruda.org)

Internet Source

<1%

9

[ejournal2.undip.ac.id](http://ejournal2.undip.ac.id)

Internet Source

<1%

10

M. Bengi Taysun, Emine Sert, Ferhan S. Atalay. "Effect of Hydrogen Bond Donor on the Physical Properties of Benzyltriethylammonium Chloride Based Deep Eutectic Solvents and

<1%

# Their Usage in 2-Ethyl-Hexyl Acetate Synthesis as a Catalyst", Journal of Chemical & Engineering Data, 2017

Publication

11

[manualzz.com](http://manualzz.com)

Internet Source

<1%

12

[docplayer.net](http://docplayer.net)

Internet Source

<1%

13

Liu, Hongmei, Dong Liu, Peng Yuan, Daoyong Tan, Jingong Cai, Hongping He, Jianxi Zhu, and Zhiguang Song. "Studies on the solid acidity of heated and cation-exchanged montmorillonite using n-butylamine titration in non-aqueous system and diffuse reflectance Fourier transform infrared (DRIFT) spectroscopy", Physics and Chemistry of Minerals, 2013.

Publication

<1%

14

[documents.mx](http://documents.mx)

Internet Source

<1%

15

[pubs.acs.org](http://pubs.acs.org)

Internet Source

<1%

16

Sevim, A.M.. "An investigation of the kinetics and thermodynamics of the adsorption of a cationic cobalt porphyrine onto sepiolite", Dyes and Pigments, 201101

Publication

<1%

17

Francisco Luna, Juan Cecilia, Rosana Saboya, Deicy Barrera, Karim Sapag, Enrique Rodríguez-Castellón, Célio Cavalcante. "Natural and Modified Montmorillonite Clays as Catalysts for Synthesis of Biolubricants", *Materials*, 2018

Publication

&lt;1%

18

C. Ravindra Reddy. "Esterification of dicarboxylic acids to diesters over Mn<sup>+</sup>-montmorillonite clay catalysts", *Catalysis Letters*, 05/2005

Publication

&lt;1%

19

Endalew, A.K.. "Inorganic heterogeneous catalysts for biodiesel production from vegetable oils", *Biomass and Bioenergy*, 201110

Publication

&lt;1%

20

[www.scribd.com](http://www.scribd.com)

Internet Source

&lt;1%

21

Didik Prasetyoko. "Tungsten Oxides-Containing Titanium Silicalite for Liquid Phase Epoxidation of 1-octene with Aqueous Hydrogen Peroxide", *Catalysis Letters*, 03/2009

Publication

&lt;1%

22

Lu-Cun Wang, Qian Liu, Miao Chen, Yong-Mei Liu, Yong Cao, He, Kang-Nian Fan. " Structural

&lt;1%

Evolution and Catalytic Properties of Nanostructured Cu/ZrO Catalysts Prepared by Oxalate Gel-Coprecipitation Technique ", The Journal of Physical Chemistry C, 2007

Publication

---

23

Xu, Bin, Carsten Sievers, Johannes A. Lercher, J. A. Rob van Veen, Patricia Giltay, Roel Prins, and Jeroen A. van Bokhoven. "Strong Brønsted Acidity in Amorphous Silica–Aluminas", The Journal of Physical Chemistry C, 2007.

Publication

---

<1%

24

Alabi, Wahab, Luqman Atanda, Rabindran Jermy, and Sulaiman Al-Khattaf. "Kinetics of toluene alkylation with methanol catalyzed by pure and hybridized HZSM-5 catalysts", Chemical Engineering Journal, 2012.

Publication

---

<1%

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

# Modification of Turen's Bentonite with AlCl<sub>3</sub> for Esterification of Palmitic Acid

---

GRADEMARK REPORT

---

FINAL GRADE

**/0**

GENERAL COMMENTS

**Instructor**

---

PAGE 1

---

PAGE 2

---

PAGE 3

---

PAGE 4

---

PAGE 5

---

PAGE 6

---

PAGE 7

---

PAGE 8

---