

Jurnal KIMIA RISET

Volume 2 No. 2, Desember 2017; ISSN: 2528-0414; e-ISSN: 2528-0422

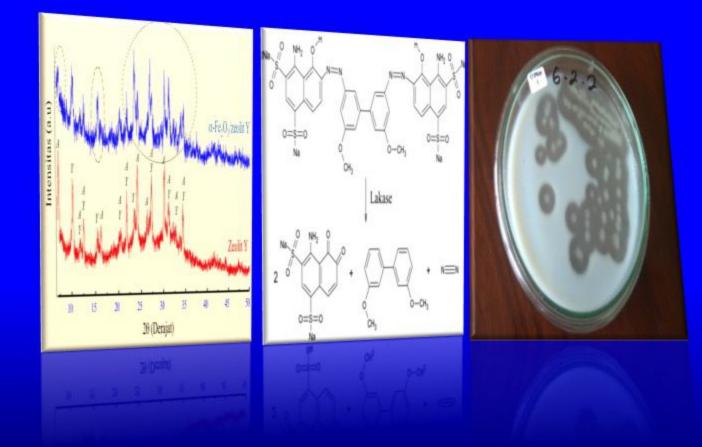

Departemen Kimia Fakultas Sains dan Teknologi Universitas Airlangga http://e-journal.unair.ac.id/index.php/JKR



Jurnal **KIMIA RISE** p-ISSN: 2528-0414 e-ISSN: 2528-0422

CURRENT

ARCHIVES

ANNOUNCEMENTS

Departemen Kimia Fakultas Sains dan Teknologi Universitas Airlangga

Instruction for Author Guide for authors **Online Submission**

Document Template

Journal Policy

Focus and Scope

Publication Ethics

Peer Reviewers

Editorial Team

Contact

Username

Password

View Subscribe

Search Search Scope All

Browse

By Issue By Author

By Title Other Journals

For Readers For Authors For Librarians

Phytoche

Remember me

Article Processing Charge

Open Access Statement Plagiarism Copyright

USER

NOTIFICATIONS

JOURNAL CONTENT

INFORMATION

KEYWORDS

Alkaline protease, Chicken feces, Gallus gallus bankiva, Pseudomonas sp Alkaloid turunan furokuinolin, skimmianin. Toddalia asiatica L, antikanker Analytical Chemistry

Antoxidant, S. polycystum, I. deccurens, Dutungan island DENV-2, 2-isopropanol, Methanol, Chloroform, Ethanol 96%, RNA Isolation Dioscorea hispida Dennst, Dioscoreaceae, phenolic, 4-ethoxy-3-methoxyphenol, methyl-3,4-dihydroxybenzoic, actionidane Goardome, Unidum antioxidant Ganoderma lucidum, senyawa fitokimia, GCMS Inorganic Chemistry RNA, Precipitation Solvent, DMF, EDTA, Ultrapure H2O Selada merah (Lactuca sativa var. Crispa), sitotoksik, Artemia salva val. crispa), sitotoksik, Artemia salva val. crispa), zSM-5, metakaolin, terdealuminasi, tanpa templat, pengaturan suhu dan waktu antibakteri, Enterobacter aerogenes, Mangifera foetida L., metanol asam amino, besi, nanomagnetit, dan mineral enzym biodegradation, fungus enzyme fenil propanoid, skopoletin, dan Ipomoea batatas L. fotokatalitik methanol.

mical screening, Piper betle L. var Nigra. methyloleate, catalyst, Ni/H5NZ,hydrocracking remazol red 198

nggang

Antifungal preparations, Candida albicans, Betel leaf (SDS), Geling leaf extract (Cassia alata L.) Antioxidant, S. polycystum, T.

Home > About the Journal > Editorial Team

LOGIN

REGISTER

EDITORIAL TEAM

SEARCH

EDITOR-IN-CHIEF

ABOUT

номе

Dr. Purkan Purkan, Department of Chemistry, Faculty of Science and Technology, Airlangga University

VICE EDITOR-IN-CHIEF

Dr Abdulloh Abdulloh, Department of Chemistry, Faculty of Science and Technology, Airlangga University

EDITORIAL BOARD

Prof. Ni Nyoman Tri Puspaningsih, Department of Chemistry, Faculty of Science and Technology, Airlangga

Prof. Nur-Yunan Trospannigsin, Department of Chemistry, National Sun Yat-sen University, Kaohsiung, 80424, Taiwan Prof. Chun-Hu Chen, Department of Chemistry, National Sun Yat-sen University, Kaohsiung, 80424, Taiwan Prof. Punnapayak Hunsa, Faculty of Science, Chulalongkorn University, Bangkok, 10330, Thailand Dr.rer.nat Ganden Supriyanto, Department of Chemistry, Faculty of Science and Technology, Airlangga University

Dr. Hery Suwito, Department of Chemistry, Faculty of Science and Technology, Airlangga University


MANAGING EDITOR

Dr. Imam Siswanto, Department of Chemistry, Faculty of Science and Technology, Airlangga University Rico Ramadhan, Ph.D, Department of Chemistry, Faculty of Science and Technology, Airlangga University Qurrota A'yuni, M.Si, Department of Chemistry, Faculty of Science and Technology, Airlangga University Fatiha Khairunnisa, M.Si, Department of Chemistry, Faculty of Science and Technology, Airlangga University

ADMINISTRATION SUPPORT


Fendi Kristanto, Department of Chemistry Faculty of Science and Technology Universitas Airlangga Oktavia Wahyu Ningsih, Department of Chemistry Faculty of Science and Technology Universitas Airlangga





Jurnal KIMIA RISET P-ISSN: 2528-0414 e-ISSN: 2528-0412

Departemen Kimia Fakultas Sains dan Teknologi Universitas Airlangga

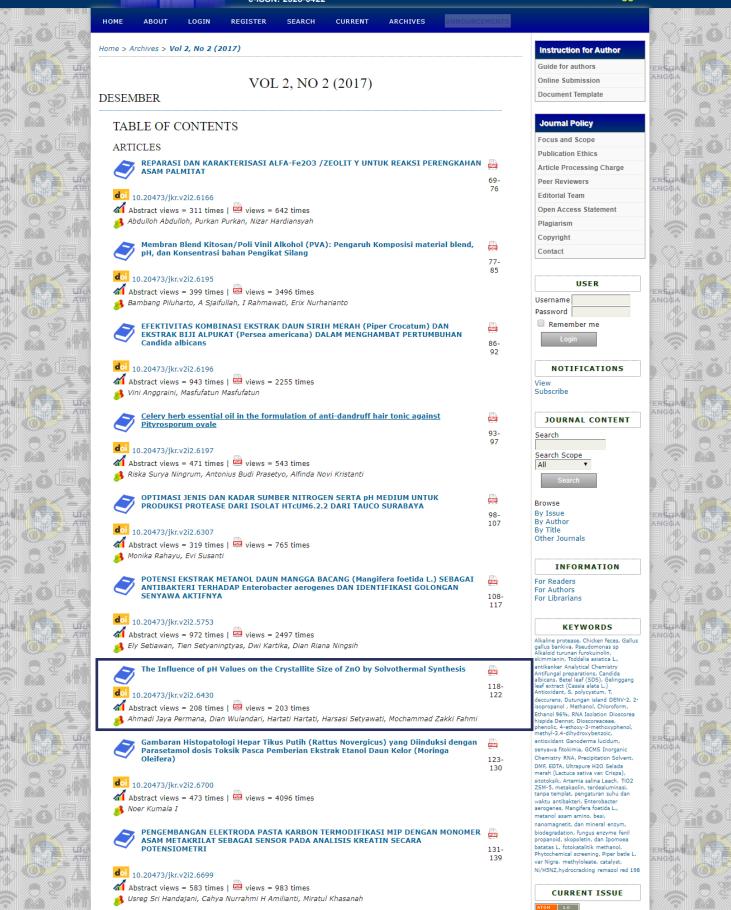



Jurnal Kimia Riset

elSSN : 2528–0422 | plSSN : 2528–0414

<u>Science</u> <u>Universitas Airlangga</u>

Asînta

S3

Sinta Score

👽 🍖 garuda

Indexed by GARUDA

3

H-Index

З H5-Index

15

Citations

15

5 Year Citations

118 - 122

THE INFLUENCE OF PH VALUES ON THE CRYSTALLITE SIZE OF ZnO SOLVOTHERMAL SYNTHESIS

Ahmadi Jaya Permana^{*}, Dian Wulandari, Hartati, Harsasi Setyawati, Mochamad Zakki Fahmi

> Department of Chemistry Faculty of Science and Technology Universitas Airlangga *email: ahmadi-j-permana@fst.unair.ac.id

> > Received 11 Nopember 2017 Accepted 28 Nopember 2017

Abstract

Zinc oxide (ZnO) is a semiconductor material that widely used in various applications due to its unique properties. Synthesis of ZnO by solvothermal method has been conducted with controlled pH values. The variations of pH value were 10, 11 and 12 by adjusting NaOH content. Crystall structure of the synthesis products after heat treatment at 110oC and 600oC has been characterised by X-ray Diffratometer (XRD). Crystallite size of ZnO was calculated by Scherrer equation. Crystall phase of ZnO has been observed on all pH value variations at 110 oC with 22,98-37,06 nm of crystallite size, whereas ZnO has been observed on all pH value variations at 600 oC with 41,39-71,77 nm of crystallite size.

Keywords: ZnO, pH values, crystallite size, solvothermal

Introduction

Zinc oxide (ZnO) as semiconductor material has high stability in chemical, mechanical, photoradiation and thermal, board band gap energy and good in electrochemical and photochemical (Kołodziejczak-radzimska, properties 2014). As a semiconductor material, ZnO is widely used as promising materials for electronic and optoelectronic applications such as laser diodes, photoelectrodes, LEDs and gas sensors. Besides electronic application, ZnO is also catalyst that has lewis acid and basic for organic (Kothandapani, compounds synthesis In health and environmental 2016). application like medicine, biomedical diagnosis and therapy, water treatment, photodegradation. waste ZnO has antimicrobial (Król, 2017), antioxidant (Zare, 2017) and photocatalytic properties (Atchudan, 2017). According to versatile applications, ZnO is still attractive

materials to be investigated especially in synthesis development.

Synthesis of ZnO by solvothermal method is an alternative method to produce single-crystalline nanostructure, controlled size and shape (Rai, 2013). In addition, solvothermal synthesis is able to produce fine and uniform nanoparticle (Sari, 2015). This method performance is influenced by reaction environment such as precursor, solvent and additives (An, 2015). Precursor, solvent and additives affect microstructures, morphology and the properties of product (Zare, 2017). Synthesis of ZnO by solvothermal method basicly is conducted in base environment. As an important factor, the influence of pH on ZnO synthesis has been investigated in this work

In this research, ZnO has been synthesized by facile solvothermal method in various pH then continued with heat treatment process at 110°C and 600°C. The influences of pH have been studied by X- ray diffraction method to study the crystall structures and crystallite size. Crystallite size average was calculated using Scherrer method.

Materials and Methods

Materials

Zinc acetate dihydrate $(Zn(CH_3COO)_2.2H_2O, 99\%)$, sodium hydroxide (NaOH, 98%), ethanol absolute were purchased from Sigma-Aldrich, that used without further purification.

Methods

Synthesis of ZnO

Synthesis of ZnO has started by dissolving of 2 gram $Zn(CH_3COO)_2.2H_2O$ in 100 mL ethanol absolute until homogenous. The solution of NaOH 2 M in ethanol was then added drop wise into $Zn(CH_3COO)_2$ to adjust pH values to 10, 11 and 12 while still stirred constantly and heated at 75 °C for 8 hours. The mixtures were then digest at room temperature for 24 hours. The percipitates were formed during this process then filtered and washed with demineralised water. After this, the precipitates were heated at 110°C and 600°C for 5 hours, respectively.

Characterisation of ZnO

Phase and crystall structure was analyzed on a X-ray diffractometer (XRD) X'PERT-PRO PA using CuK α radiation (λ = 1,5418 Å) for 2 θ values for 20-80°. Crystallite size was measured by X-ray peak profile analysis and calculated by Debye-Scherrer equation (Thomas, 2014).

$$D = \frac{\kappa \lambda}{\beta_{hkl} \cos\theta} \tag{1}$$

where D is crystallite size, K is Scherrer constant equal to 0,90, λ is X-ray wavelength for CuK α radiation equal to 1,5418 Å, β_{hkl} is full width at half maximum (FWHM) of XRD peak and θ is diffraction angle.

Results and Discussion

Herein, white powders of ZnO were sucessfully synthesised by solvothermal method at all variations of pH value and at all temperature heat treatment. These results are following precipitation reaction of Zn(OH)₂ then transformed to ZnO by heating process (Kołodziejczakradzimska, 2014)

Elimination of Na(CH₃COO) and H₂O as side products was conducted by washing and heating process so that can produce single product of ZnO. Figure 1 shows the difractogram of ZnO with similar XRD peaks pattern of all pH variation at 110°C. The XRD peaks pattern are indexed to JCPDS 36-1451 that confirm the hexagonal wurtzite phase of ZnO. There are no other crystalline phase detected that mean this synthesis method produce single crystalline phase of ZnO. Besides all pH variation show similar pattern, the XRD peak intensity ratio are quite similar at all pH variations

Single cristallinity of hexagonal wurtzite phase of ZnO showed on Figure 2. Peak intensity of XRD increased at all pH value along the increasing of temperature from 110°C to 600°C. Similar results with heat treatment at 110°C, XRD peak intensity ratio are quite similar at all pH value that indicates similar shape and morphology formation (Jaimeewong, 2016)

$$Zn(CH_3COO)_2 + NaOH \rightarrow Zn(OH)_2 + 2 Na(CH_3COO)$$
(2)

$$Zn(OH)_2 \xrightarrow{\Delta} ZnO+H_2O$$
 (3)

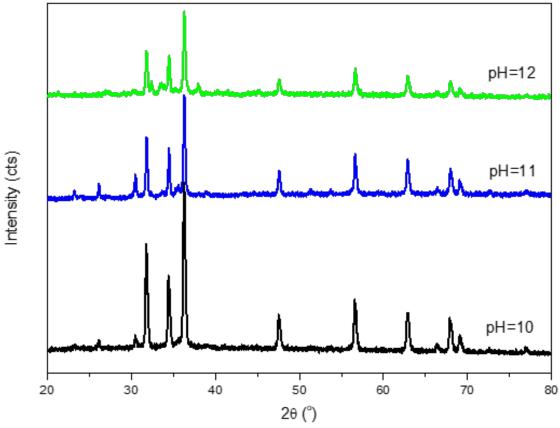


Figure 1. XRD diffactograms of ZnO products of different pH variation at 110°C

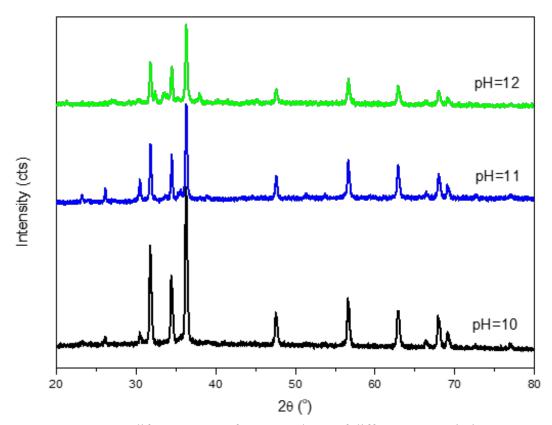


Figure 2. XRD diffactograms of ZnO products of different pH variation at 600°C

	Table 1.	Table I. Crystallite size average of ZnO			
-	Temperature (°C)	Crystallite Size Average (nm)			
_		рН =10	pH = 11	pH =12	
_	110	22,98	37,06	26,12	
	600	71,77	54,23	41,39	

4 11.4 C7 0

The influence of pH value variations to crystallite size of ZnO can be oberved on Table 1. At 110°C, there are no corelation results about the influence of pH value to ZnO crystallite size due to the diffrence of products transformation to ZnO. The product formation before heat treatment at pH 10 are dominantly Zn(OH)₂, product at pH 11 are dominantly Zn(OH)₂ and $Zn(OH)_3$ and product at pH =12 are dominantly $Zn(OH)_3$ (Pandit, 2017). The increased of heat temperature increase the crystallite size of ZnO because the inccreased of aggregation process (Jaimeewong, 2016). The influence of pH value observed the decreased of the crystallite size from 10 to 12. The function of NaOH on solvothermal method as mineraliser and catalyst (An, 2015) can be

References

An, A., Marin, M., Crnjak, Z., and Majda, Ž. (2015). Basic zinc carbonate as a solvothermal precursor in the synthesis of nano-zinc oxide, 86, 347-353.

http://doi.org/10.1016/j.matdes.2015. 07.087

Atchudan, R., Nesakumar, T., Immanuel, J., Perumal, S., Shanmugam, M., and Journal Rok, Υ. (2017). of Photochemistry and Photobiology A: Direct Chemistry solvothermal synthesis of zinc oxide nanoparticle decorated graphene oxide nanocomposite for ef fi cient photodegradation of. "Journal of Photochemistry and Photobiology, A: Chemistry," 337, 100-111. http://doi.org/10.1016/j.jphotochem.2 017.01.021

the reason about the decreased of the crystallite size.

Conclusions

To conclude, ZnO have successfully been synthesized by solvothermal method. ZnO were formed in all of pH values variation at both 110°C and 600°C temperature of heat treatment. Synthesis of ZnO at pH = 10 at 600° C resulted highest XRD peak intensity and greatest crystallite average size to 71,77 nm.

Acknowledgements

We thank to Faculty of Science and Technology for the financial support by Hibah Dosen Muda Dana RKAT Fakultas Sains dan Teknologi Universitas Airlangga Nomor Tahun 2017 SP POPA 628/UN3.6/KU/2016.

Jaimeewong, P., Promsawat. М., Jiansirisomboon, S., and Watcharapasorn, A. (2016). Surface and Coatings Technology In fl uence of pH values on the surface and properties of BCZT nanopowders synthesized via sol-gel autocombustion method. Surface and Coatings Technology, 306(3), 16–20. http://doi.org/10.1016/j.surfcoat.2016 .03.091

Kołodziejczak-radzimska, A., and Jesionowski, T. (2014). Zinc Oxide-From Synthesis to Application: A 2833-2881. Review, http://doi.org/10.3390/ma7042833

- Kothandapani, J., Ganesan, A., and Kumar, G. (2016). Zinc oxide surface: a versatile nanoplatform for solvent-free synthesis of diverse isatin derivatives. *Tetrahedron Letters*, *57*(31), 3472–3475. http://doi.org/10.1016/j.tetlet.2016.06 .094
- Król, A., Pomastowski, P., Ra, K., and Buszewski, B. (2017). Zinc oxide nanoparticles: Synthesis antiseptic activity and toxicity mechanism. http://doi.org/10.1016/j.cis.2017.07.0 33
- Pandit, A. B., and Badnore, A. (2017).
 Effect of pH on sonication assisted synthesis of ZnO nanostructures: Process details Corresponding author. *Chemical Engineering and Processing: Process Intensification.* http://doi.org/10.1016/j.cep.2017.09. 013
- Rai, P., Kwak, W., and Yu, Y. (2013). Solvothermal Synthesis of ZnO Nanostructures and Their Morphology-Dependent Gas-Sensing Properties.

- Sari, A., Stefani, G., and Dra, G. (2015). Solvothermal synthesis of zinc oxide microspheres, 652, 91–99. http://doi.org/10.1016/j.jallcom.2015. 08.200
- Thomas, P. B. S. (2014). Estimation of lattice strain in ZnO nanoparticles : Xray peak profile analysis, 123–134. http://doi.org/10.1007/s40094-014-0141-9
- Zare, M., Namratha, K., Byrappa, K., Surendra, D. M., Yallappa, S., and Hungund, B. (2017). Surfactant assisted solvothermal synthesis of ZnO nanoparticles and study of their antimicrobial and antioxidant properties. *Journal of Materials Science and Technology*. http://doi.org/10.1016/j.jmst.2017.09. 014